

Spin Blockade, Spin Relaxation and Spin Dephasing, in ^{12}C and ^{13}C Nanotubes

C. M. Marcus
Harvard University

Hugh Churchill
Ferdinand Kuemmeth




Andrew Bestwick
Jennifer Harlow
Patrick Herring
Christian Barthel
David Reilly

Theory:

Karsten Flensberg (NBI Copenhagen)
Emmanuel Rashba (Harvard)




Support: NSF, Harvard NSEC,
ARO/iARPA, DoD, Harvard CNS

Pauli Blockade in a Double Quantum Dot

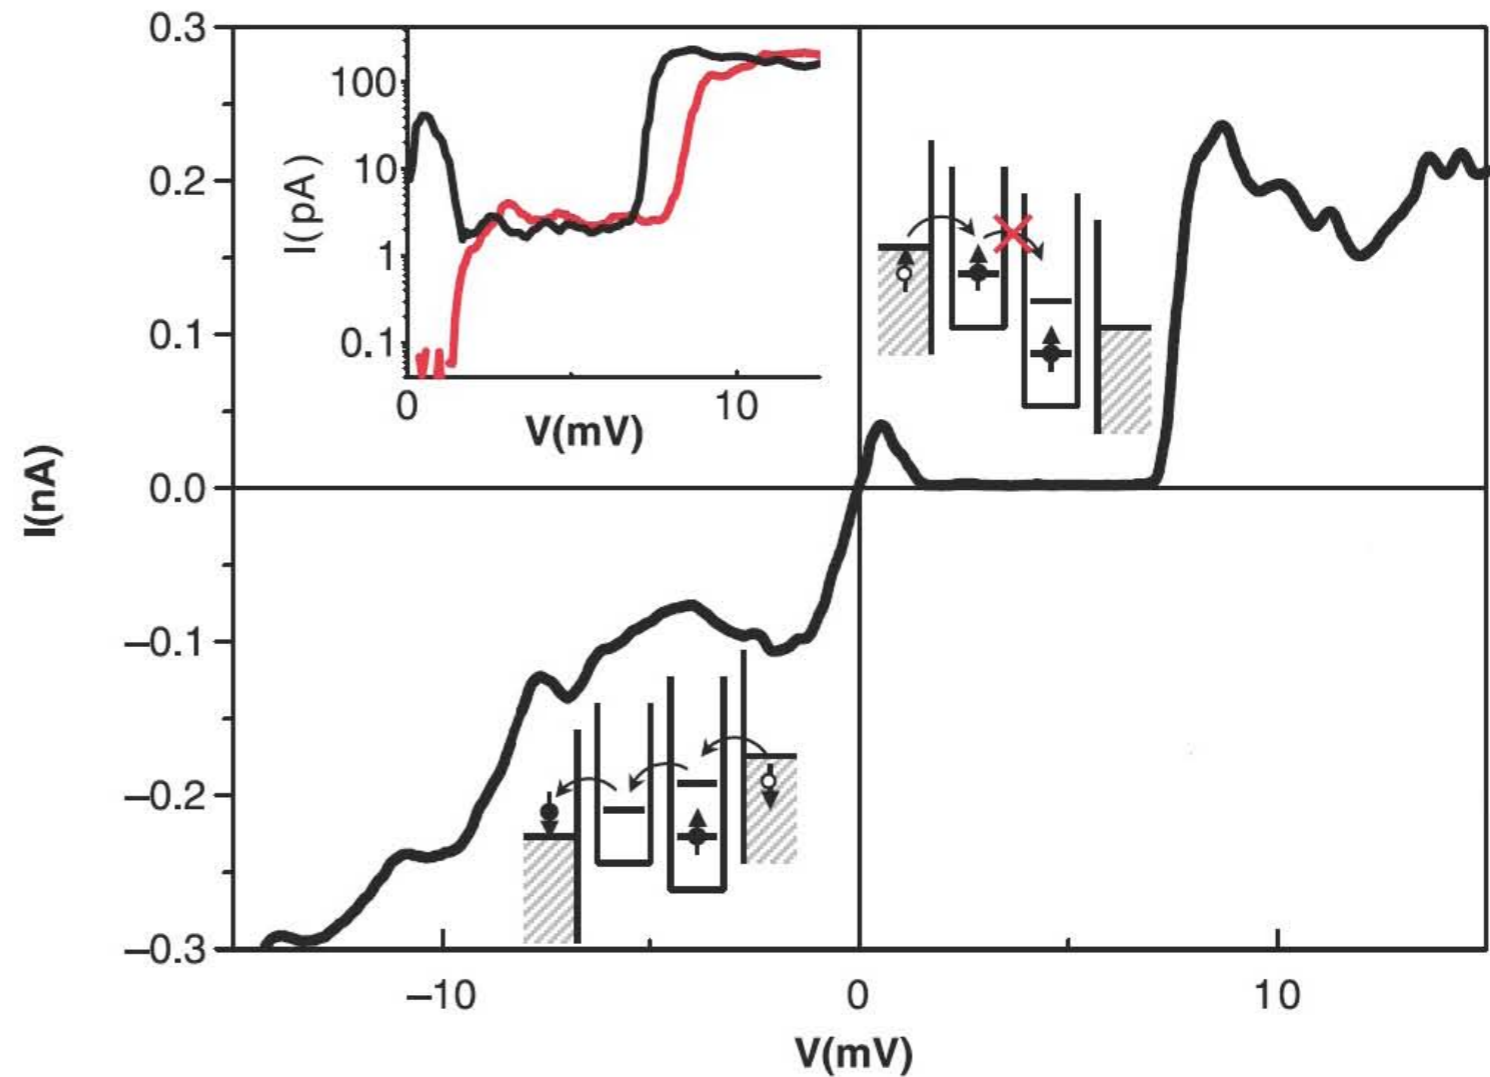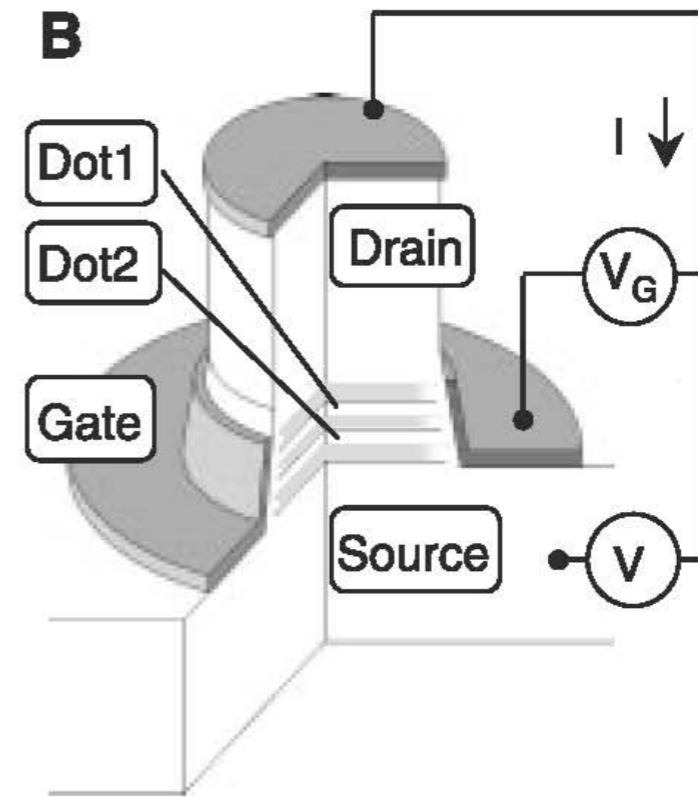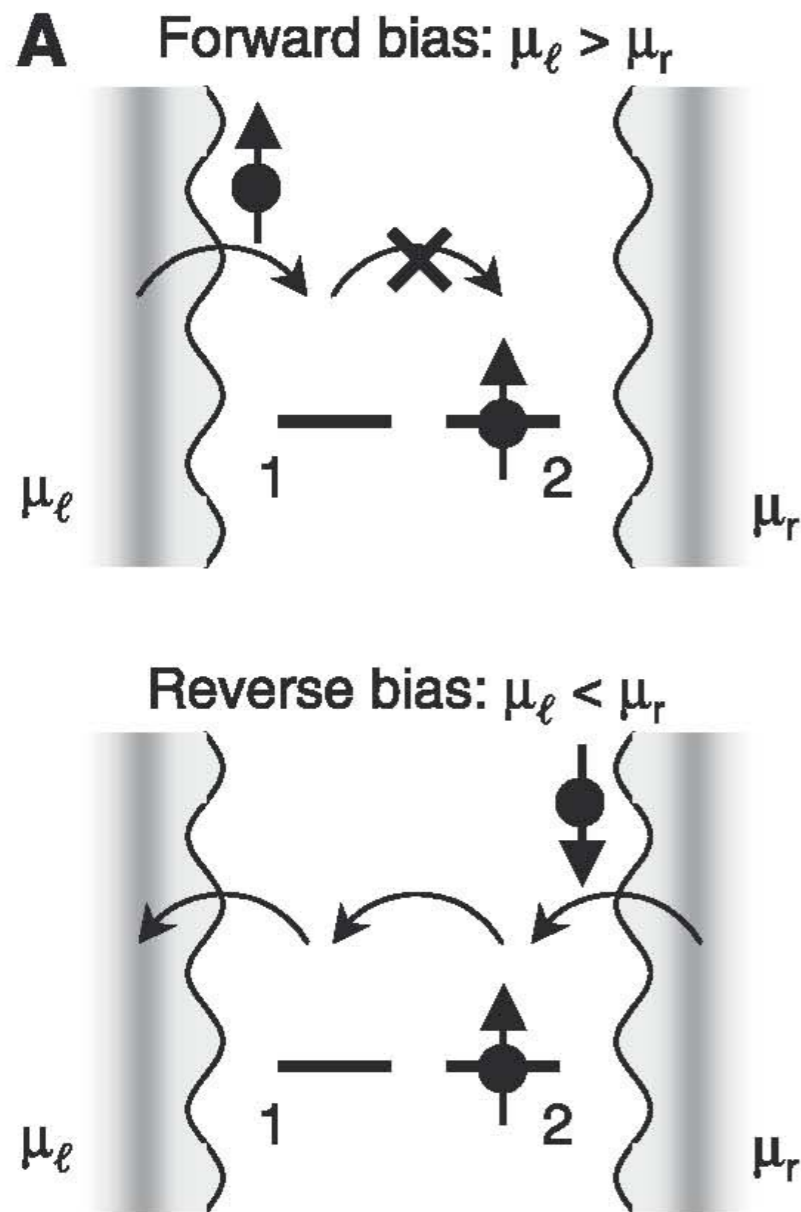


Ono, Tarucha, et al.
 Science **297**, 1313 (2002).

Spin Blockade in a Double Dot

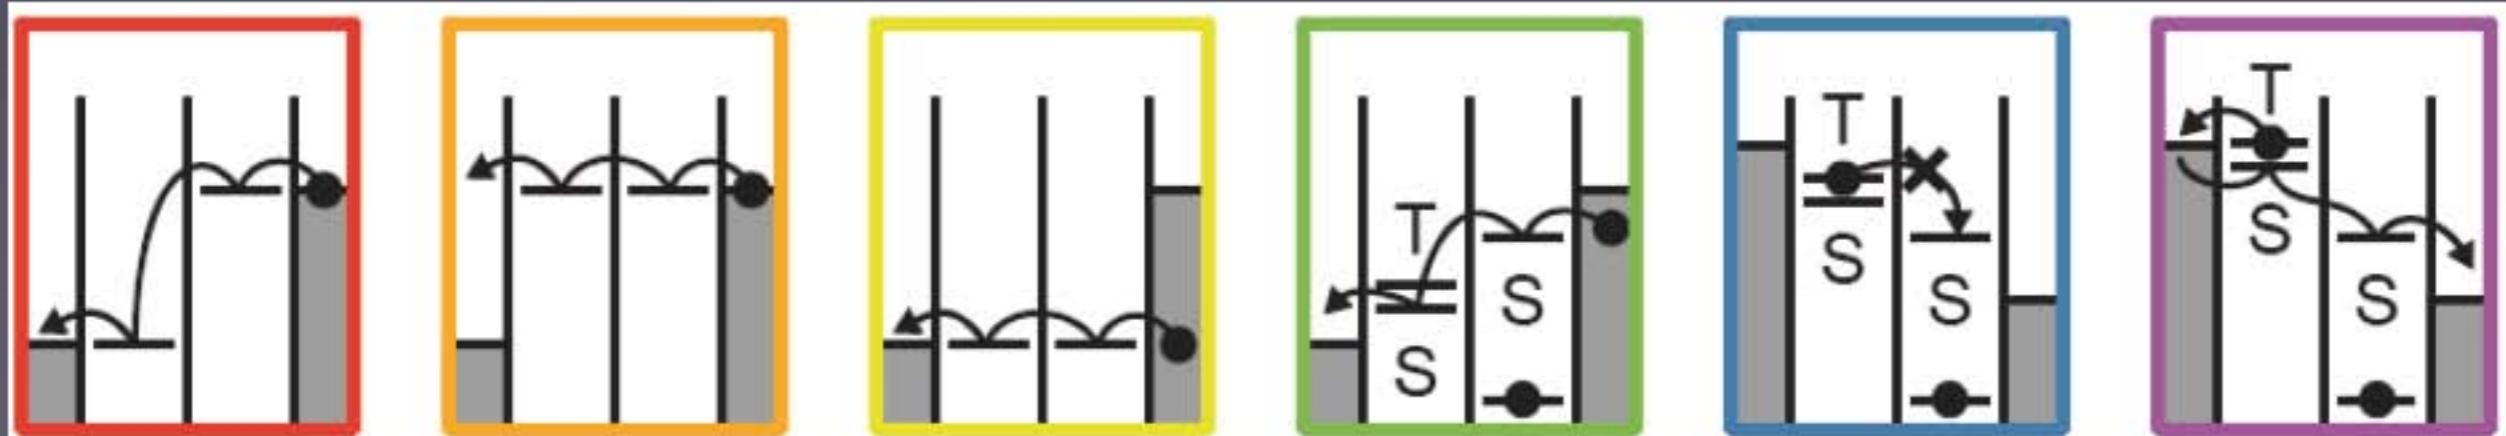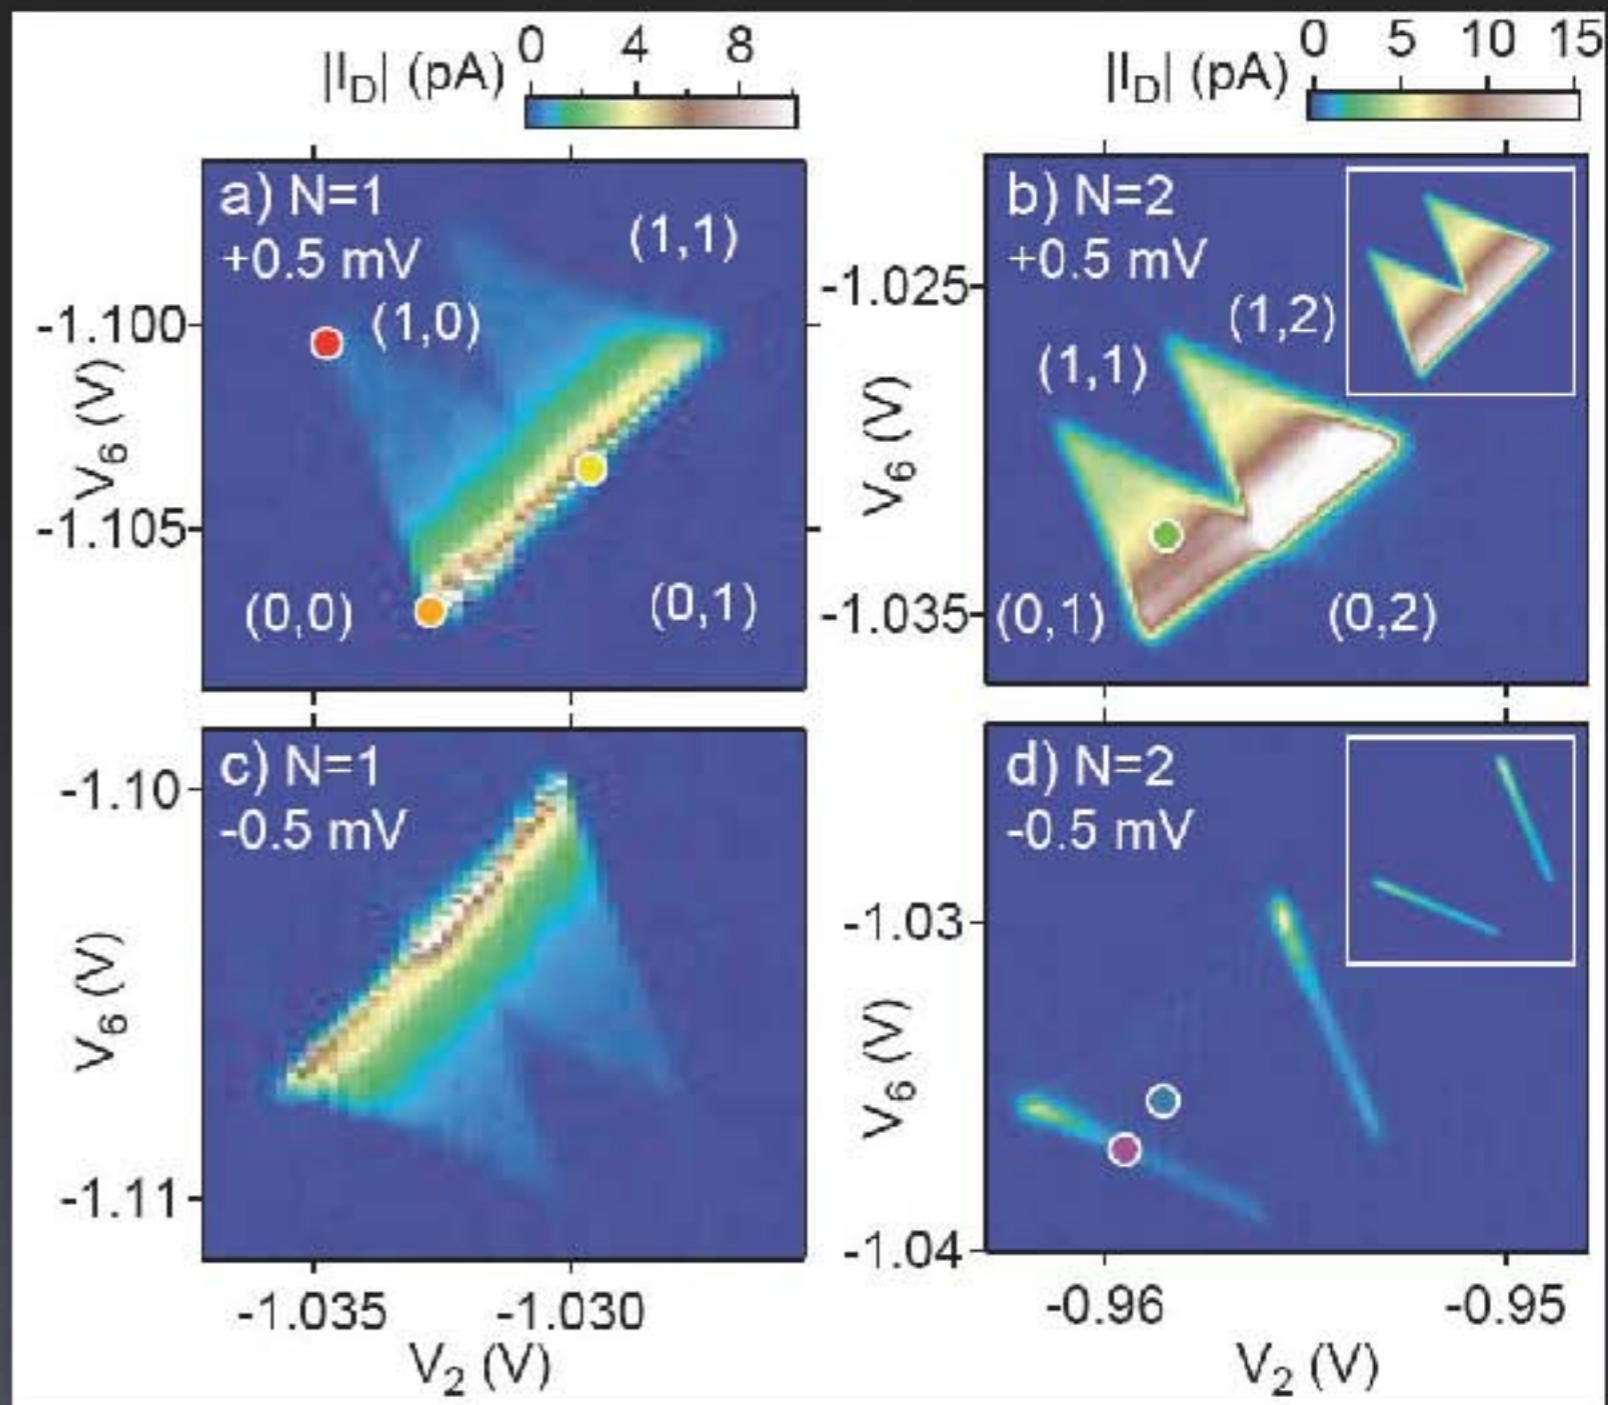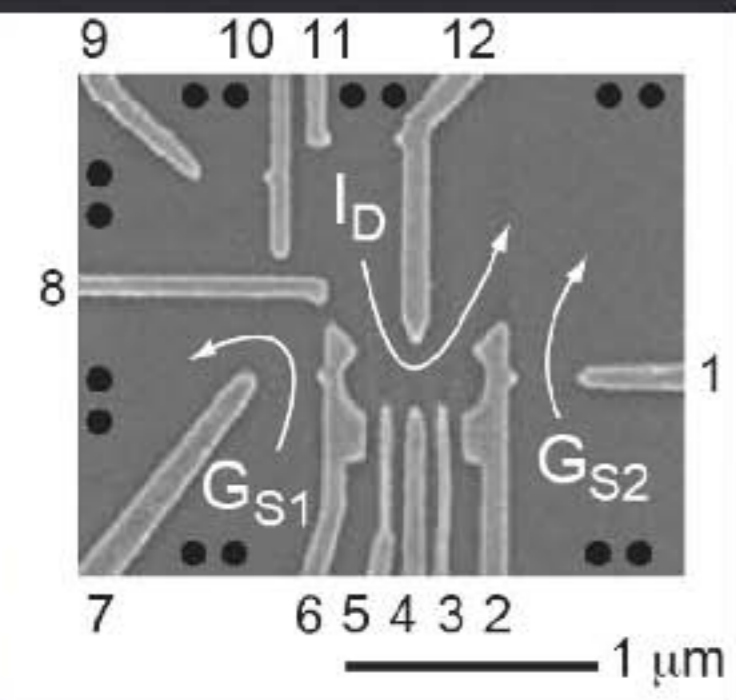

Control and Detection of Singlet-Triplet Mixing in a Random Nuclear Field




F. H. L. Koppens,^{1*} J. A. Folk,^{1*} J. M. Elzerman,¹ R. Hanson,¹
 L. H. Willems van Beveren,¹ I. T. Vink,¹ H. P. Tranitz,²
 W. Wegscheider,² L. P. Kouwenhoven,¹ L. M. K. Vandersypen^{1†}

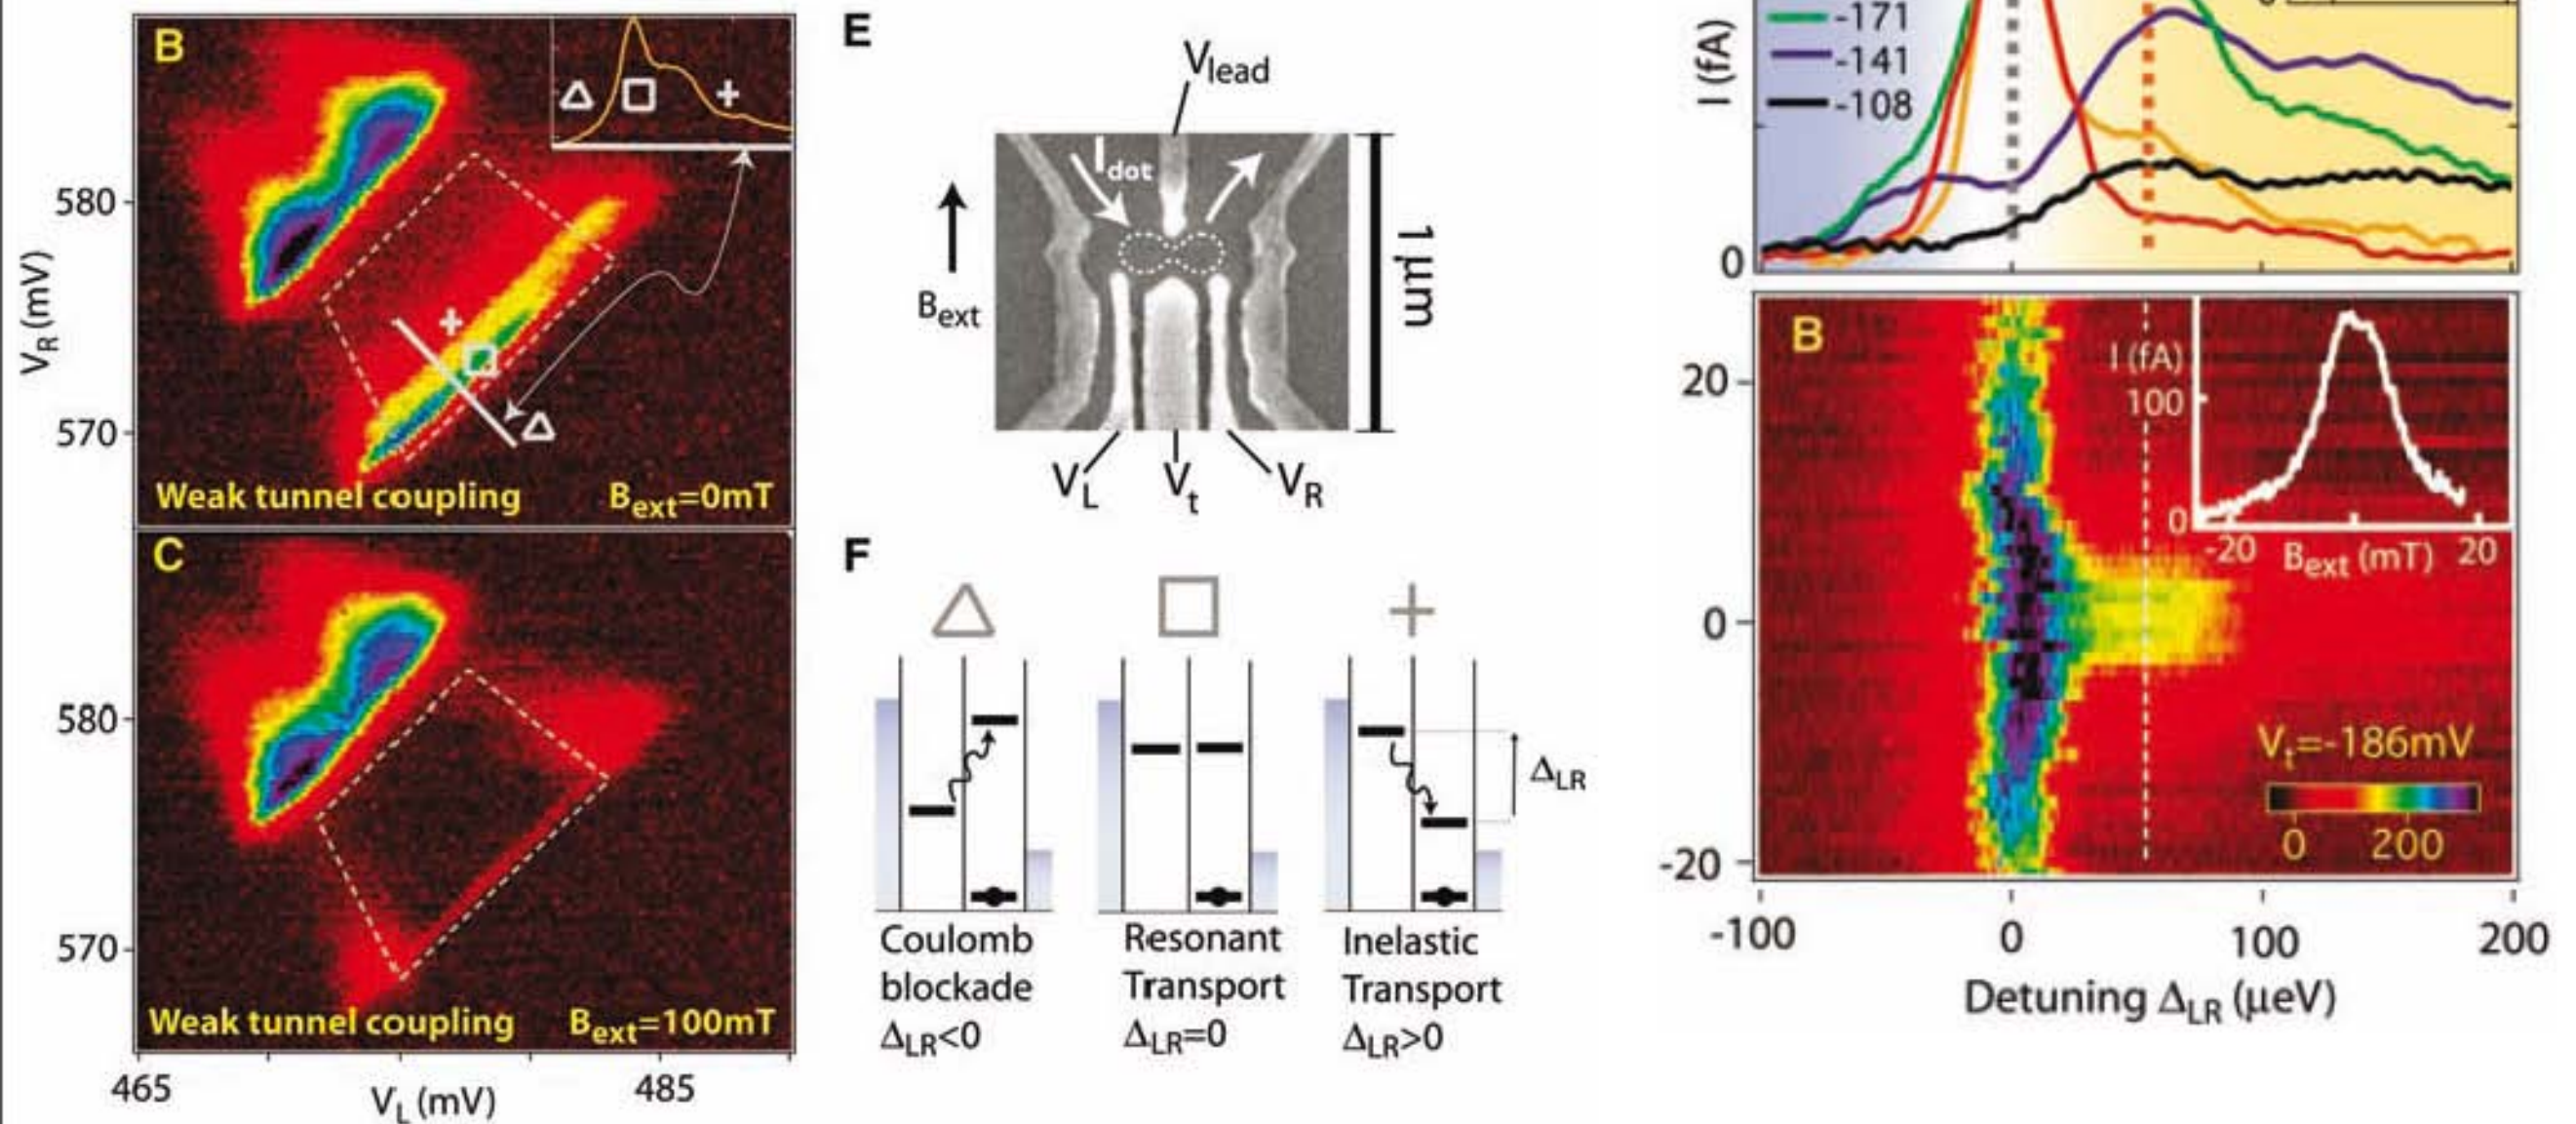




26 AUGUST 2005 VOL 309 SCIENCE

Inhomogeneous Dephasing




the situation in GaAs

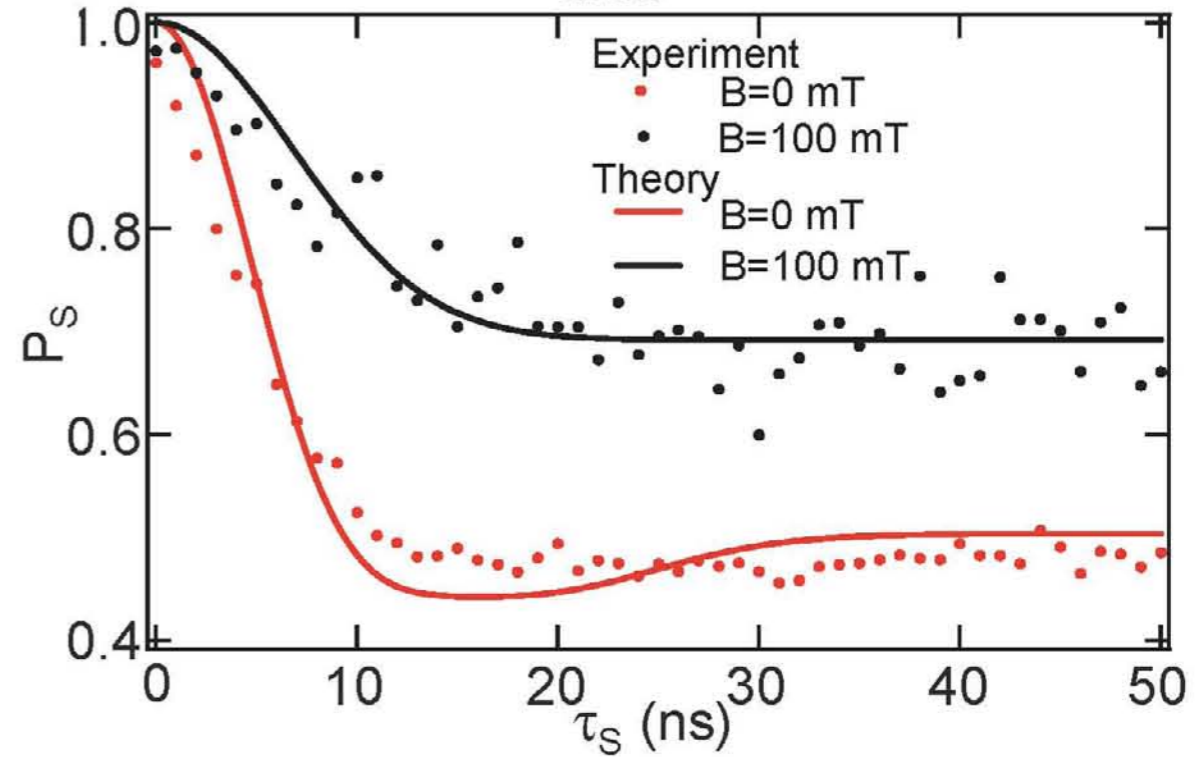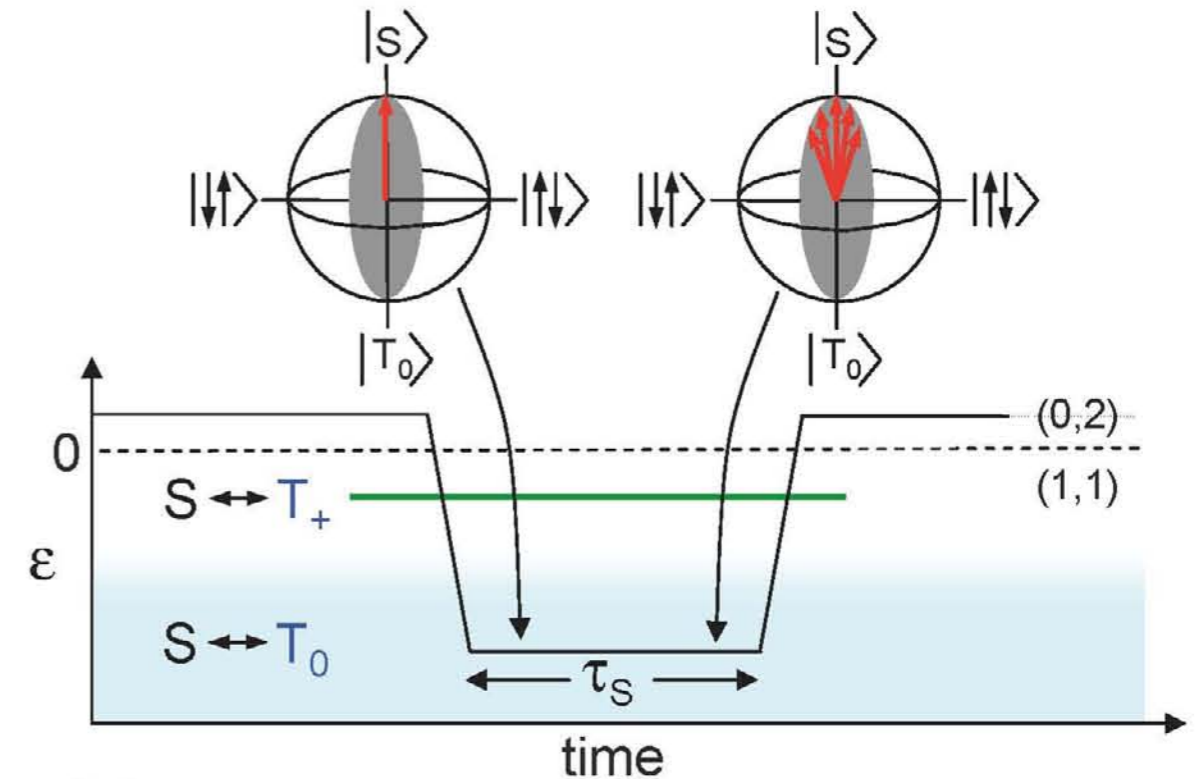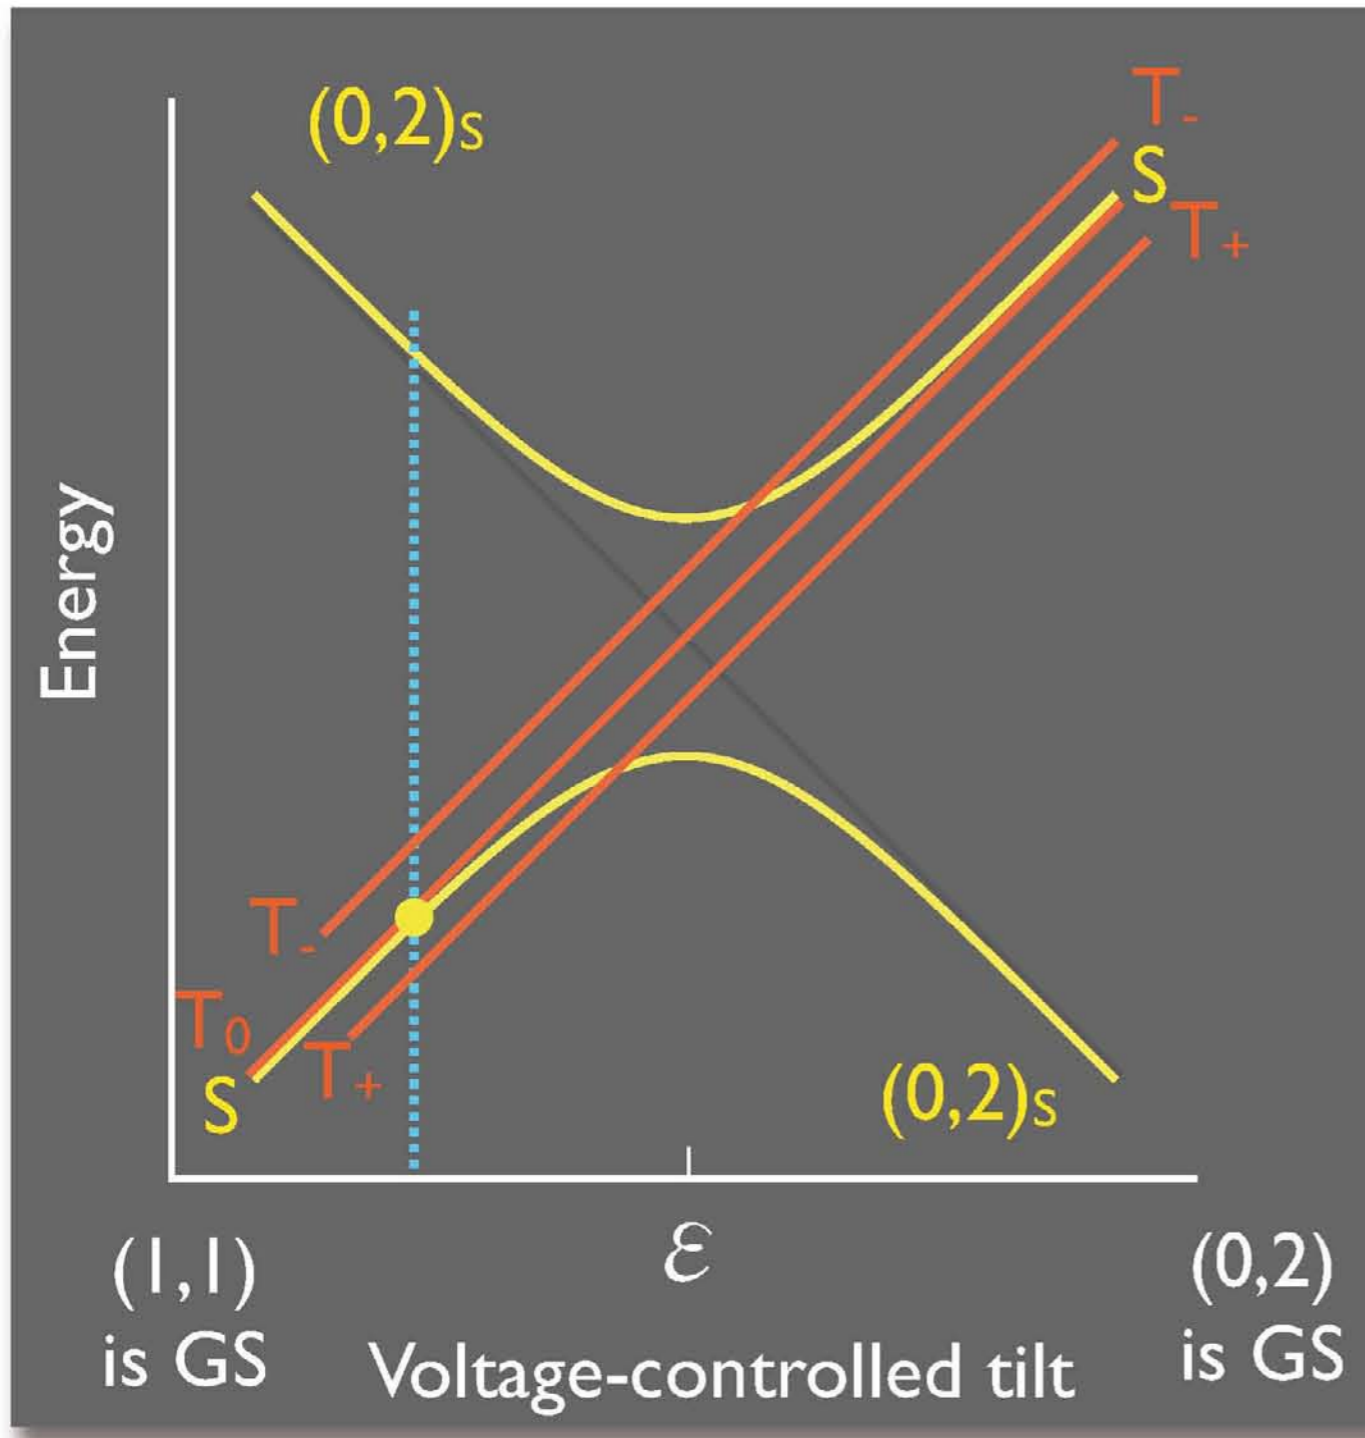


Inhomogeneous dephasing due to hyperfine fields in GaAs is revealed in single-shot measurements

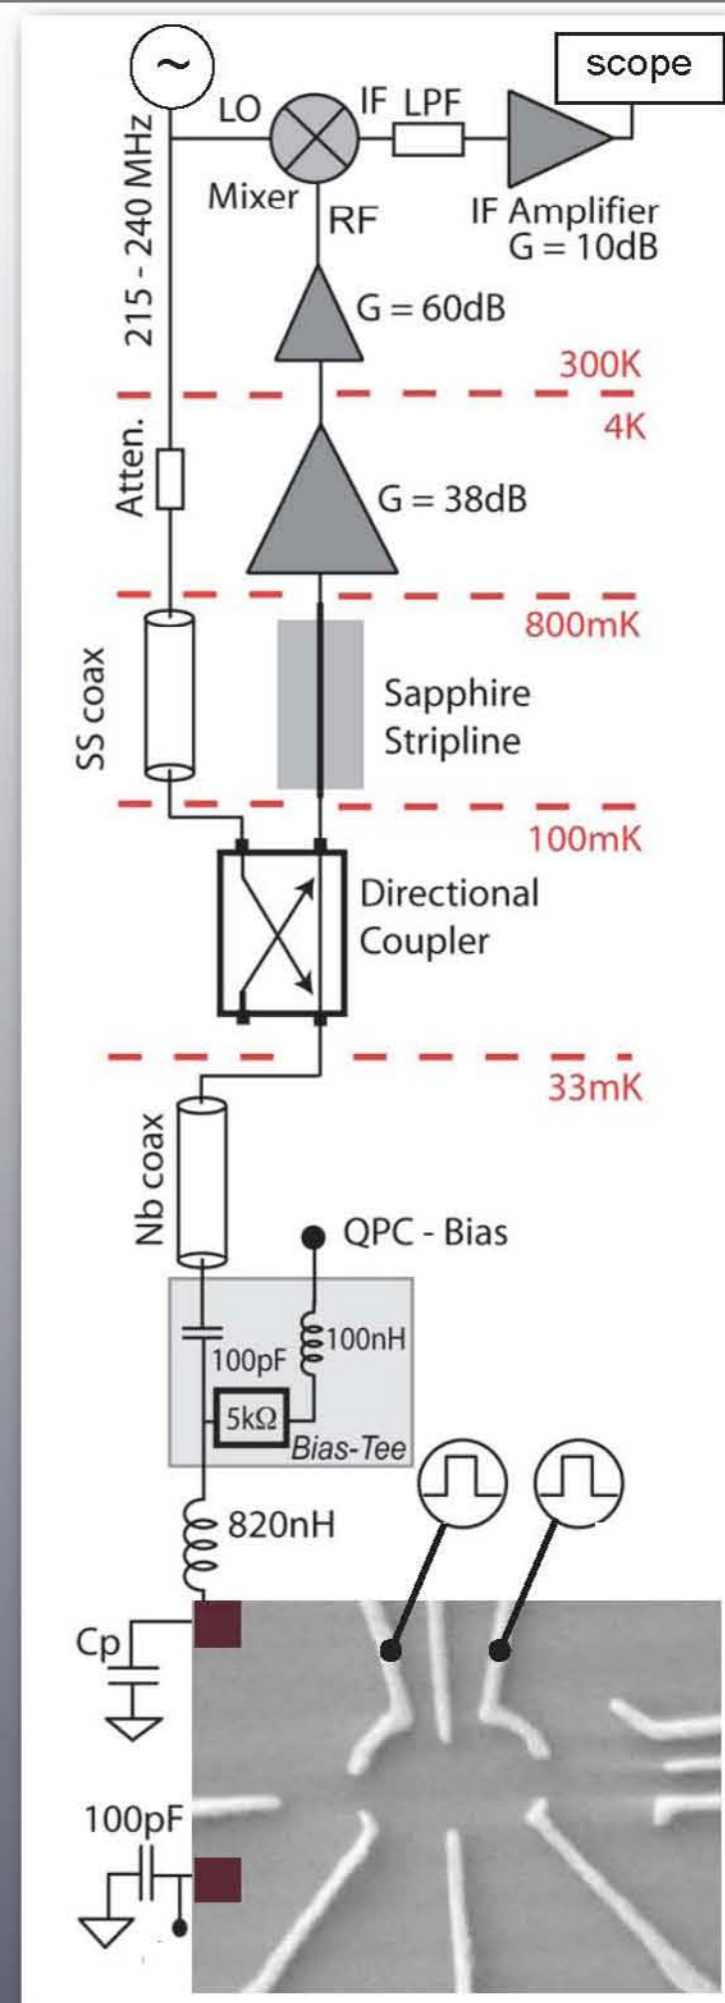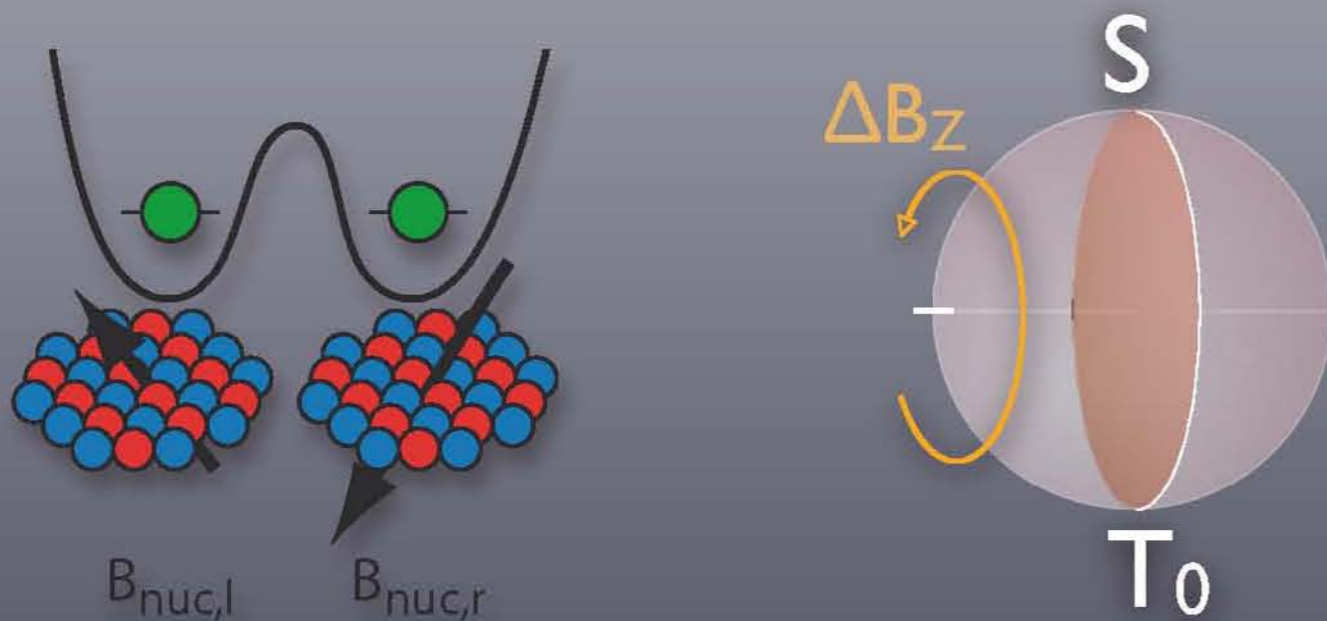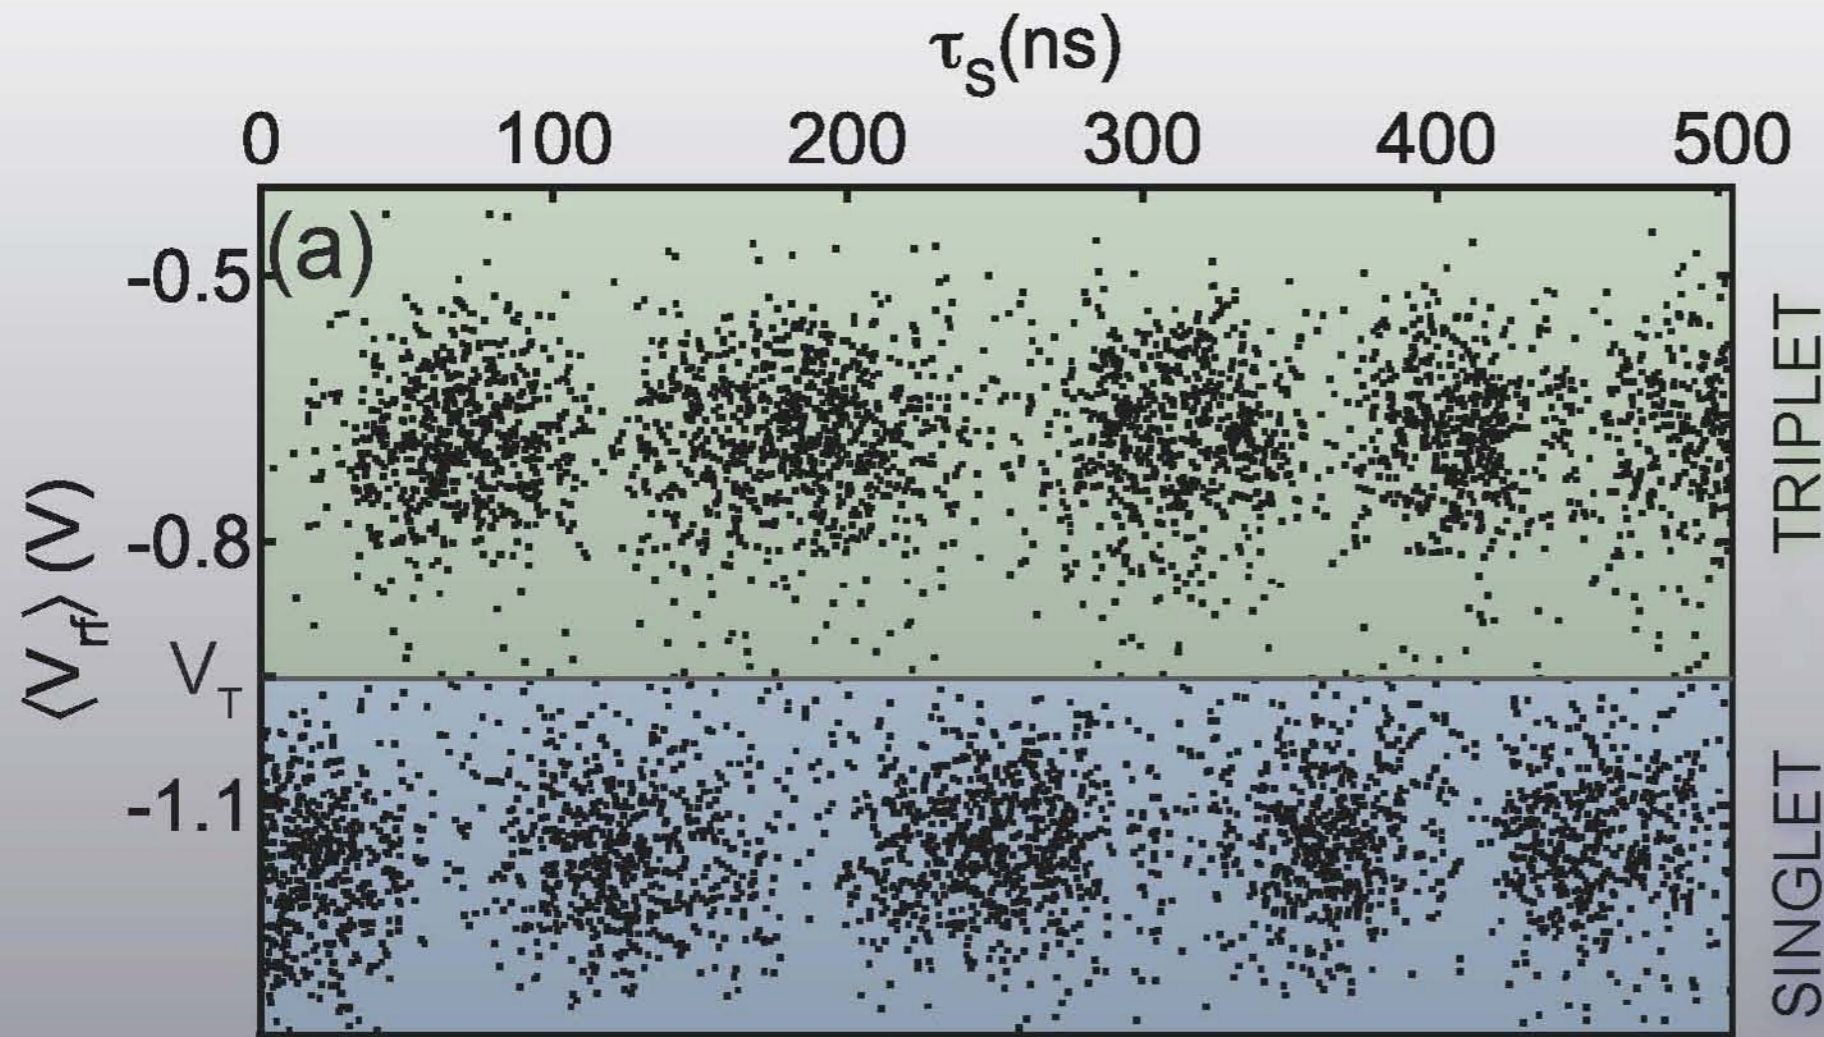


Carbon nanotubes

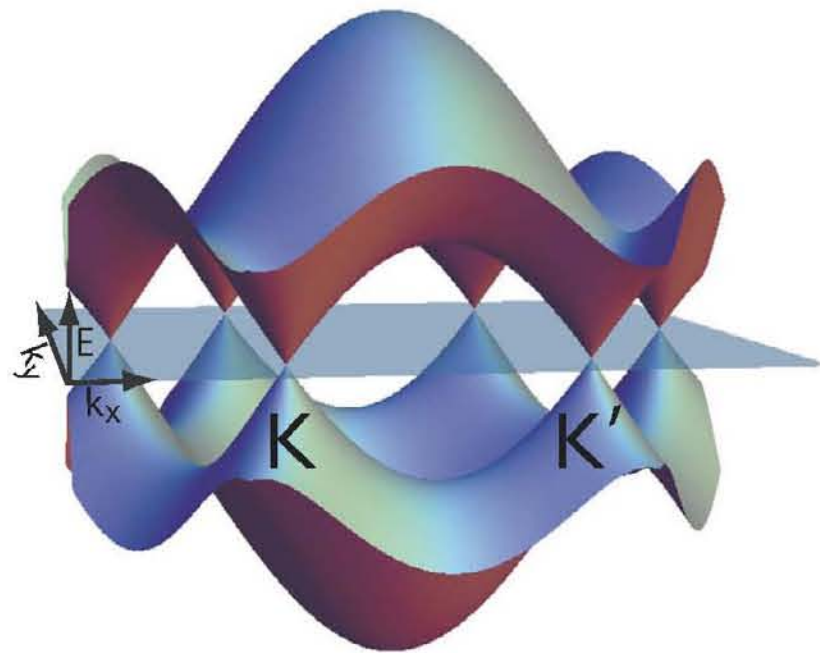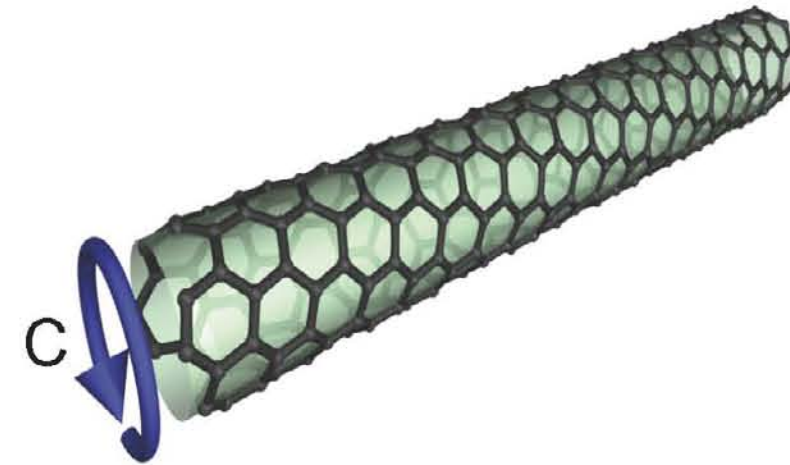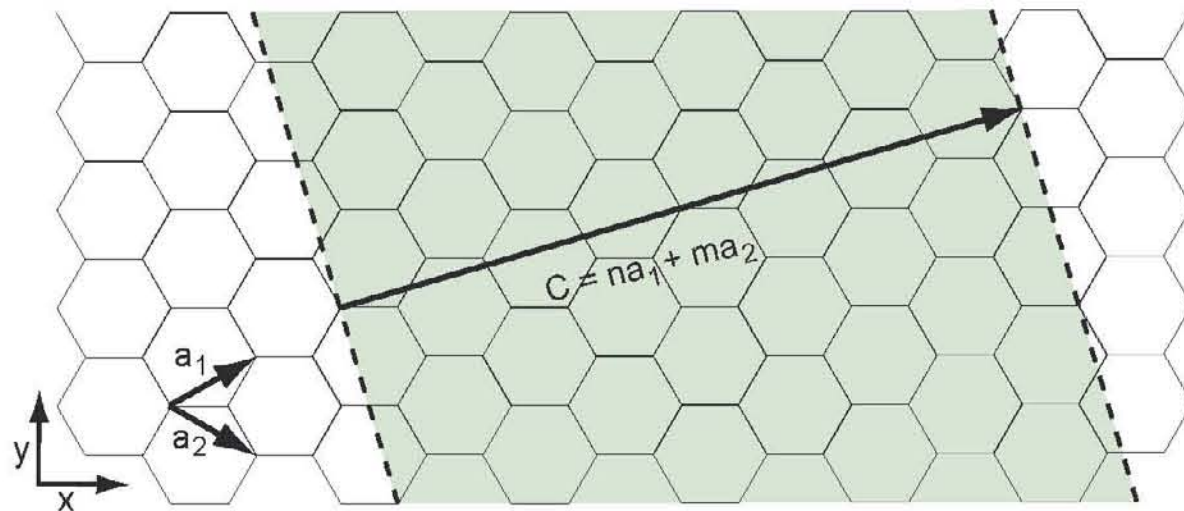

roll up
 $rk_{\perp} = \text{integer}$

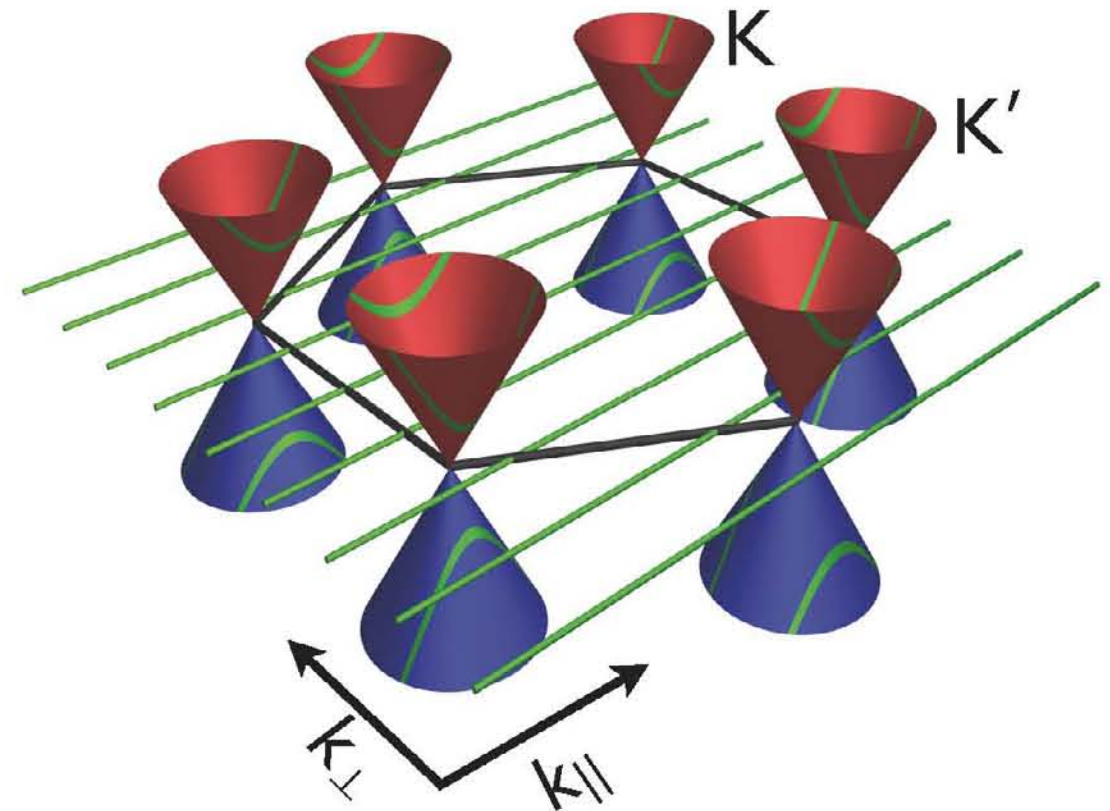


quantization around circumference gives 0 or 1.4 eV · nm/r gap

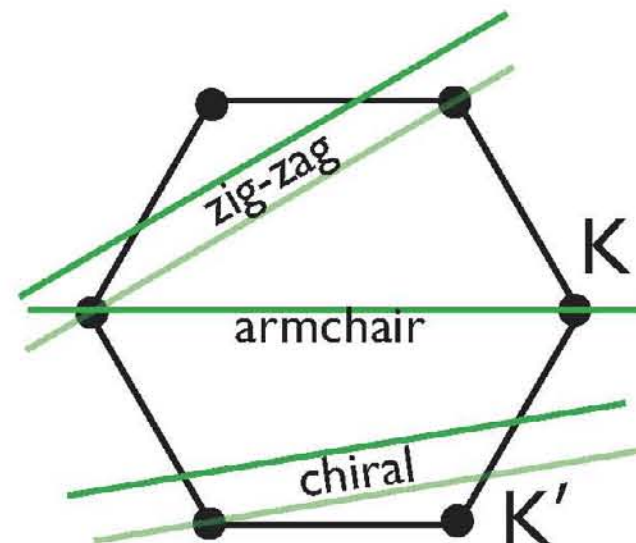

perturbations induce small ~10s meV gaps

Controlling Hyperfine Coupling using Nanotube Quantum Dots





- CVD growth with 99% $^{12}\text{C}\text{H}_4$ or 99% $^{13}\text{C}\text{H}_4$

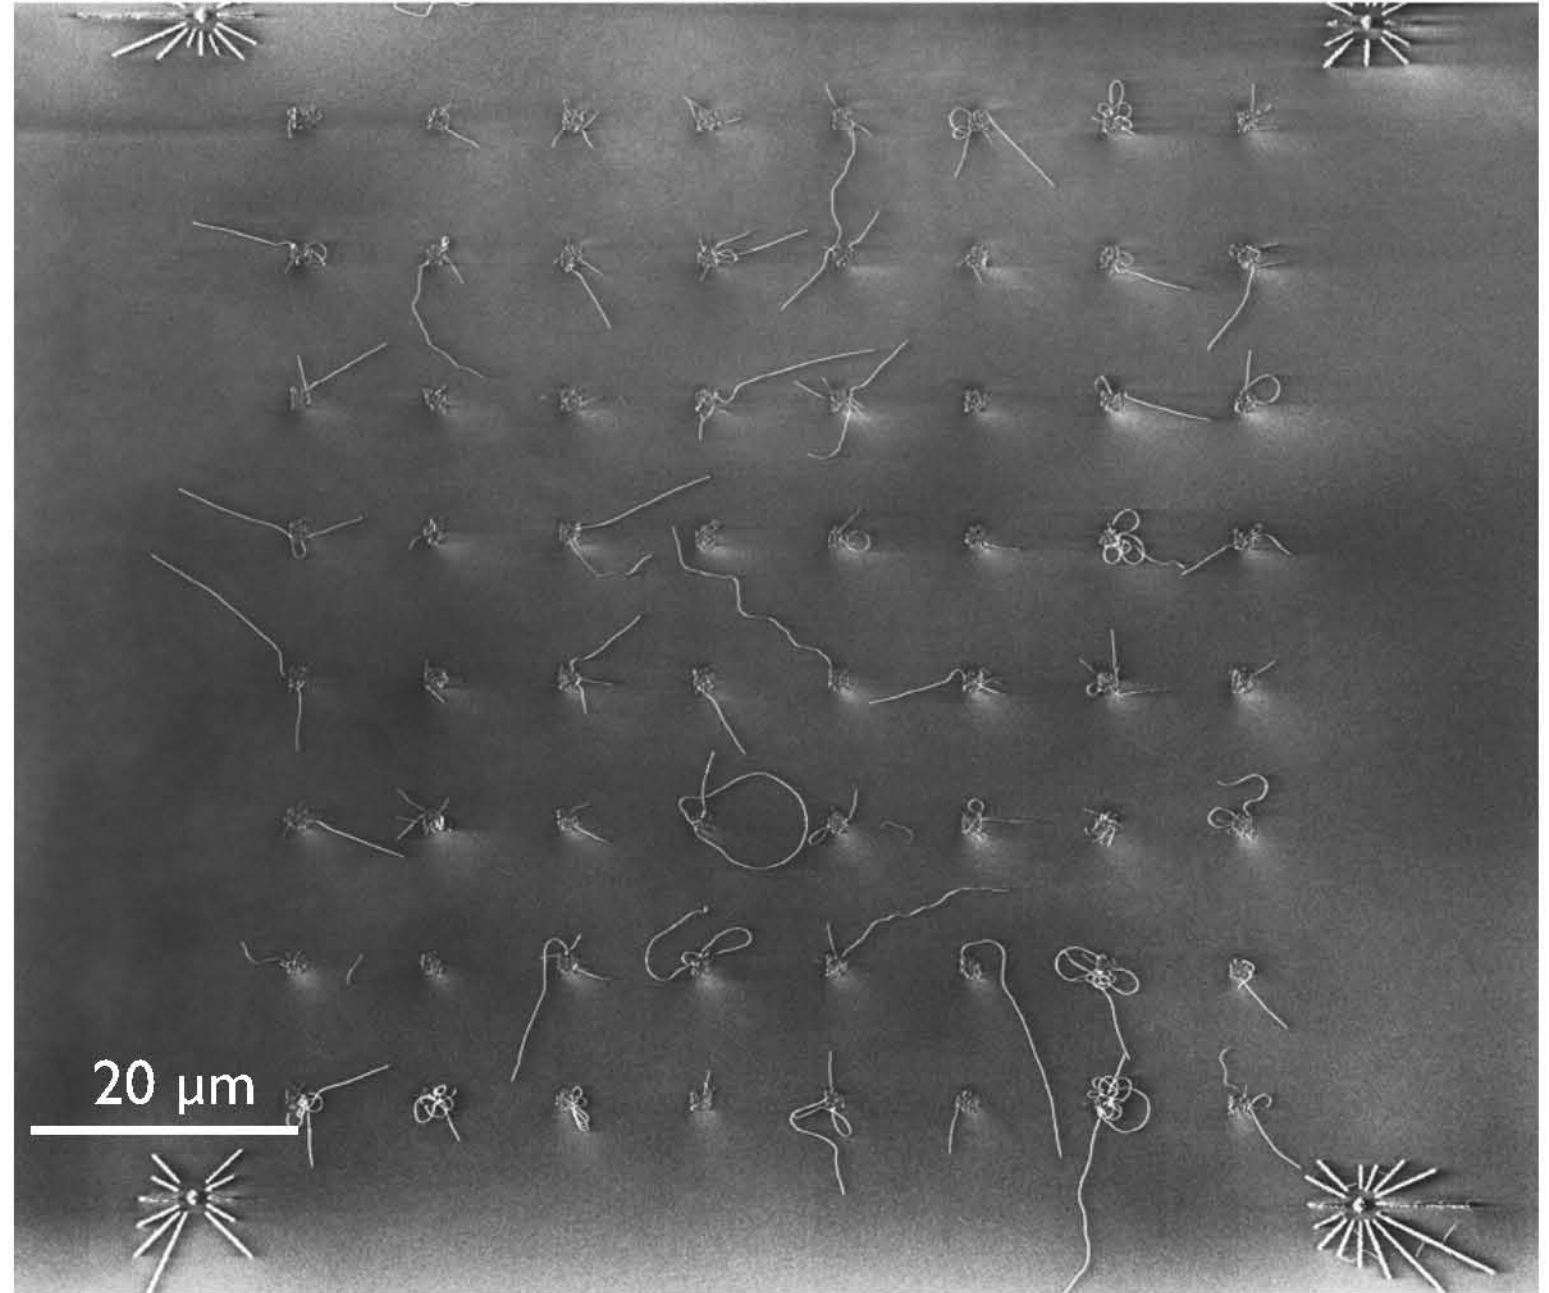

$^{13}\text{C}\text{H}_4$

Controlling Hyperfine Coupling using Nanotube Quantum Dots





- Pd contacts

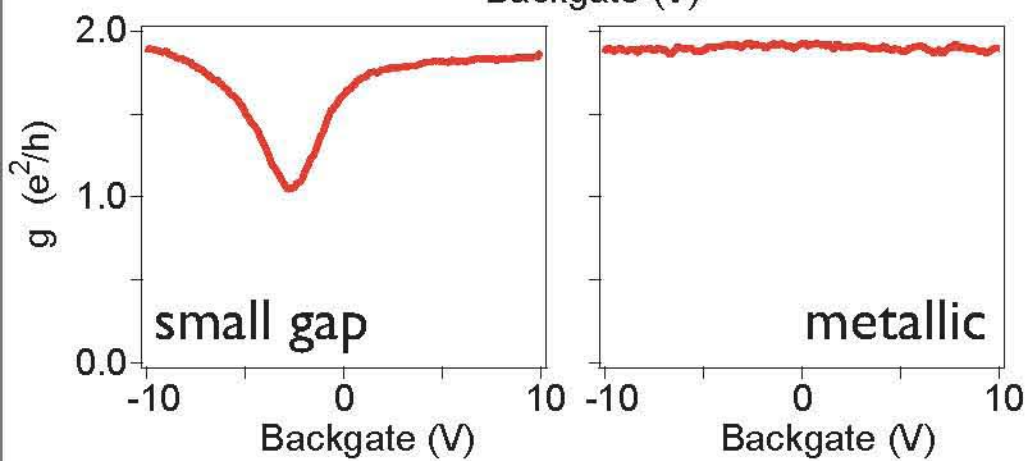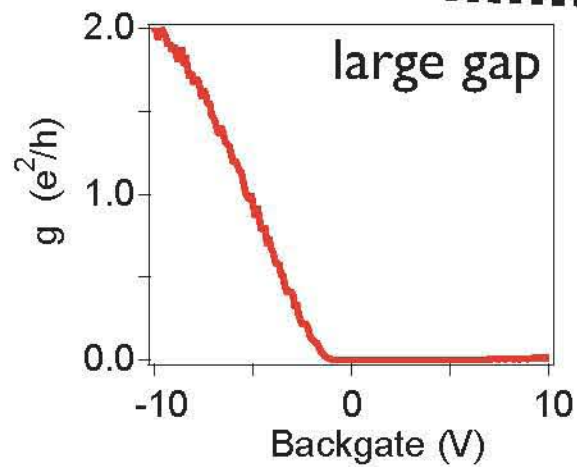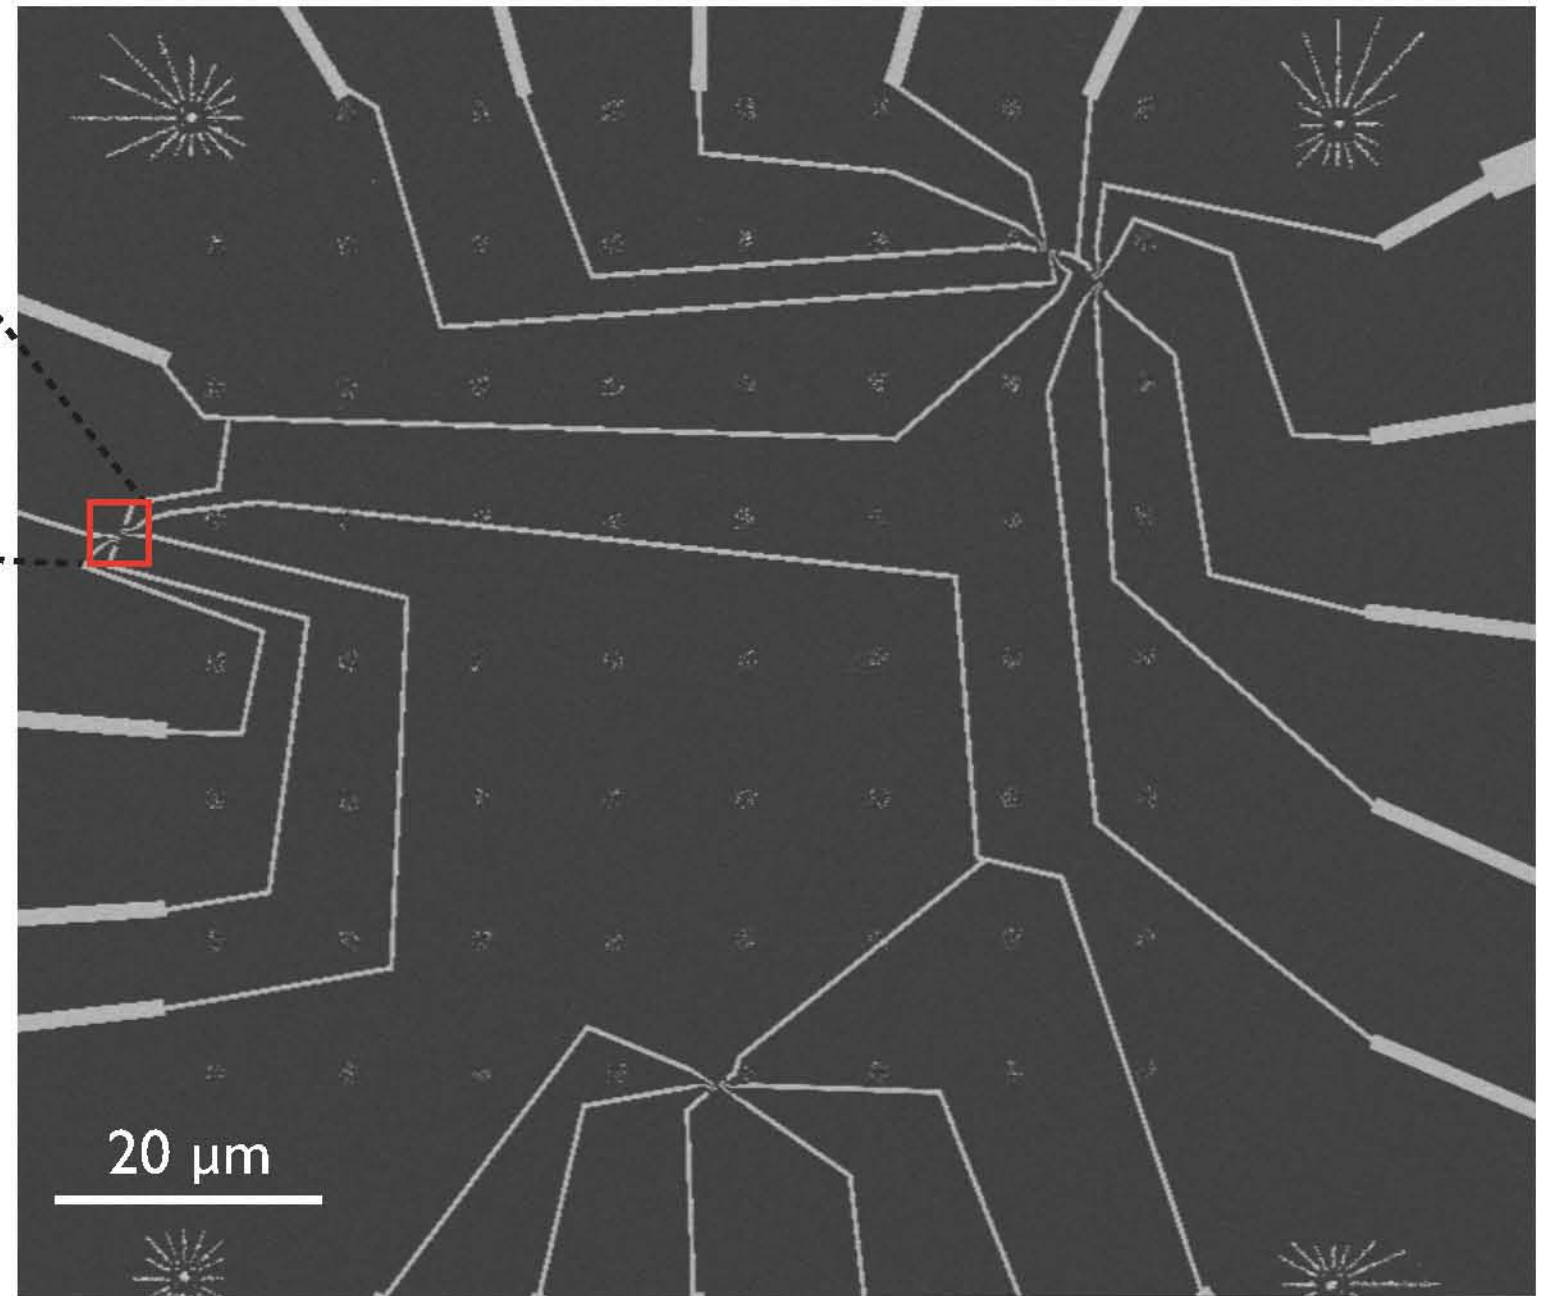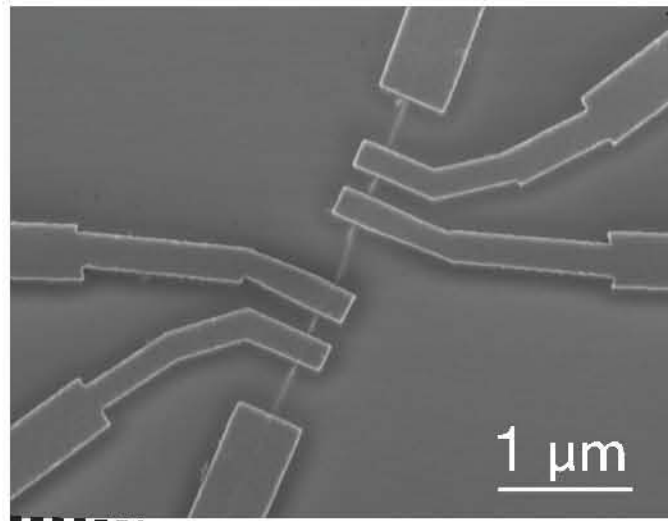

Controlling Hyperfine Coupling using Nanotube Quantum Dots




- Pd contacts

- $\text{NO}_2 + \text{Al}_2\text{O}_3$ ALD

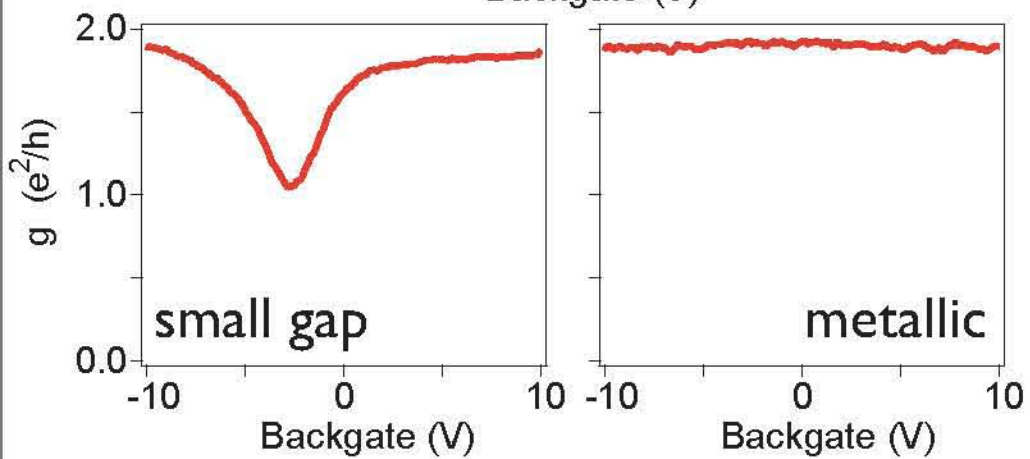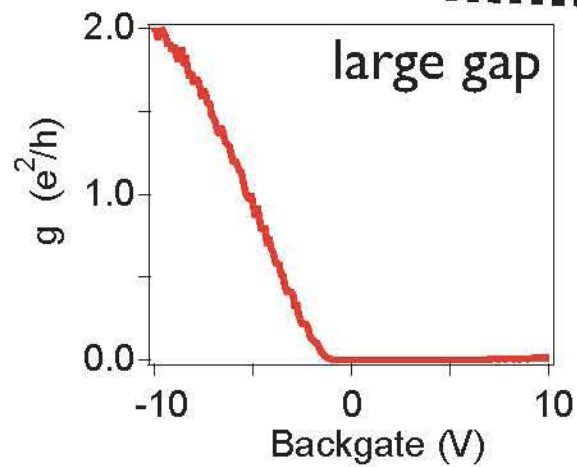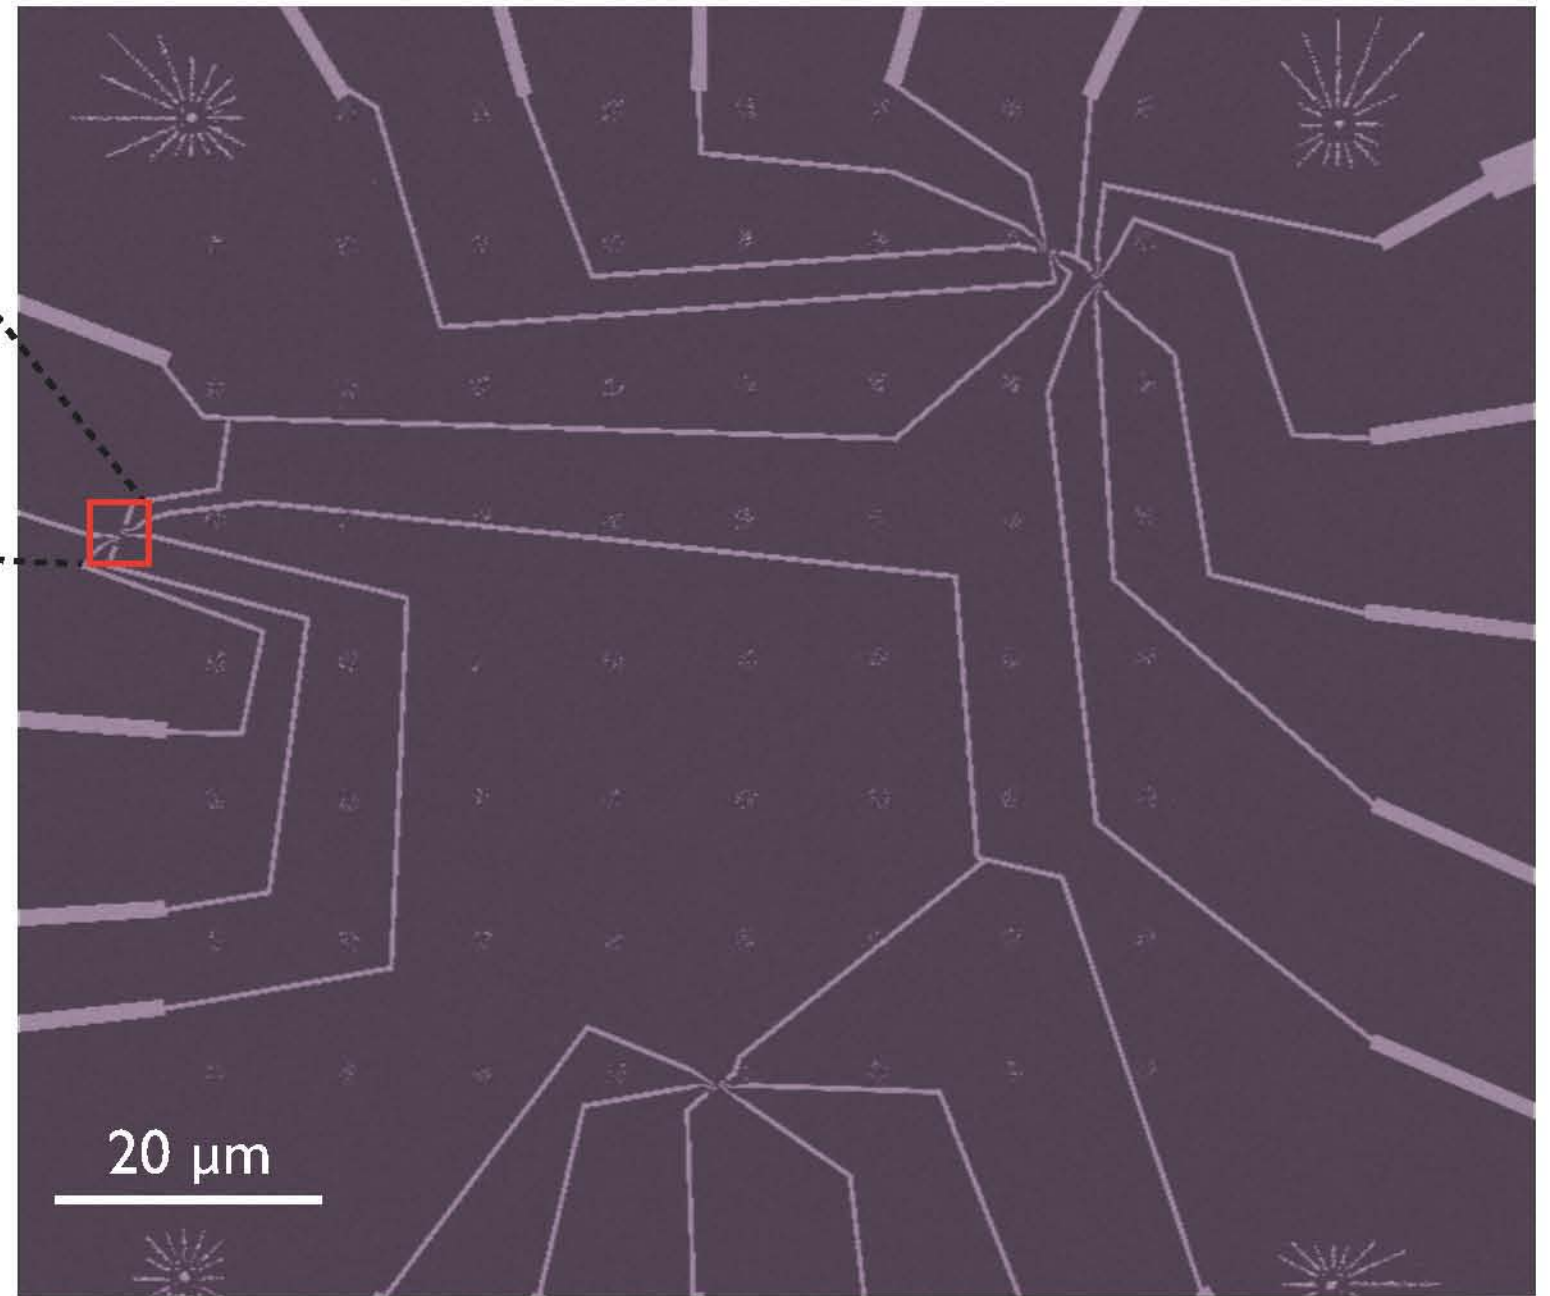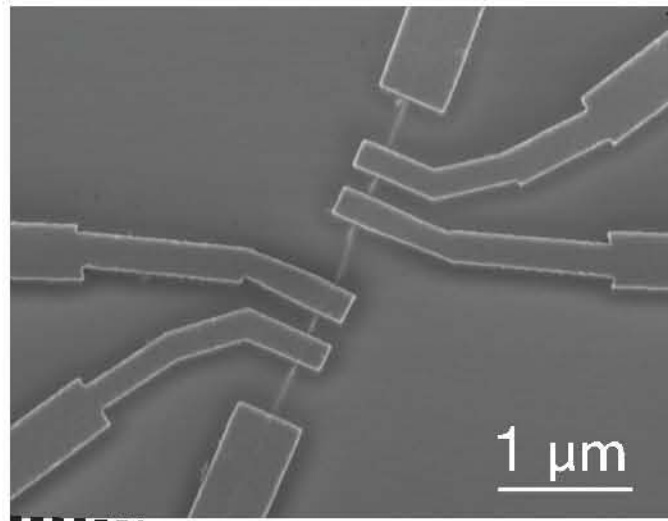


Controlling Hyperfine Coupling using Nanotube Quantum Dots

- Pd contacts

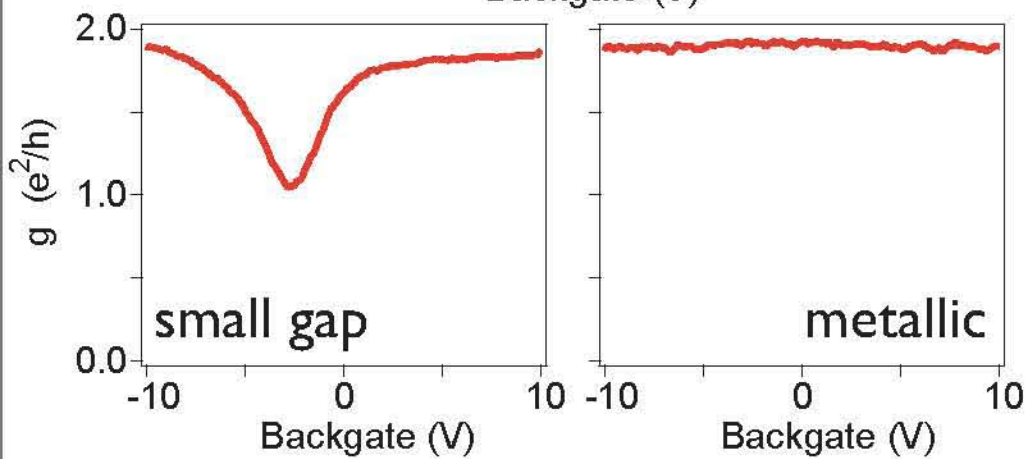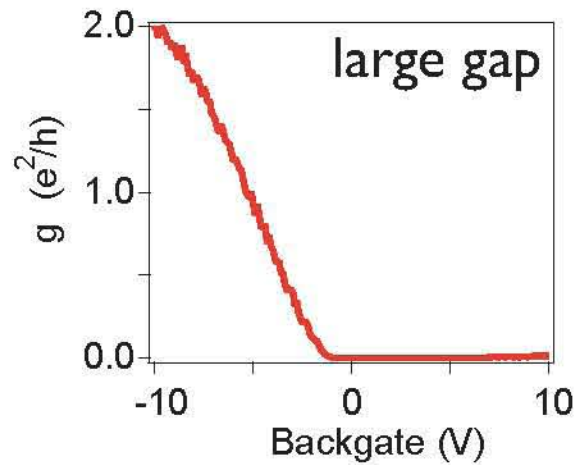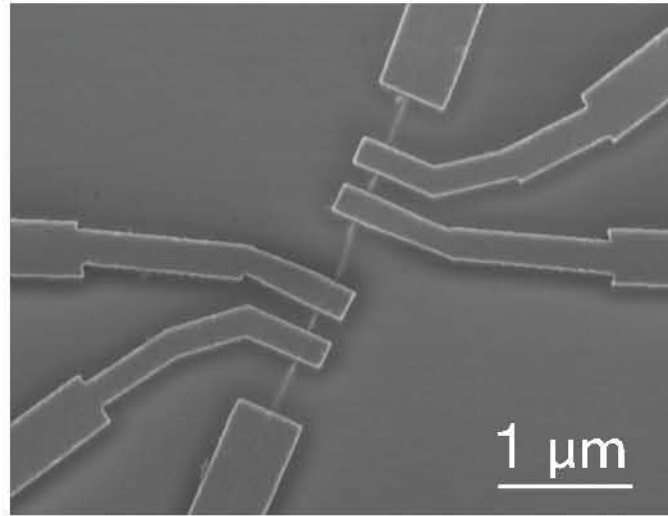


- $\text{Al}_2\text{O}_3 + \text{NO}_2$ ALD

- Al top gates

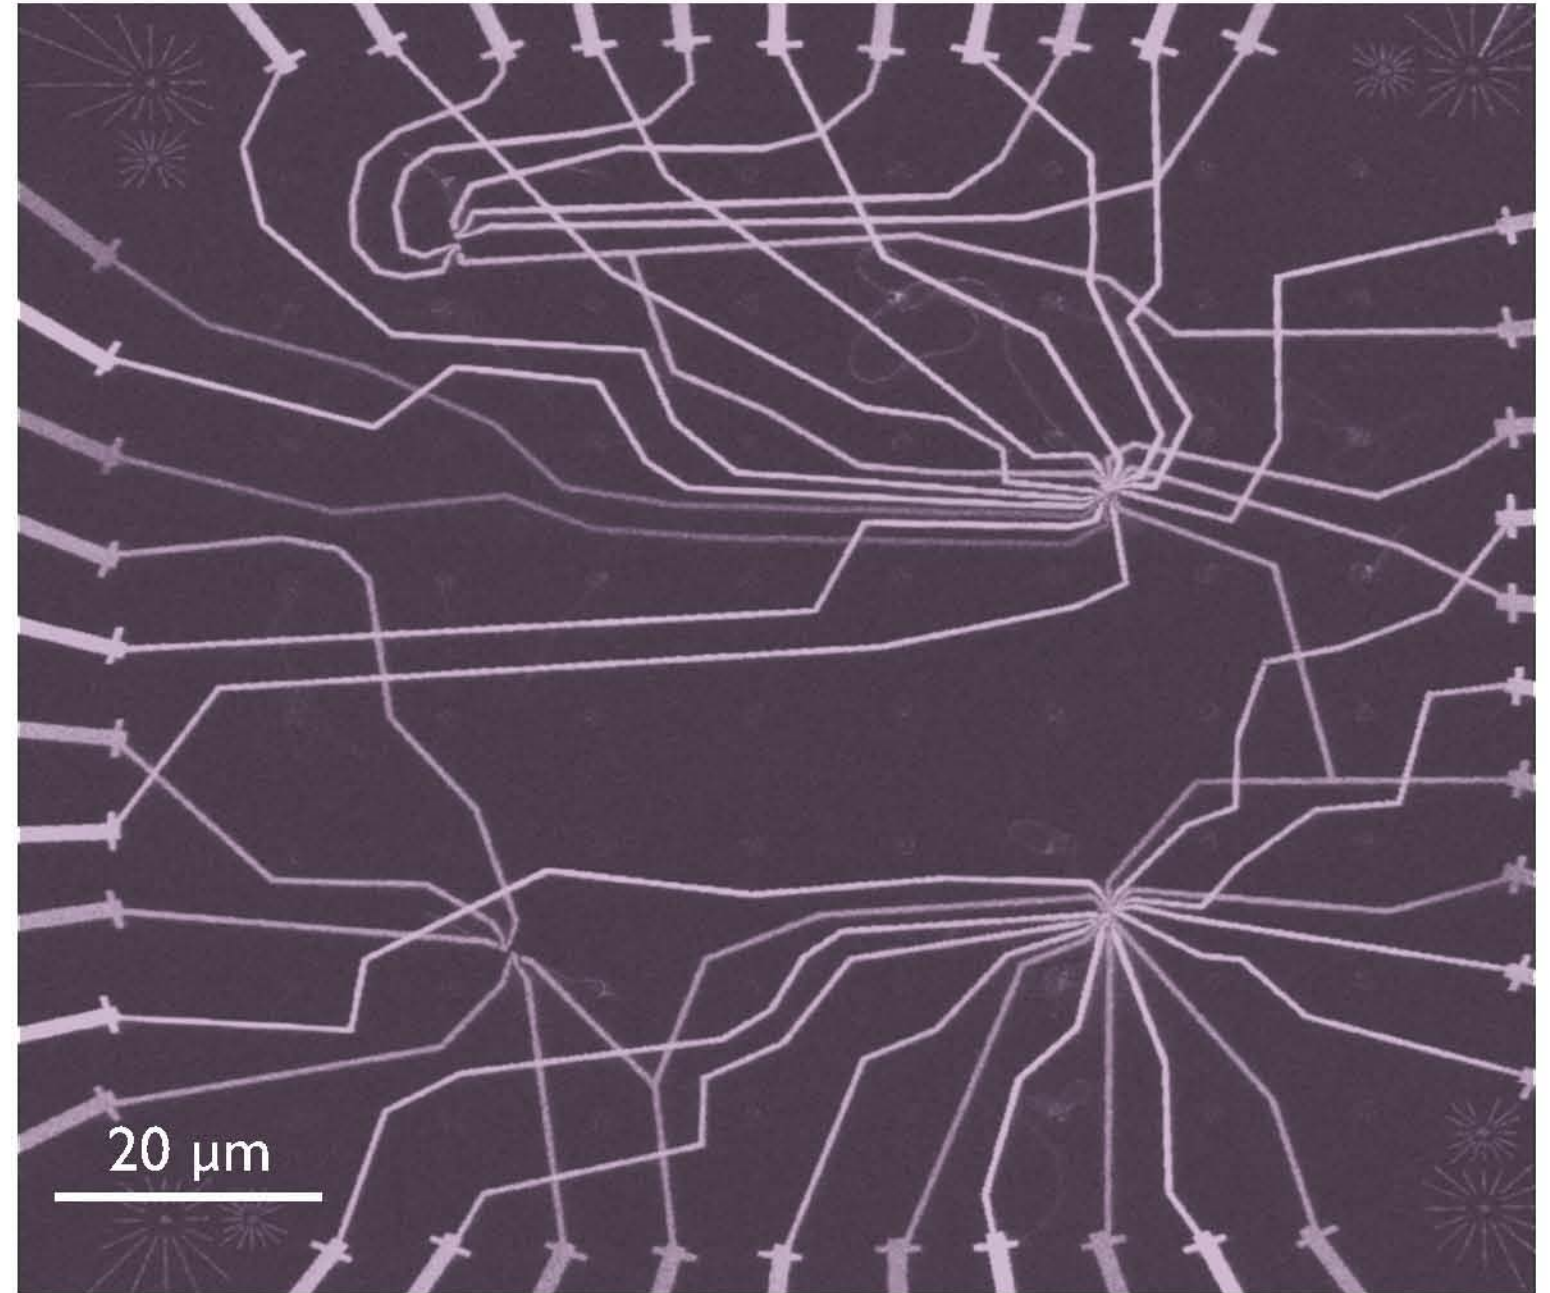

Devices

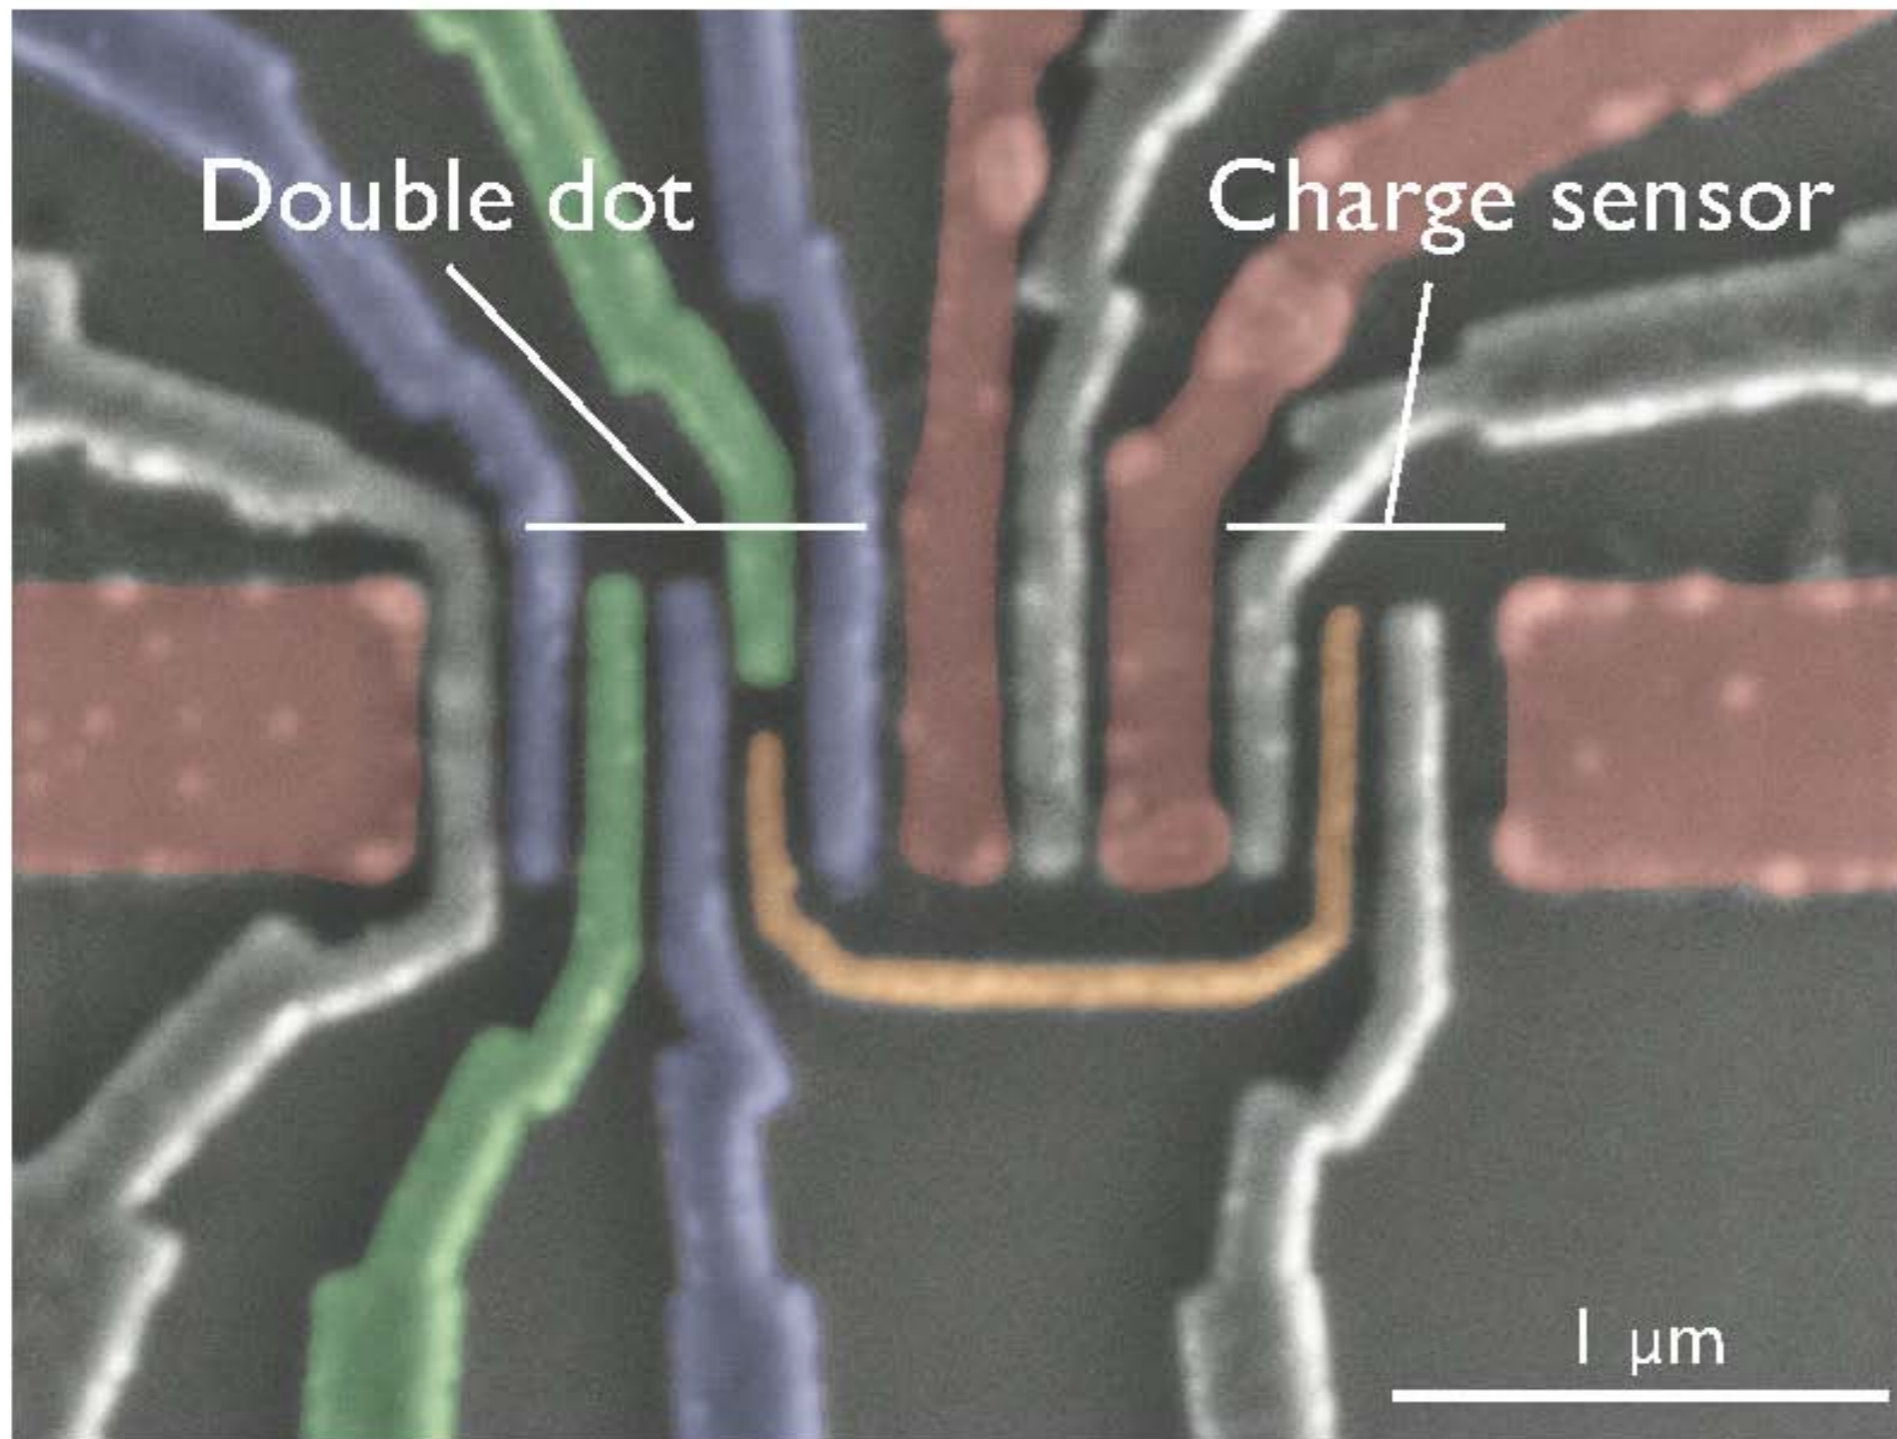

- CVD growth with $^{12}\text{CH}_4$ or $^{13}\text{CH}_4$
- Fe catalyst
- Pd contacts
- $\text{Al}_2\text{O}_3 + \text{NO}_2$ ALD
- Al top gates

Related work

DQDs: Biercuk *et al.* Nano Lett. (2005)
Sapmaz *et al.*, Nano Lett. (2006)


Graeber *et al.* PRB (2006)
Jorgensen *et al.* Nat. Phys. (2008)

Single dot charge sensing: Biercuk *et al.* PRB (2006)

$^{13}\text{CH}_4$: Liu and Fan, JACS (2001)

NO_2 : Farmer and Gordon, Nano Lett. (2006)
Williams *et al.*, Science (2007)

Devices

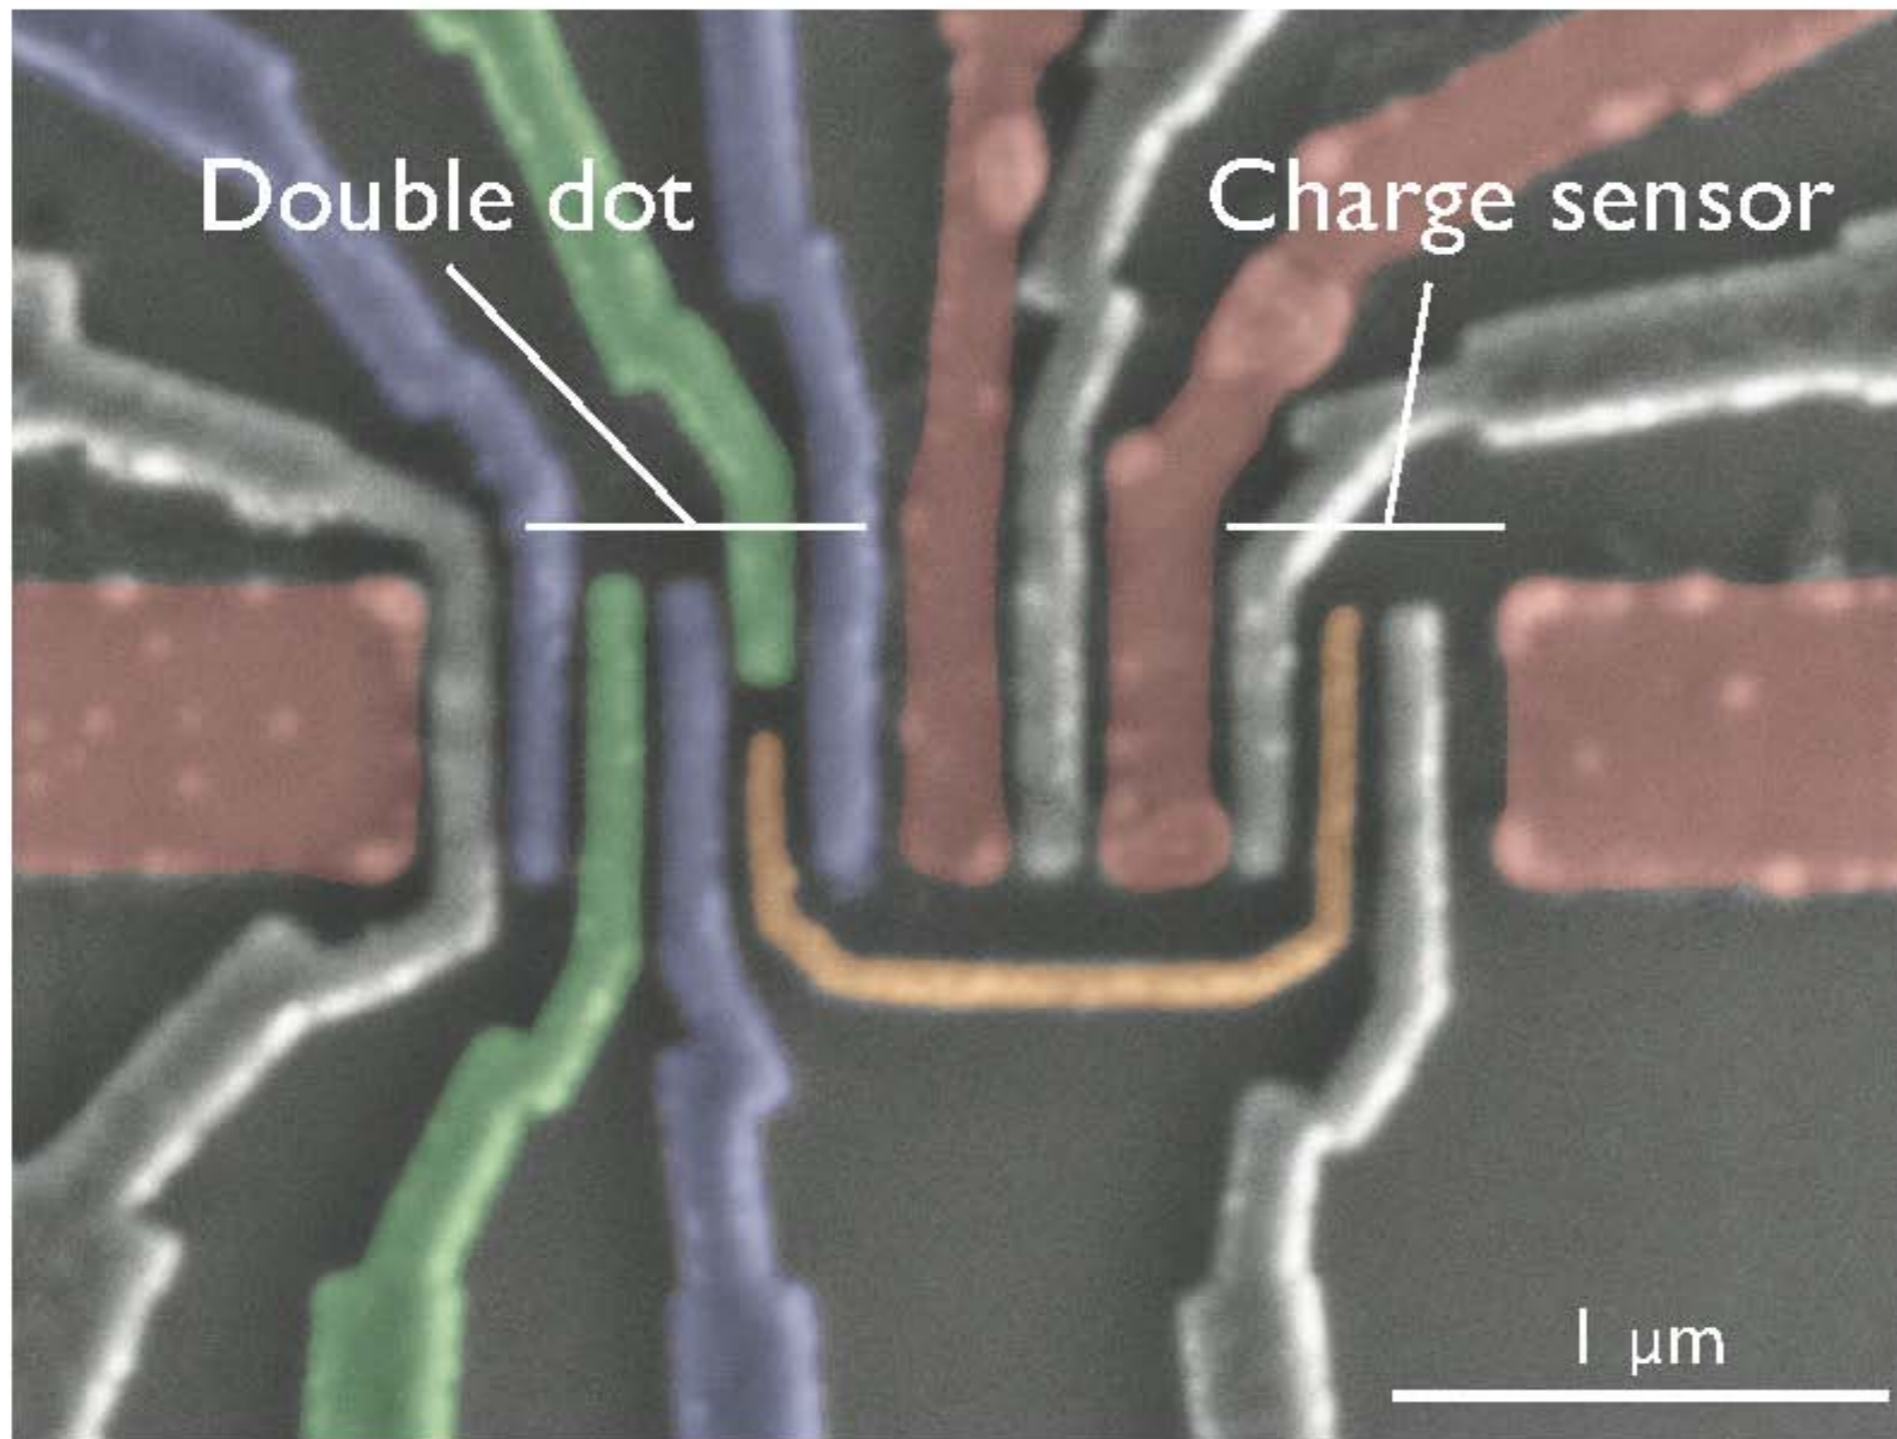

- CVD growth with $^{12}\text{CH}_4$ or $^{13}\text{CH}_4$
- Fe catalyst
- Pd contacts
- $\text{Al}_2\text{O}_3 + \text{NO}_2$ ALD
- Al top gates

Related work

DQDs: Biercuk *et al.* Nano Lett. (2005)
Sapmaz *et al.*, Nano Lett. (2006)


Graeber *et al.* PRB (2006)
Jorgensen *et al.* Nat. Phys. (2008)

Single dot charge sensing: Biercuk *et al.* PRB (2006)

$^{13}\text{CH}_4$: Liu and Fan, JACS (2001)

NO_2 : Farmer and Gordon, Nano Lett. (2006)
Williams *et al.*, Science (2007)

Devices

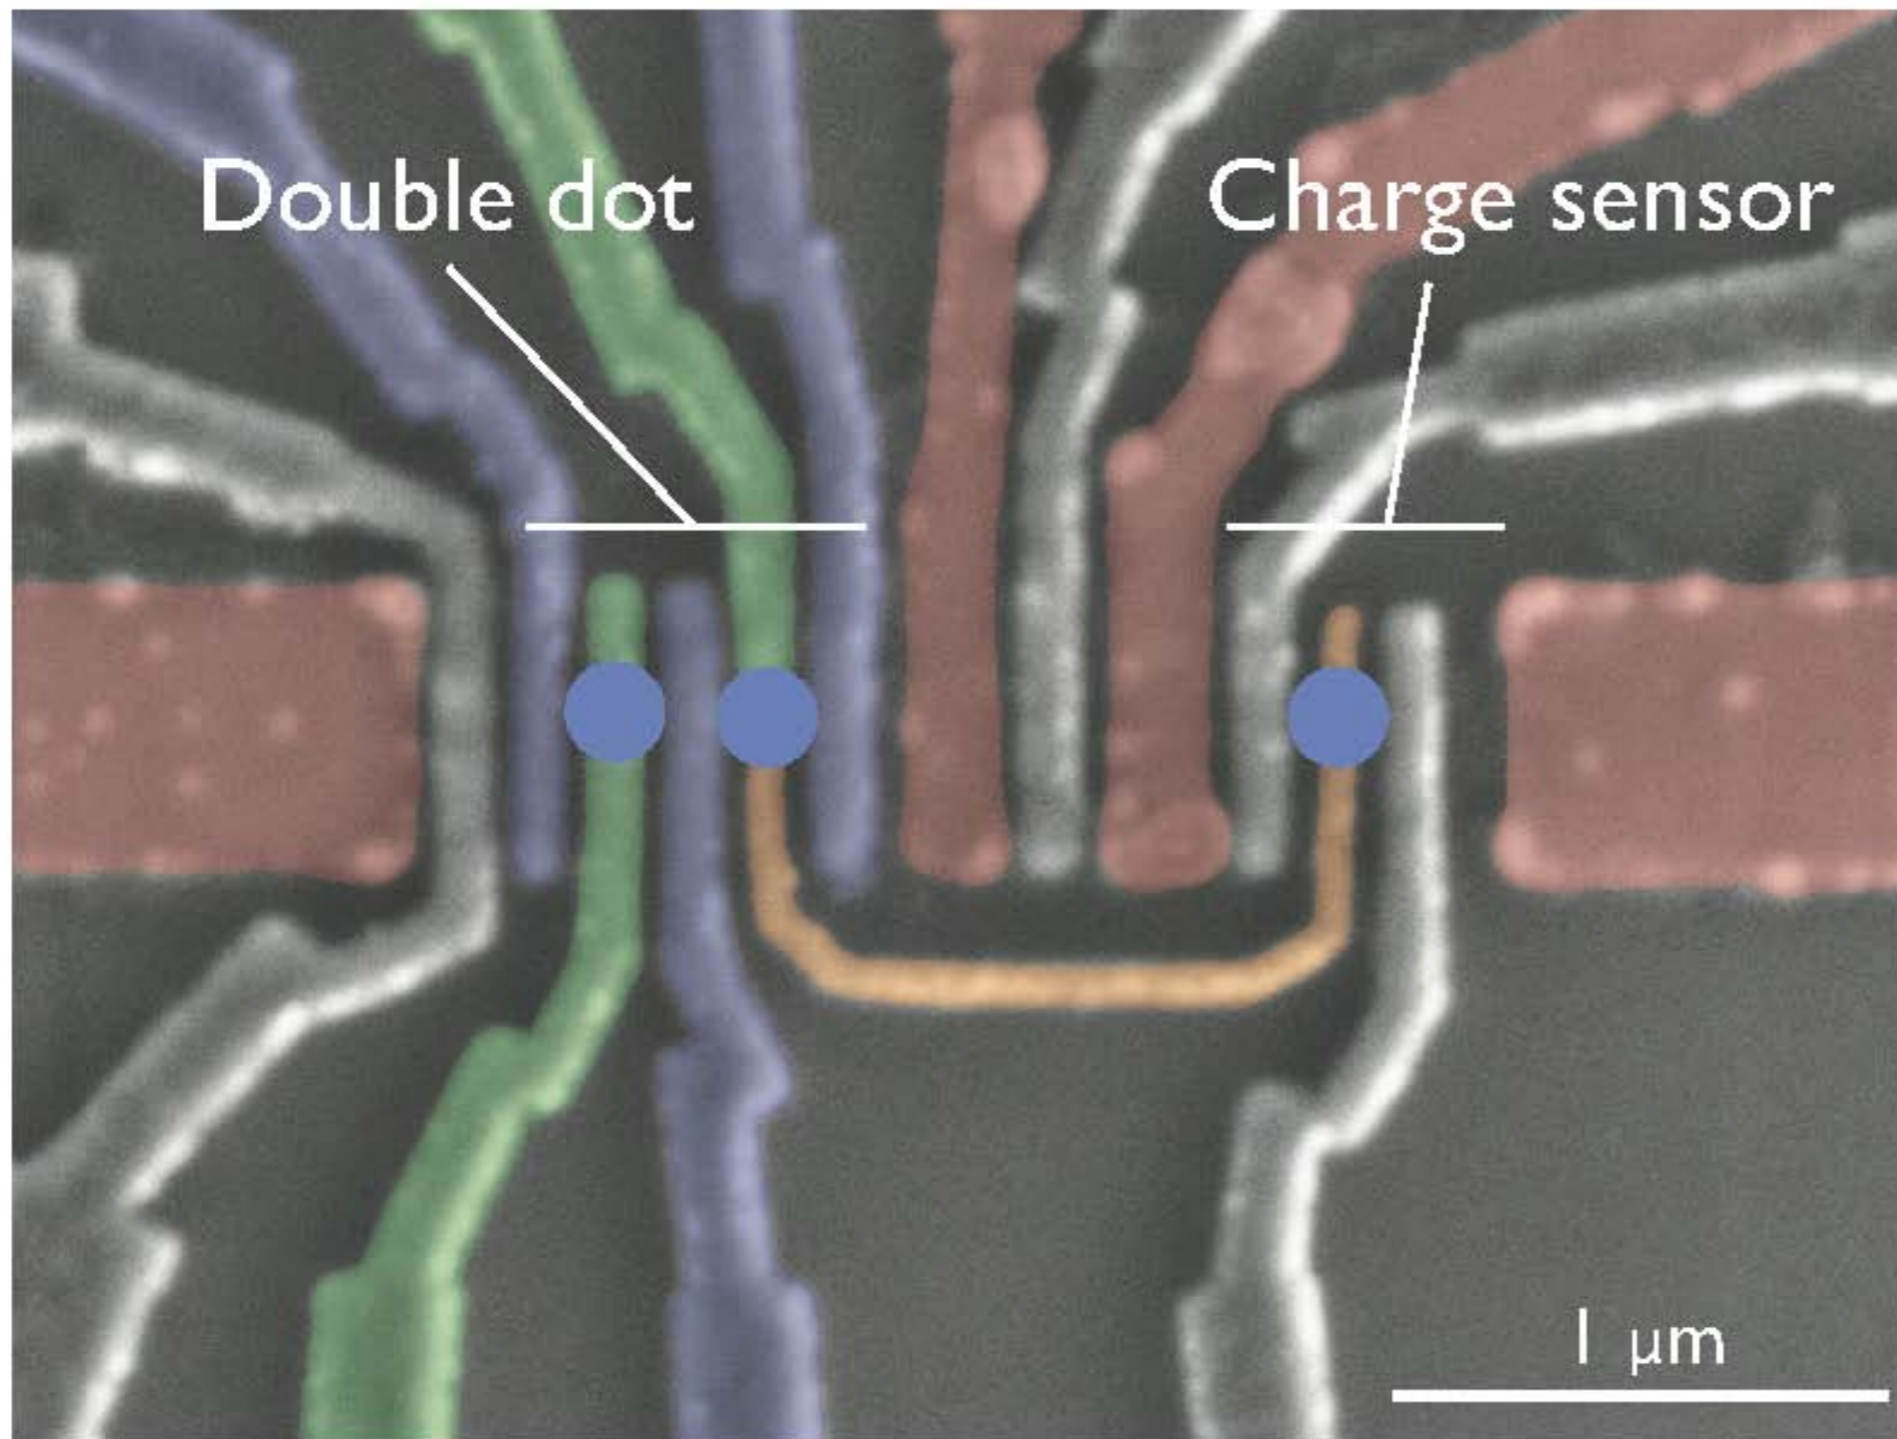

- CVD growth with $^{12}\text{CH}_4$ or $^{13}\text{CH}_4$
- Fe catalyst
- Pd contacts
- $\text{Al}_2\text{O}_3 + \text{NO}_2$ ALD
- Al top gates

Related work

DQDs: Biercuk *et al.* Nano Lett. (2005)
Sapmaz *et al.*, Nano Lett. (2006)






Graeber *et al.* PRB (2006)
Jorgensen *et al.* Nat. Phys. (2008)

Single dot charge sensing: Biercuk *et al.* PRB (2006)

$^{13}\text{CH}_4$: Liu and Fan, JACS (2001)




NO_2 : Farmer and Gordon, Nano Lett. (2006)
Williams *et al.*, Science (2007)

Tunable double dot

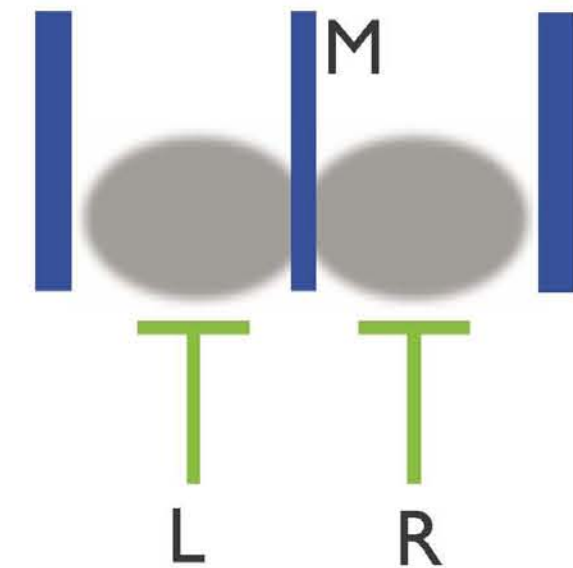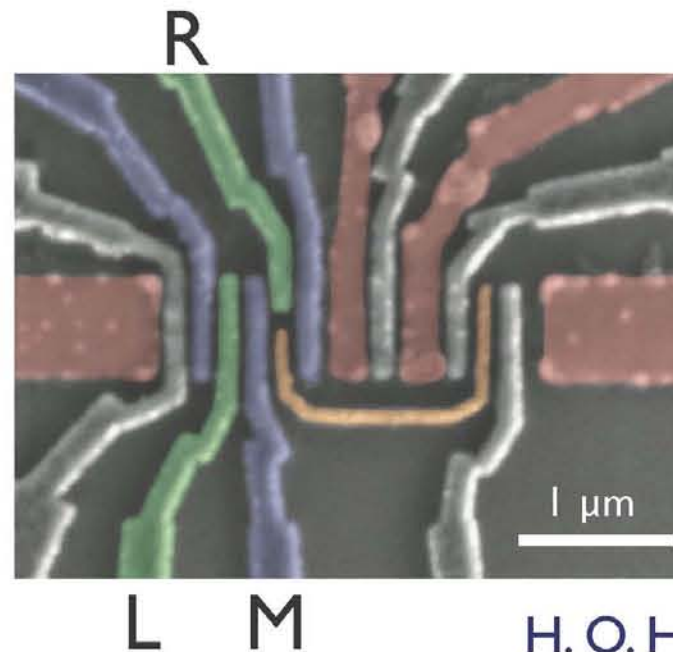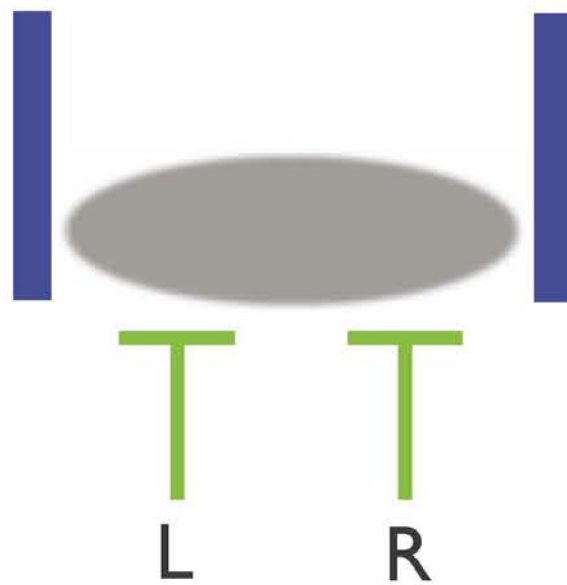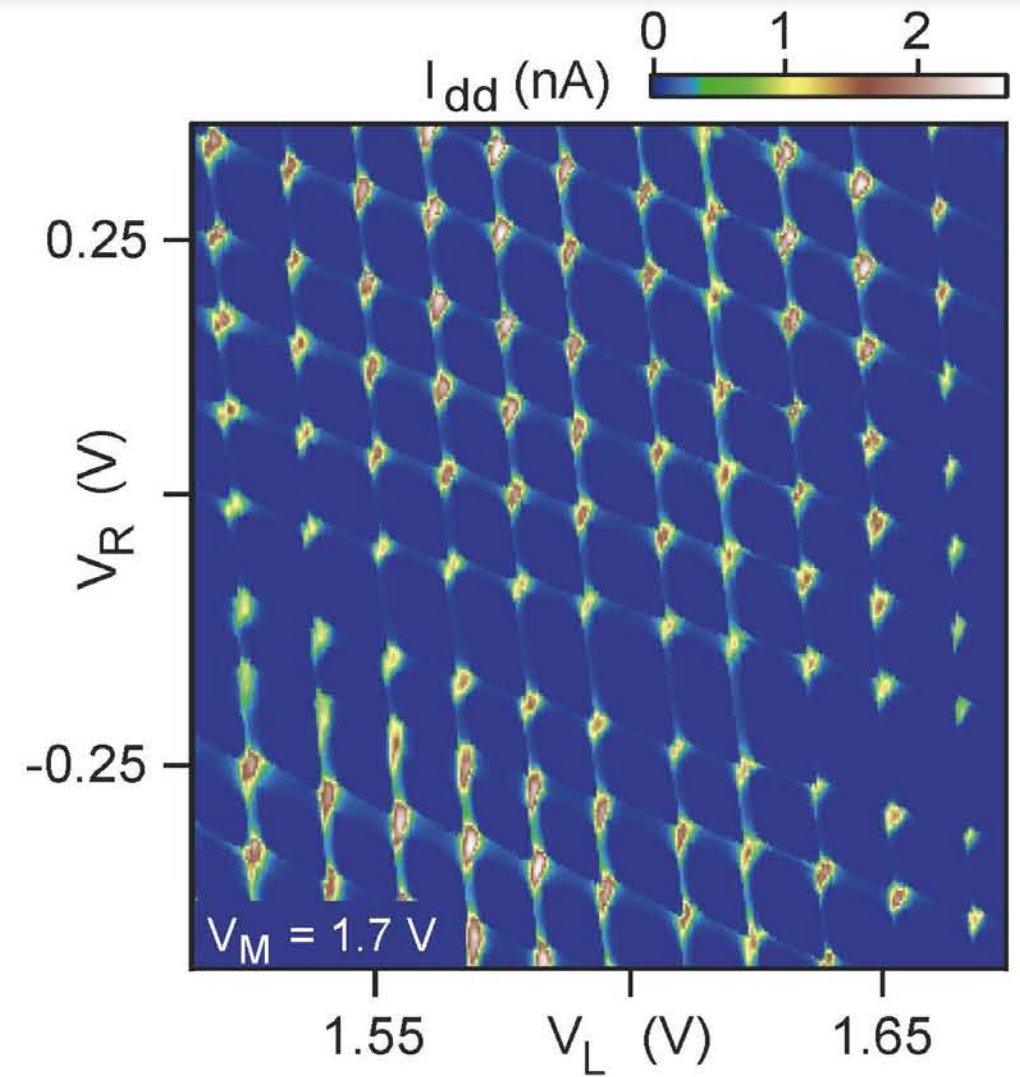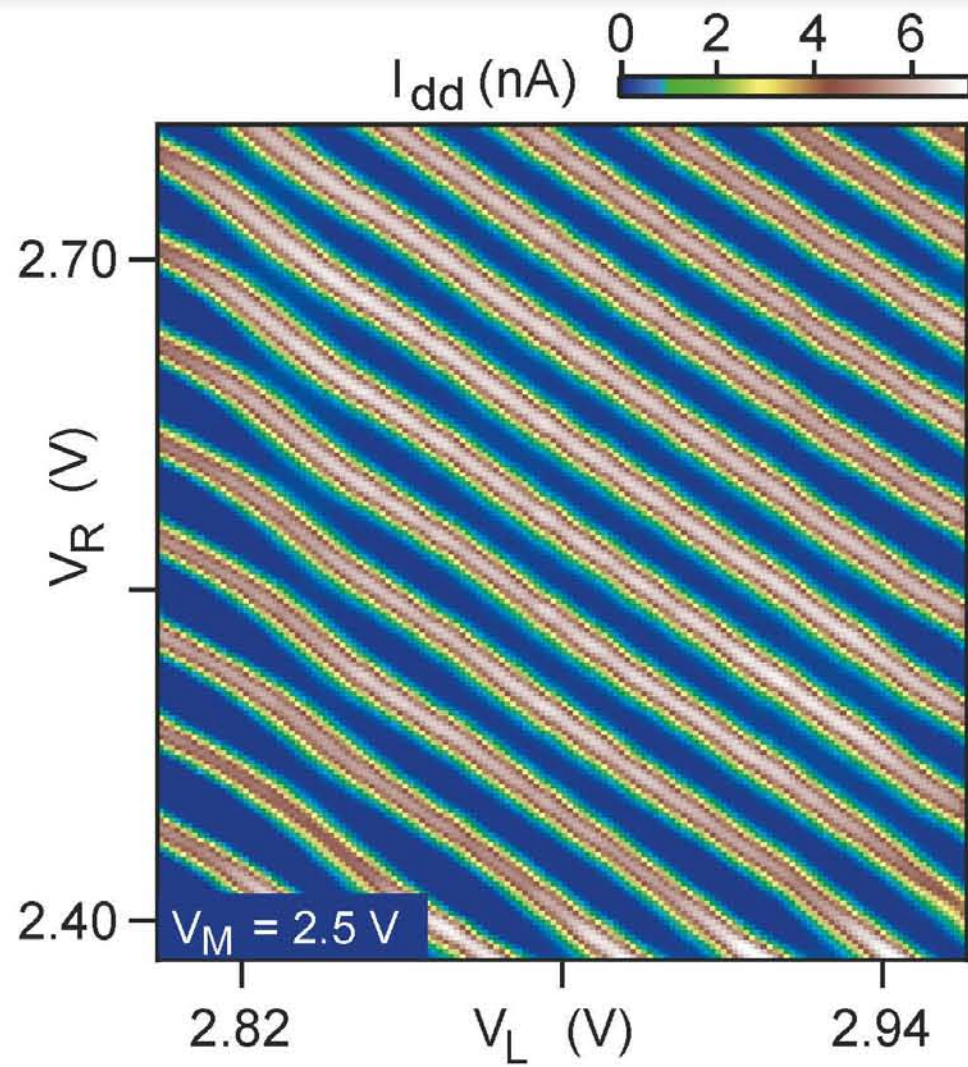




H. O. H. Churchill, et al. *Nature Physics* **5**, 321 (2009).

^{13}C spin blockade

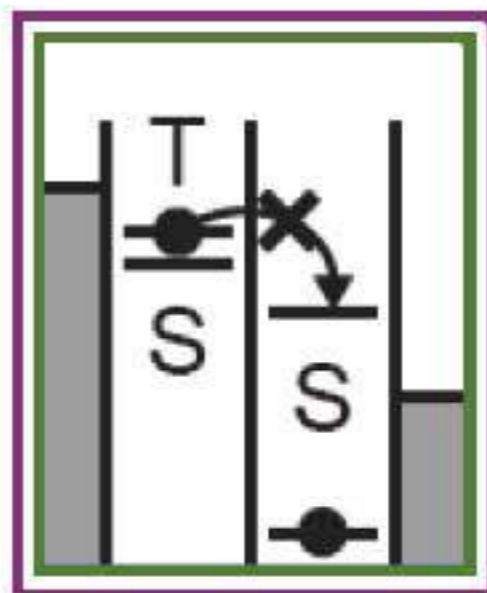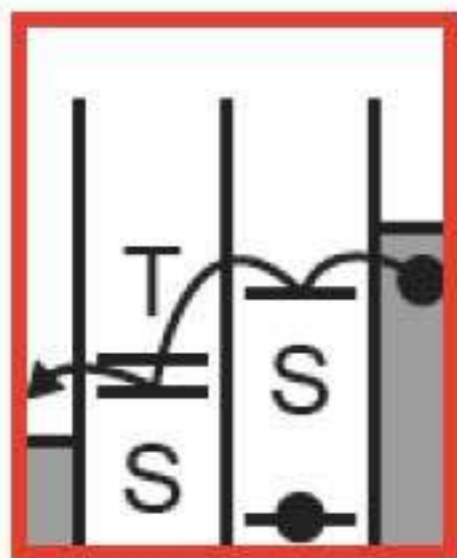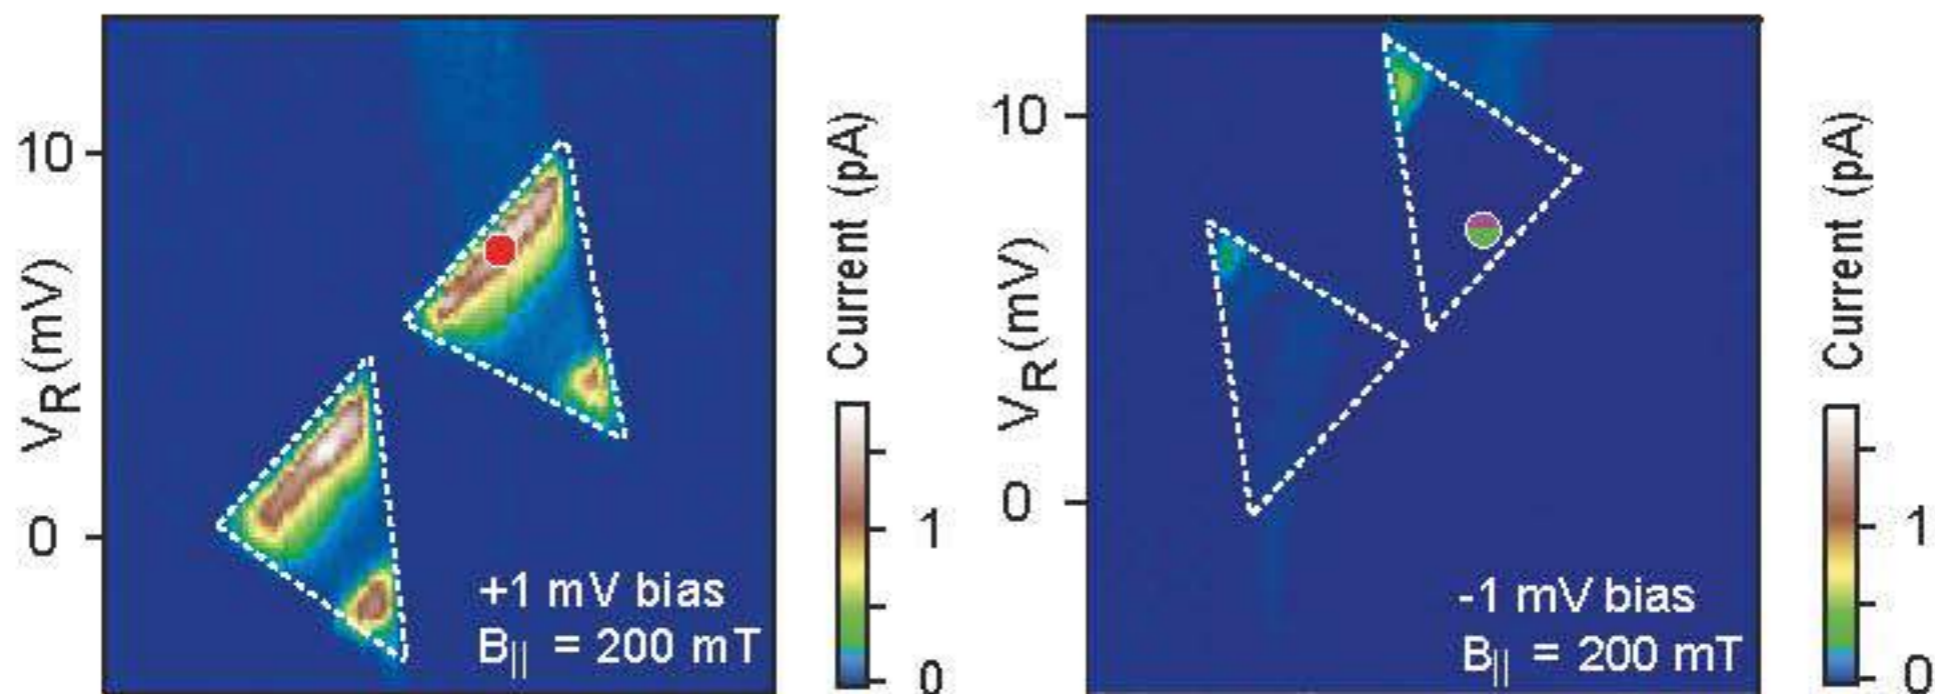





H. O. H. Churchill, et al. Nature Physics **5**, 321 (2009).

^{13}C spin blockade

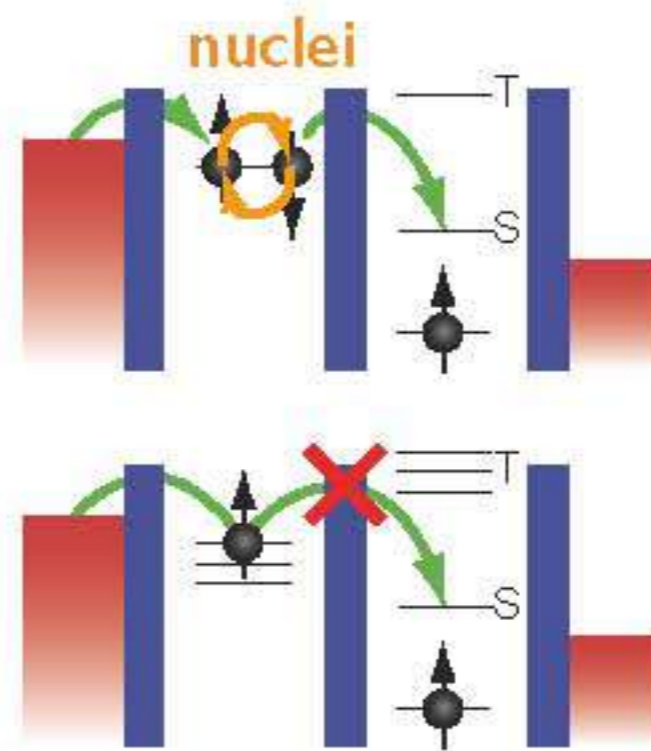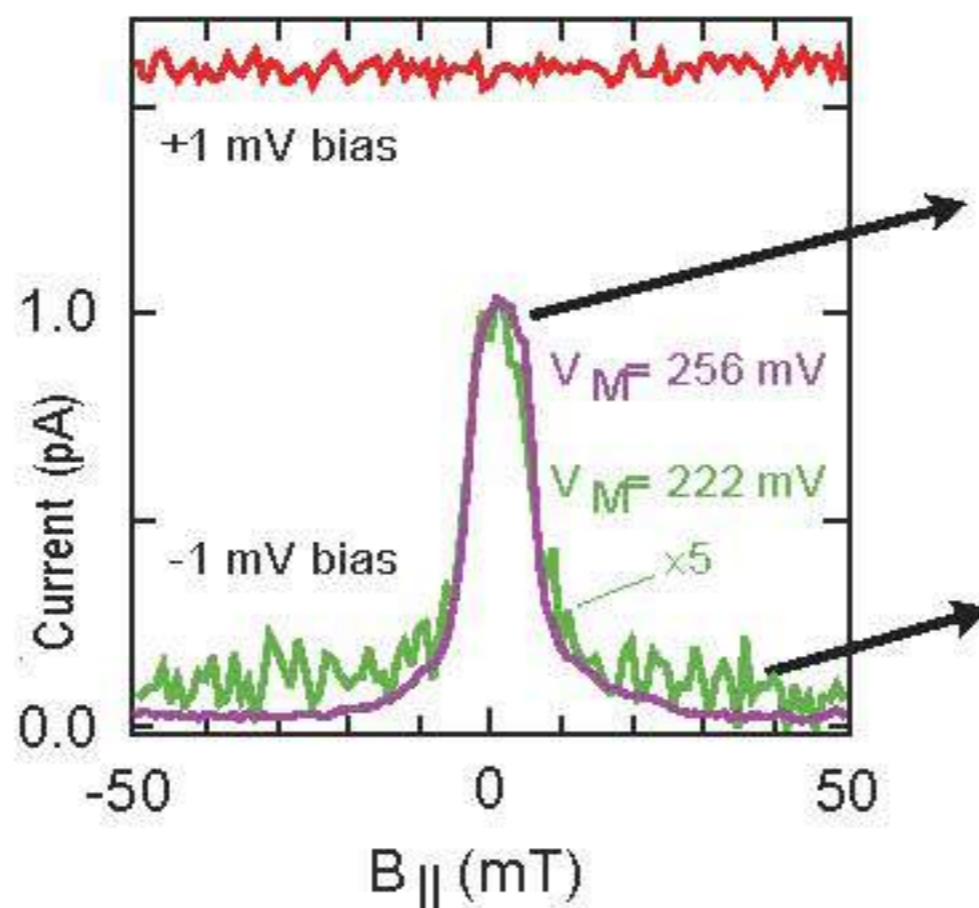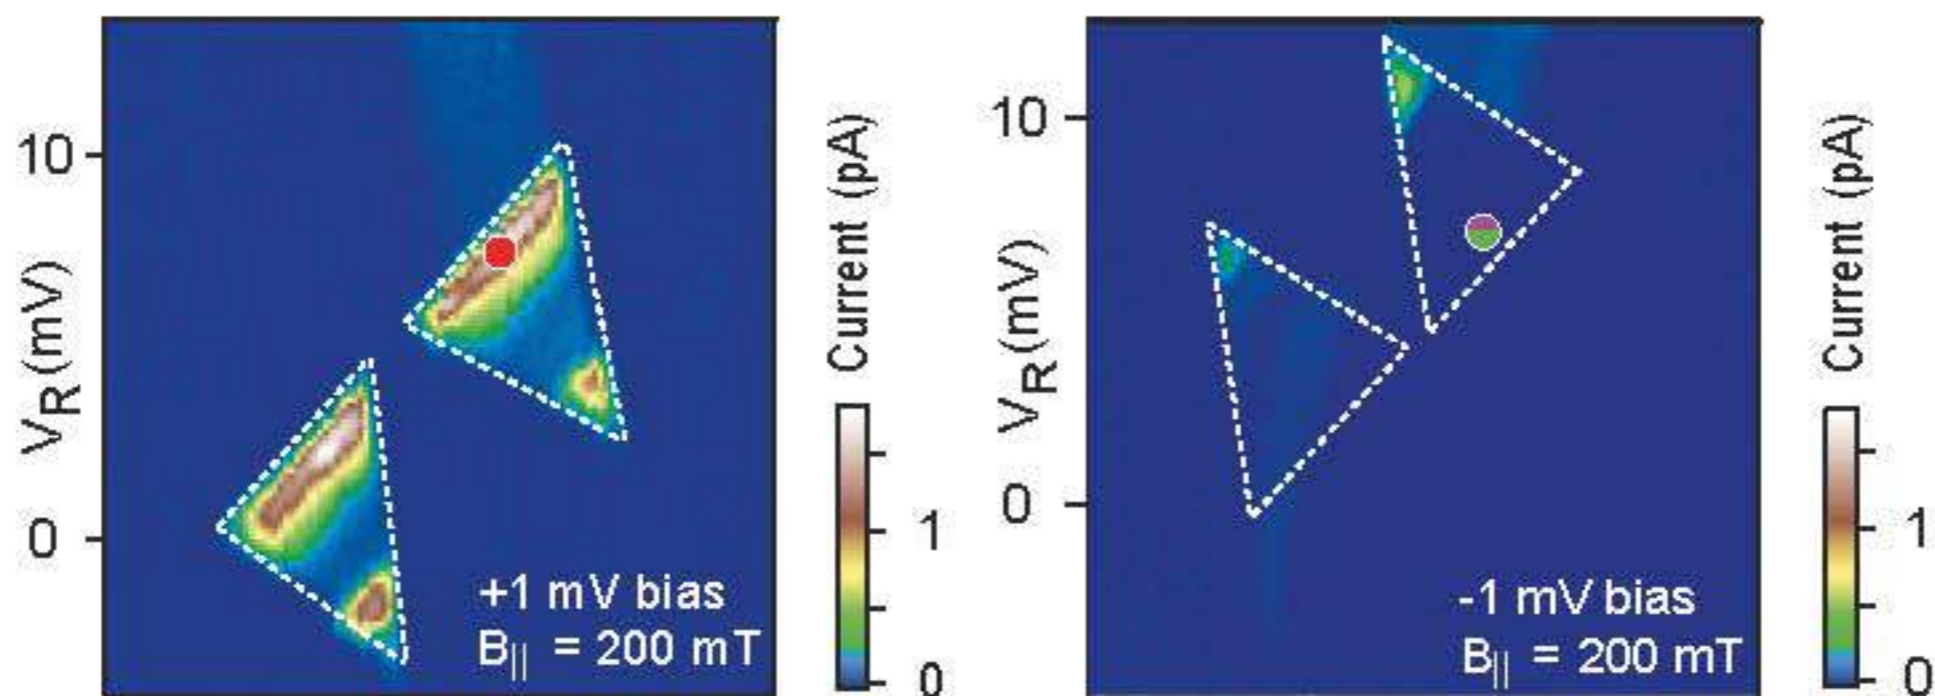

H. O. H. Churchill, et al. Nature Physics **5**, 321 (2009).

Magnetic field dependence of spin relaxation

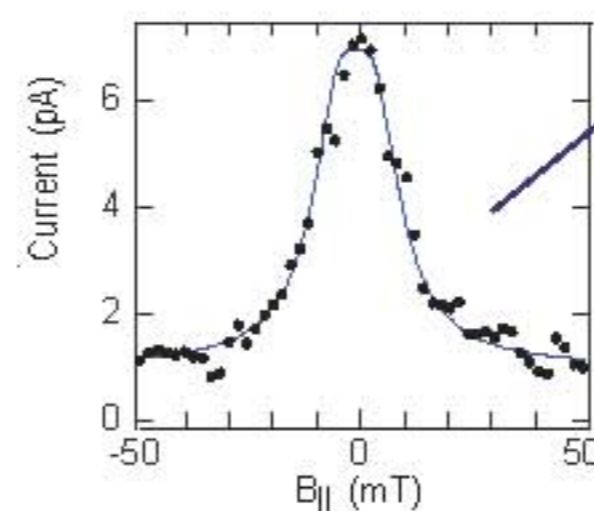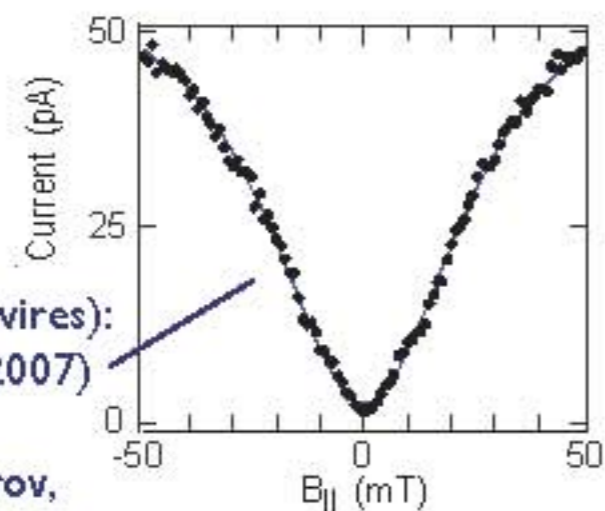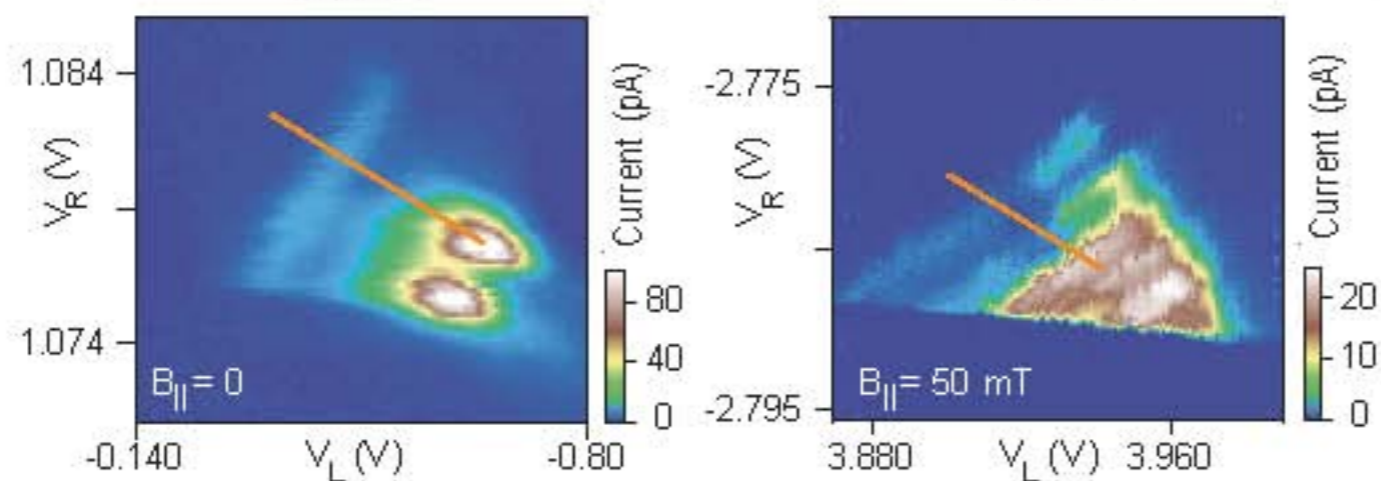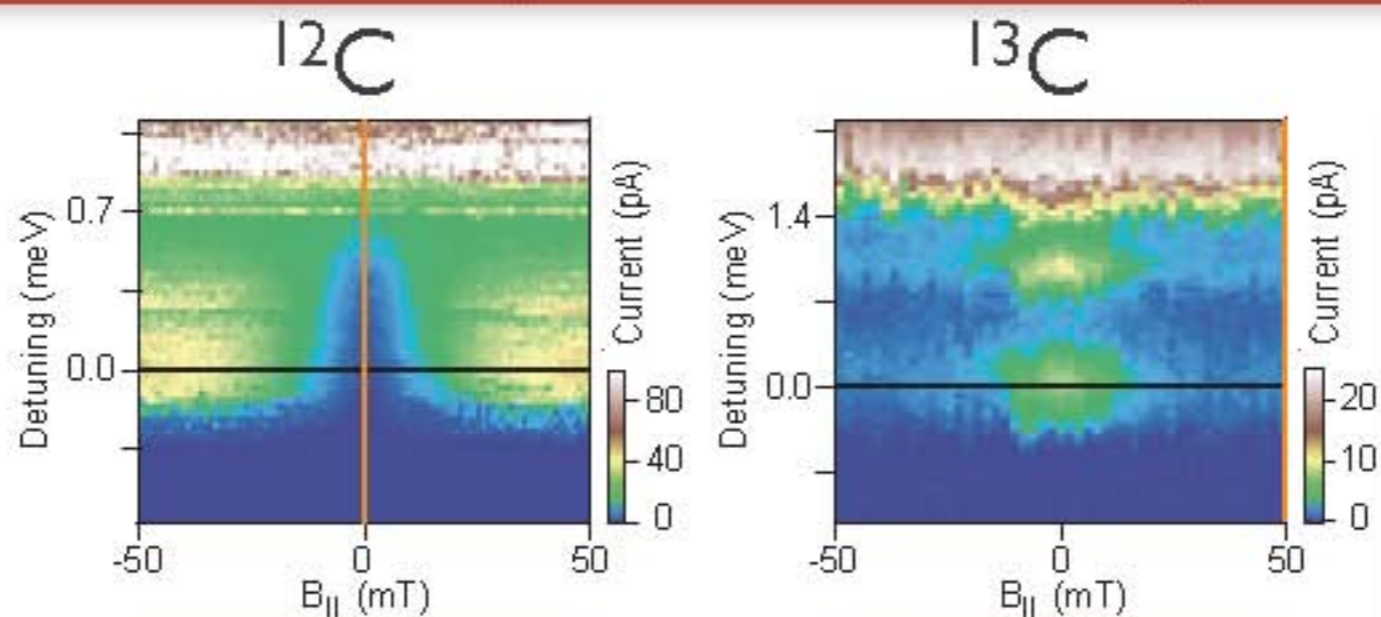

See Also
Expt:
 Koppens, Folk, et al. (GaAs)
 Science **305**, 1346 (2005).
Theory:
 Jouravlev and Nazarov
 PRL **96**, 176804 (2006)

See Also
Expt:
 Ensslin group (InAs wires):
 PRL **99**, 036801 (2007)
Theory:
 Danon and Nazarov,
 arXiv:0905.181 (2009)



$$g\mu_B B_{\text{nuc}} = A/\sqrt{N}$$

$$B_{\text{nuc}} = 6.1 \text{ mT}$$


$$\rightarrow A \sim 100 \mu\text{eV}$$

H. O. H. Churchill, et al. Nature Physics **5**, 321 (2009).

Hysteresis in ^{13}C leakage current

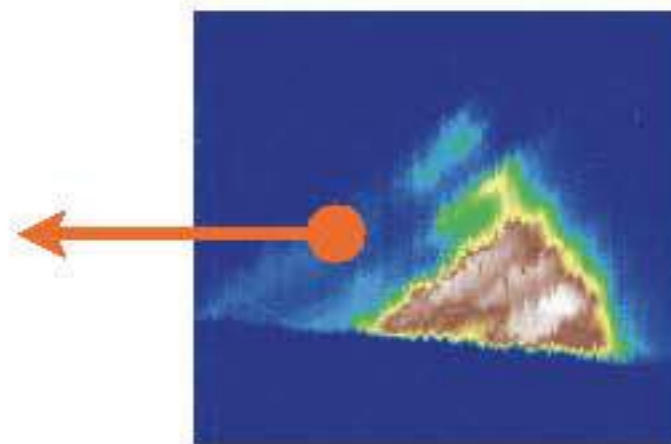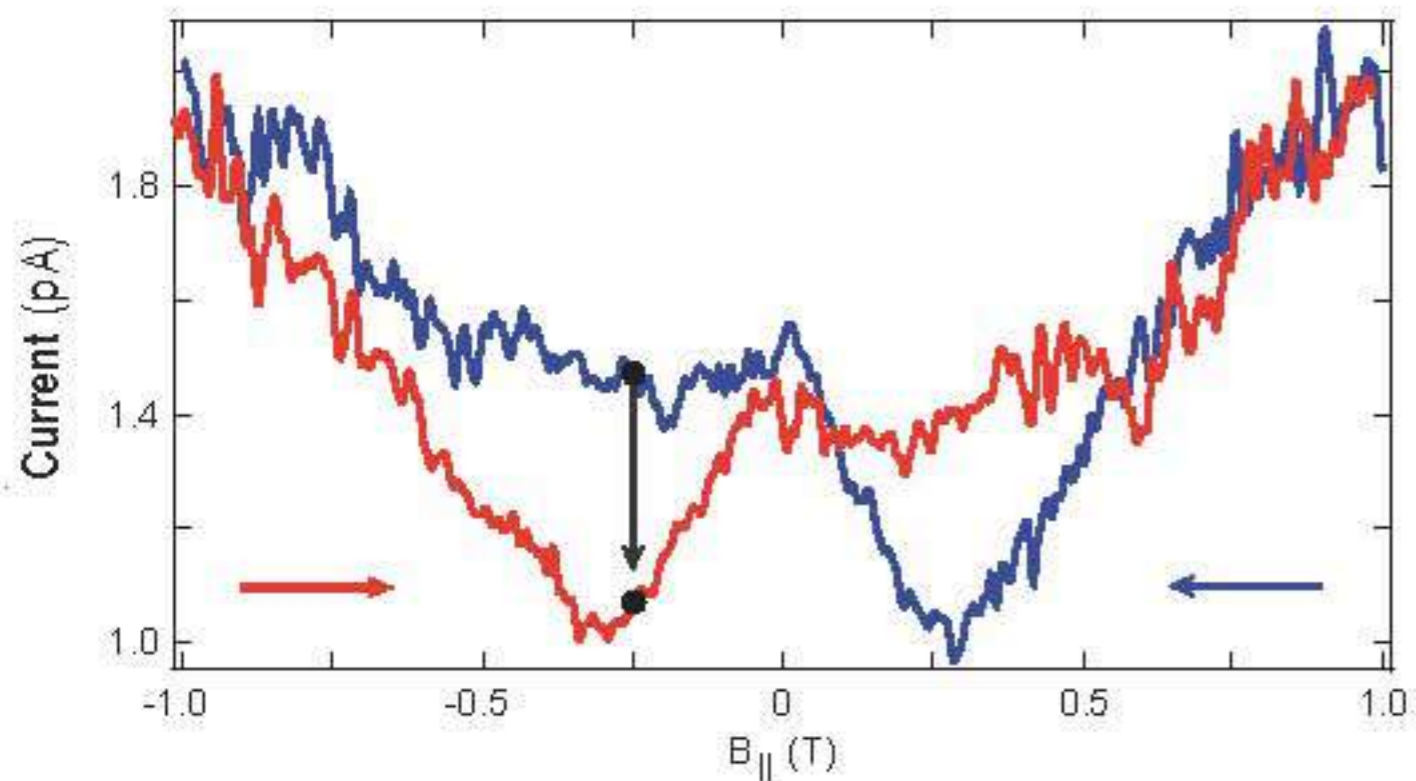


sets independent
lower bound on
 $A \sim 50 \mu\text{eV}$

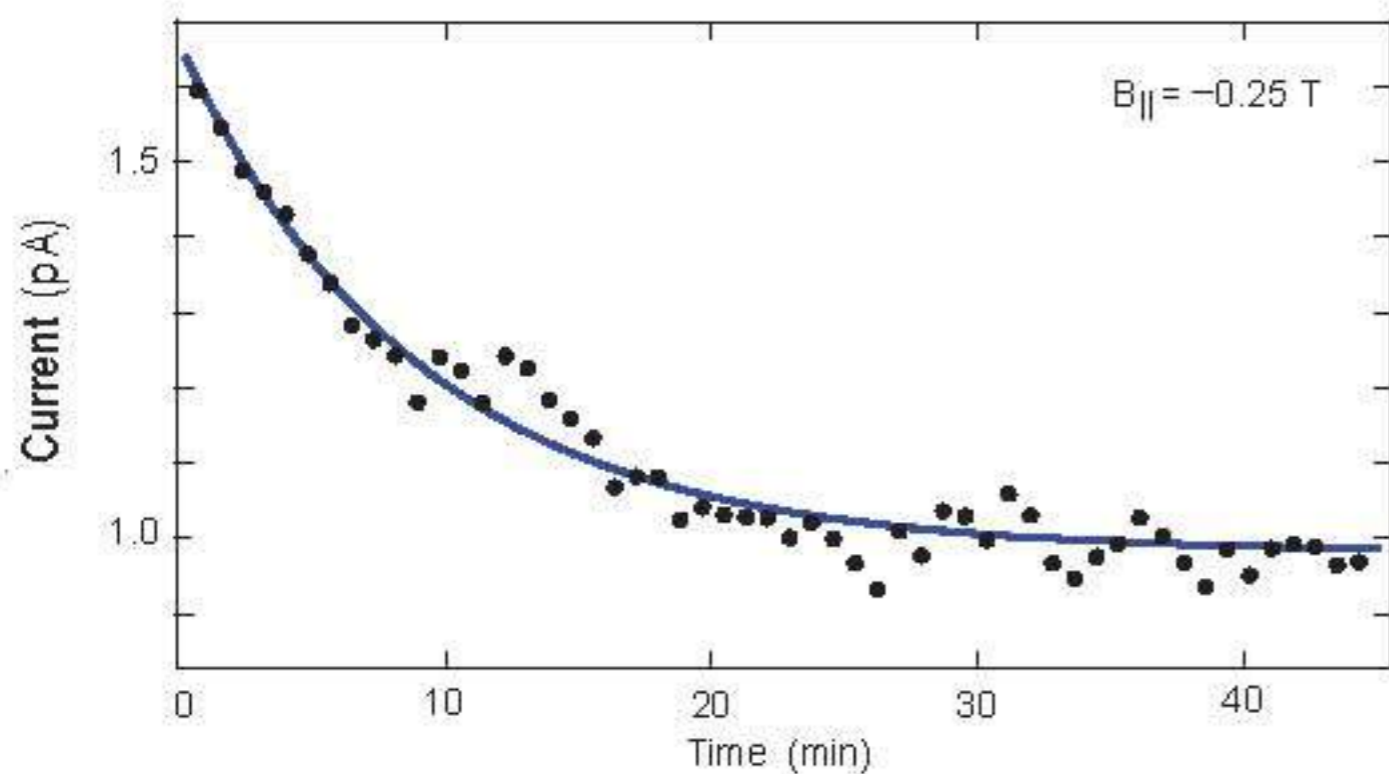


H. O. H. Churchill, et al. Nature Physics **5**, 321 (2009).

Charge sensing

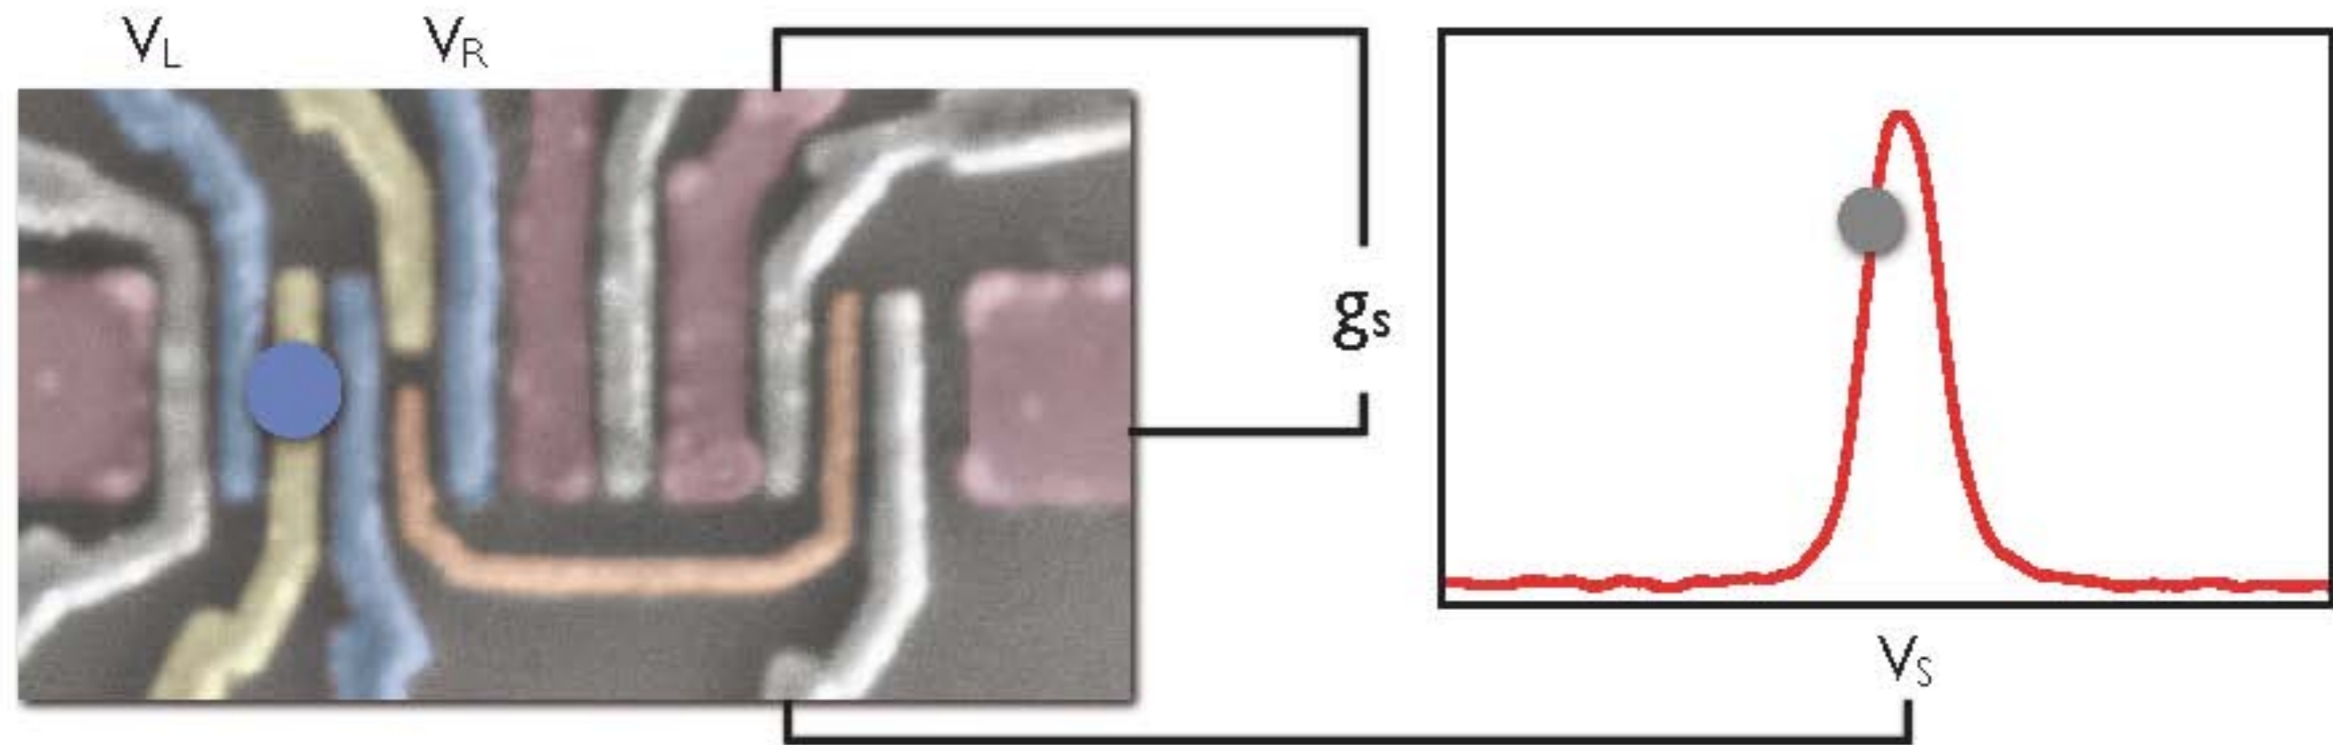

double dot charges
'gate' sensor dot


Charge sensing

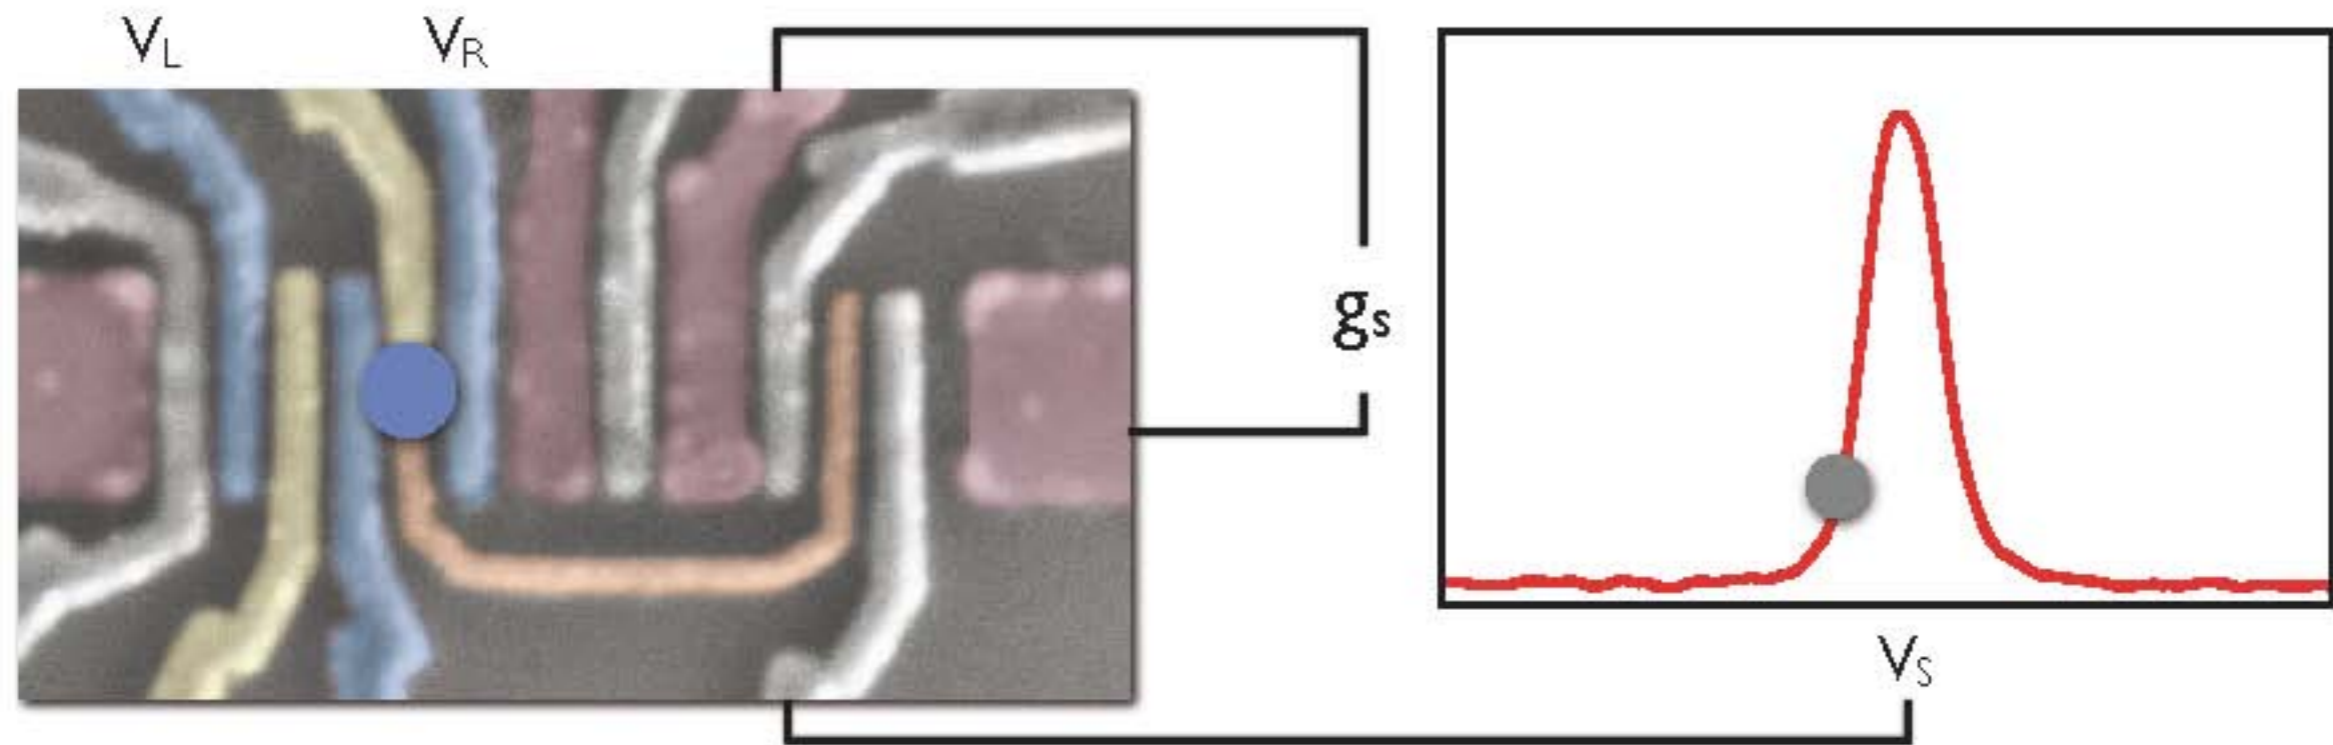


double dot charges
'gate' sensor dot

^{13}C Nanotube Double Dot with Integrated Charge Sensor

Few-Electron Regime


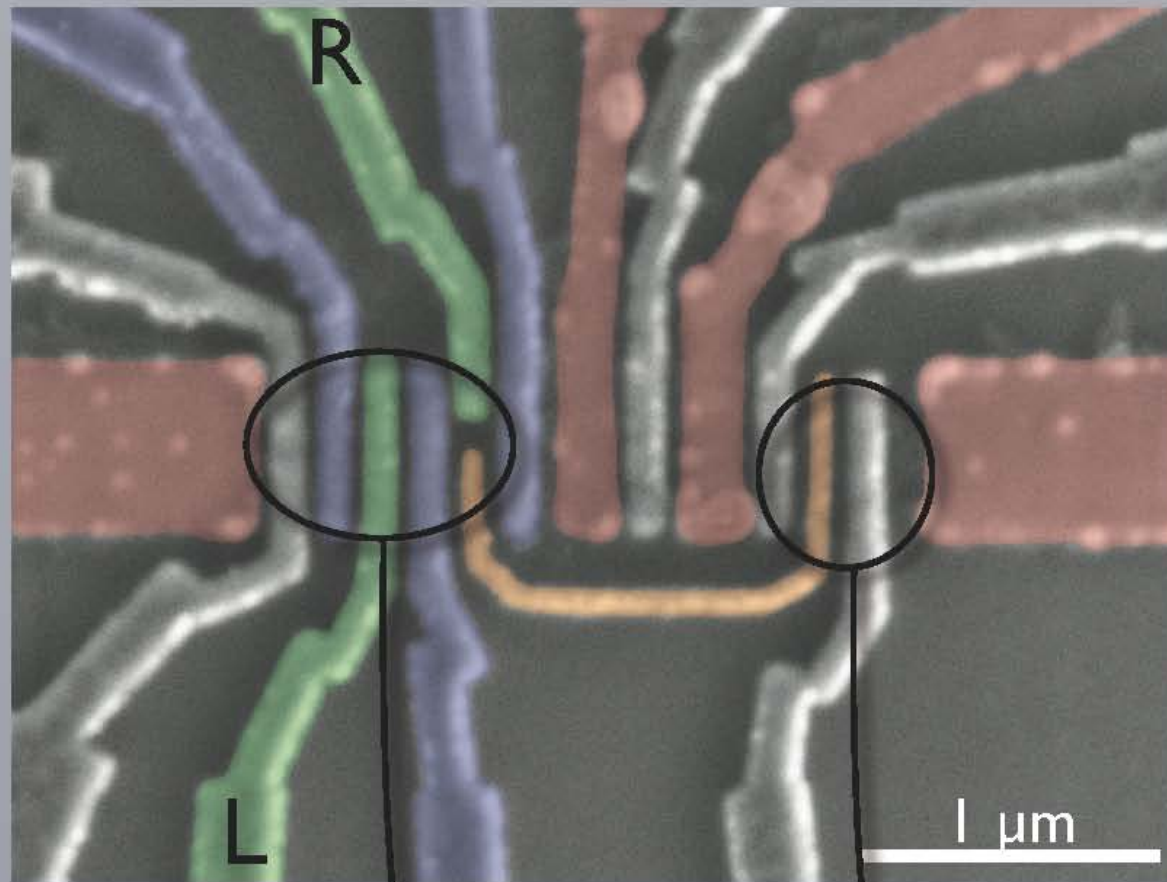


Double Dot Sensor

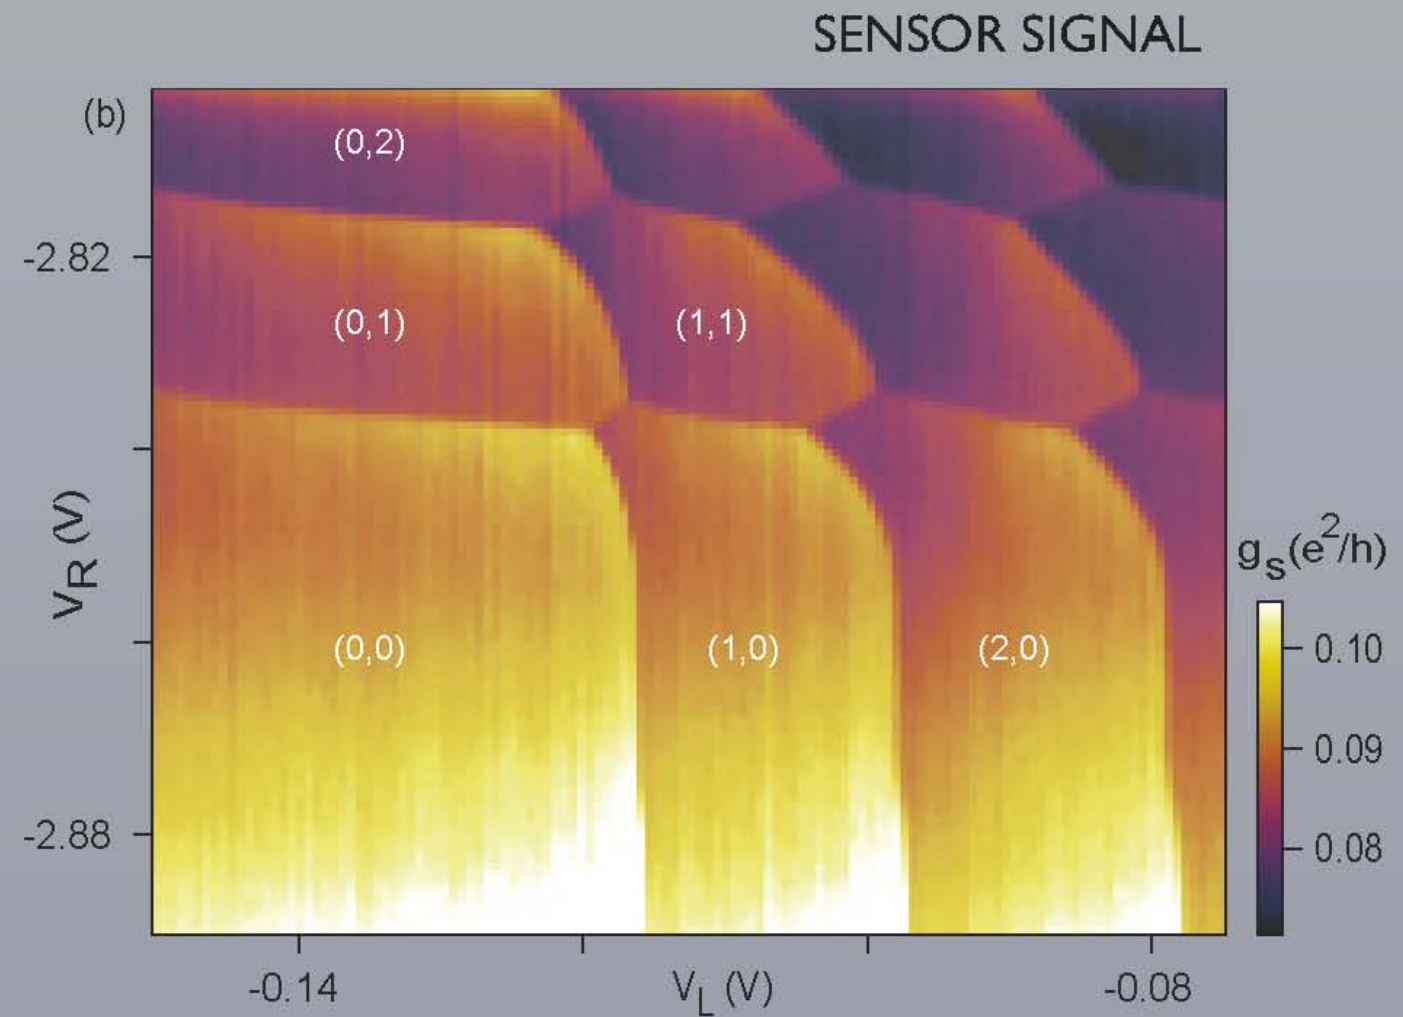


H. O. H. Churchill, et al. Phys. Rev. Lett. **102** 1066802 (2009).


Levels in a single dot

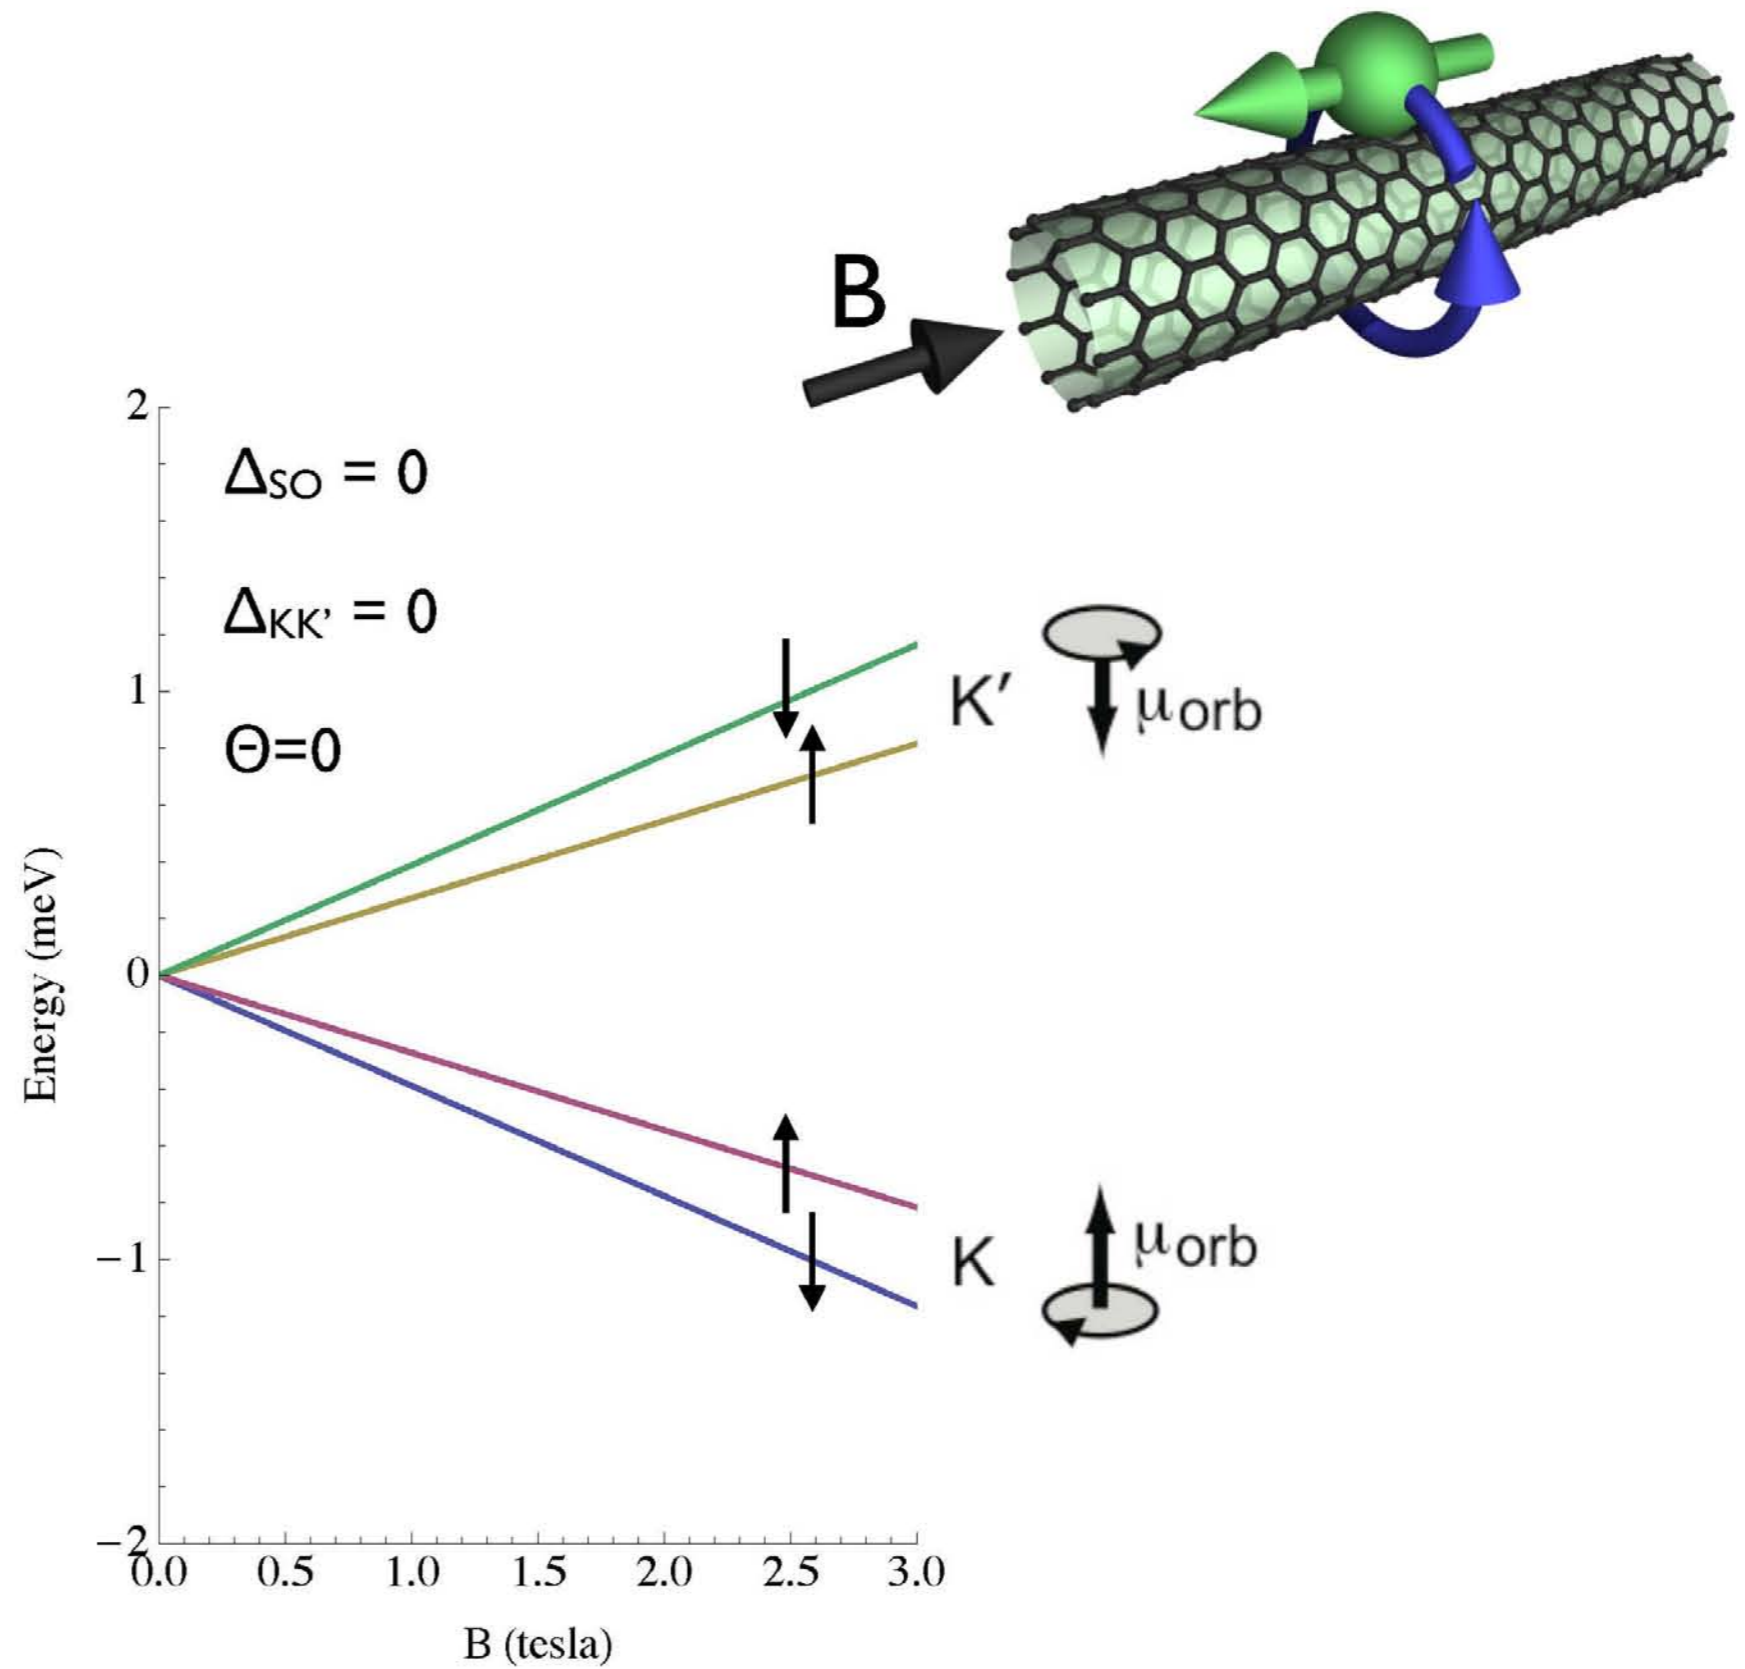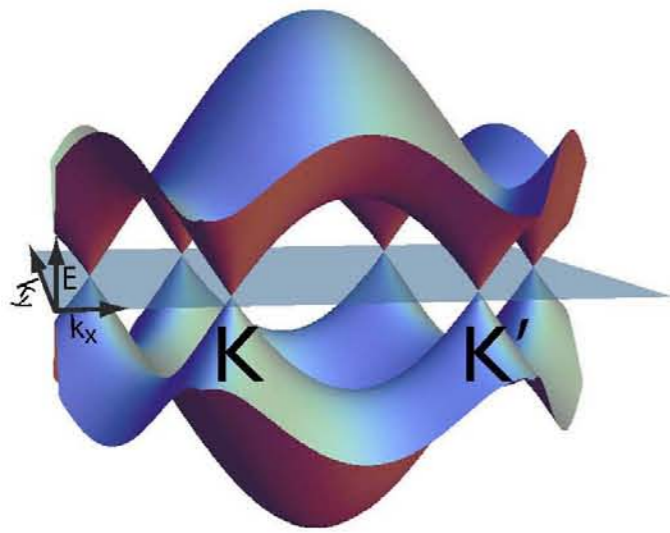


Levels in a single dot, including spin-orbit coupling

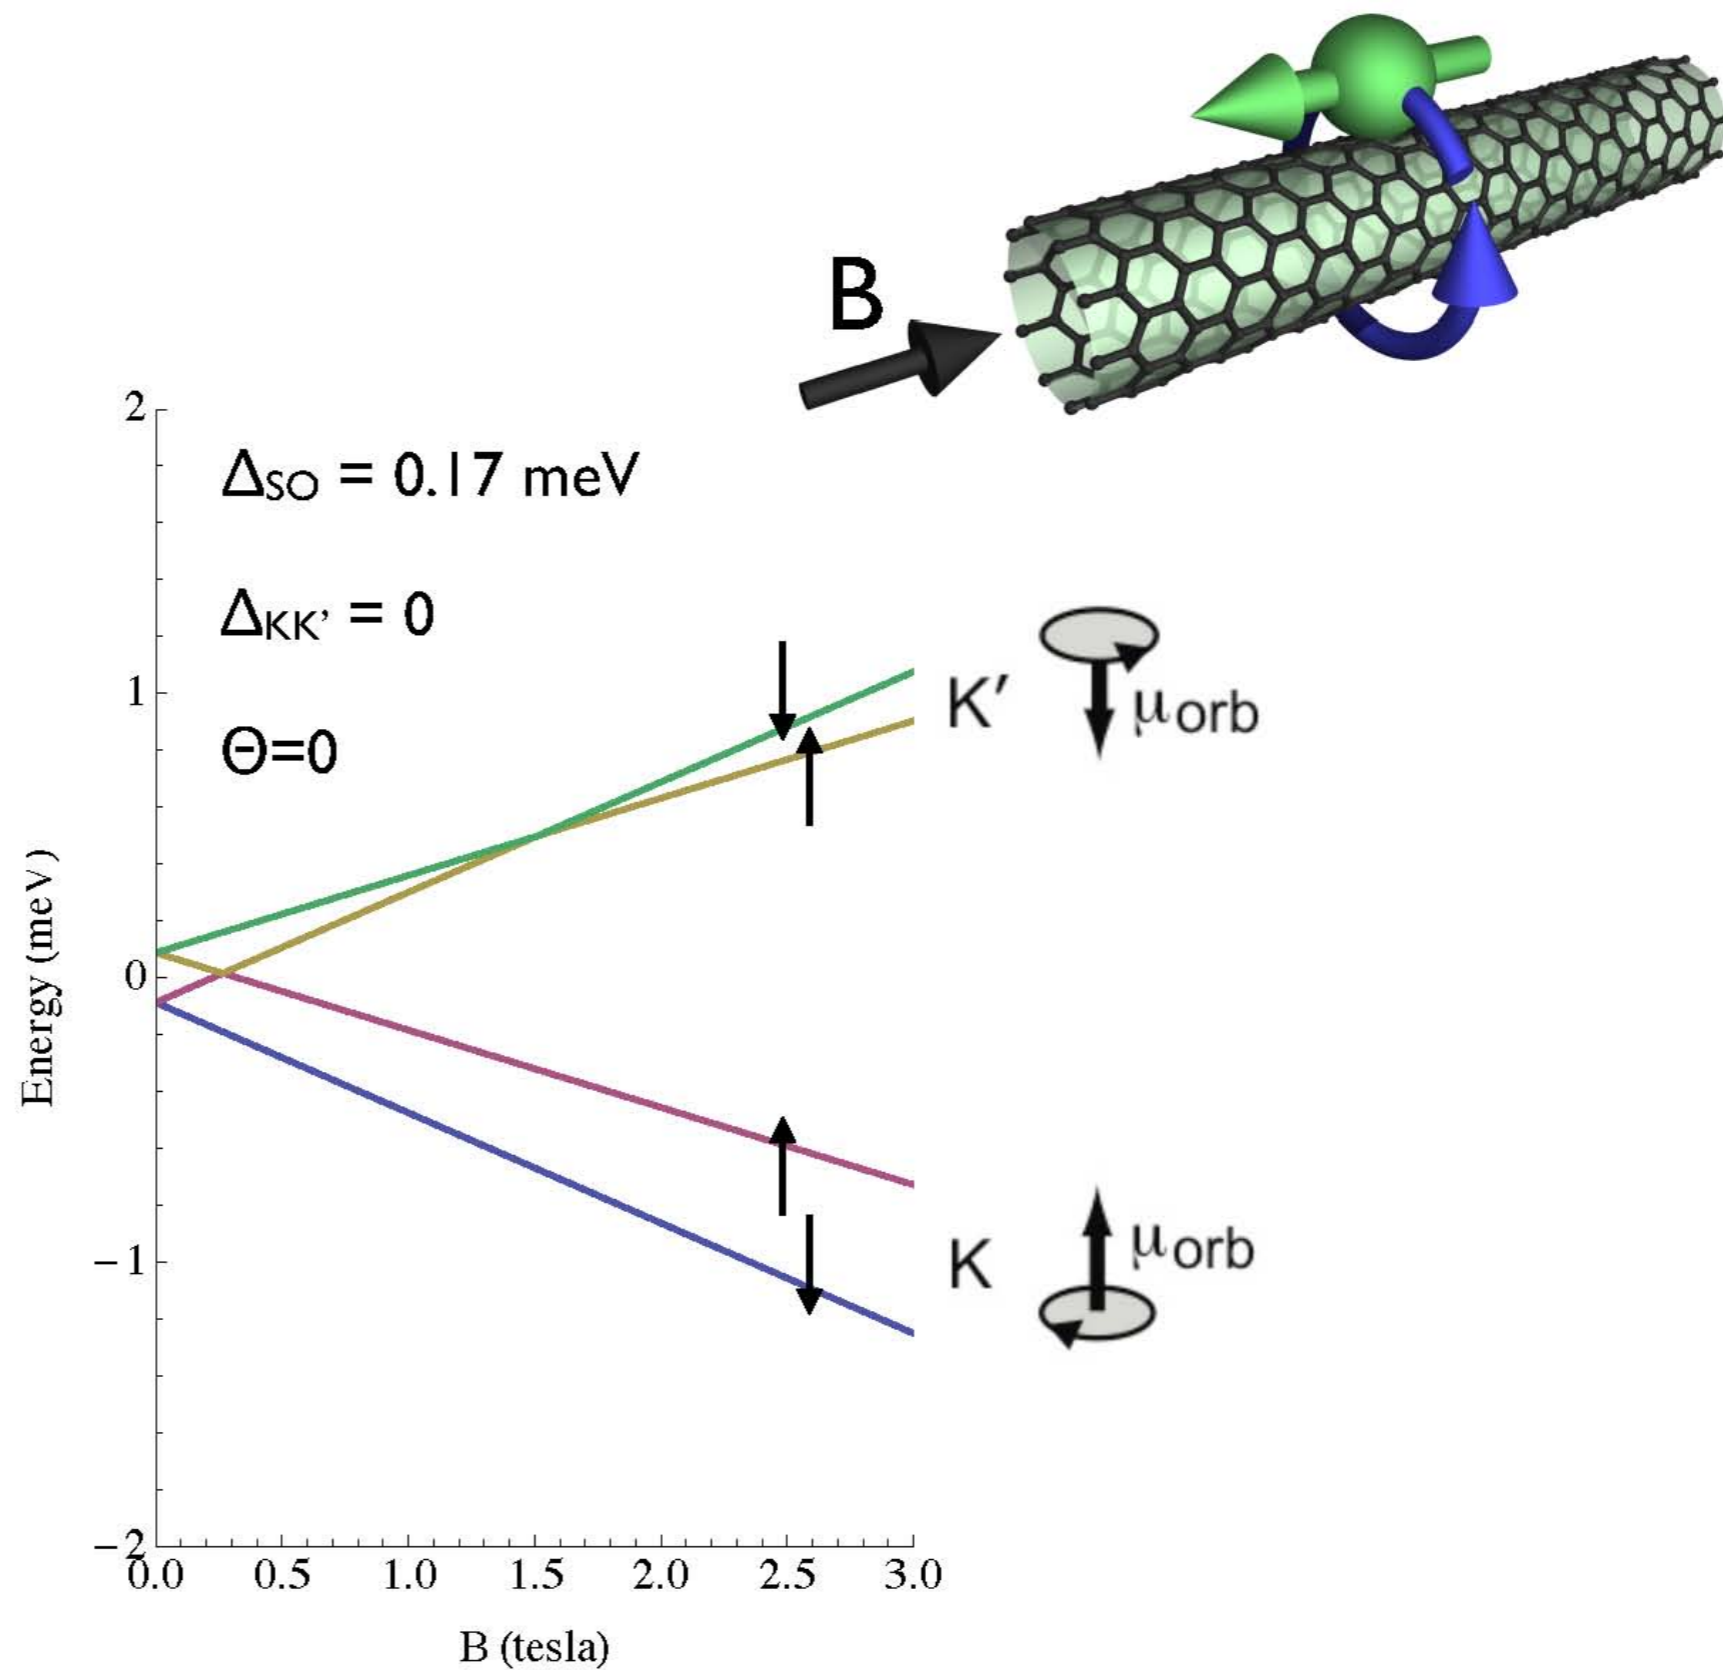


Levels in a single dot, including spin-orbit coupling

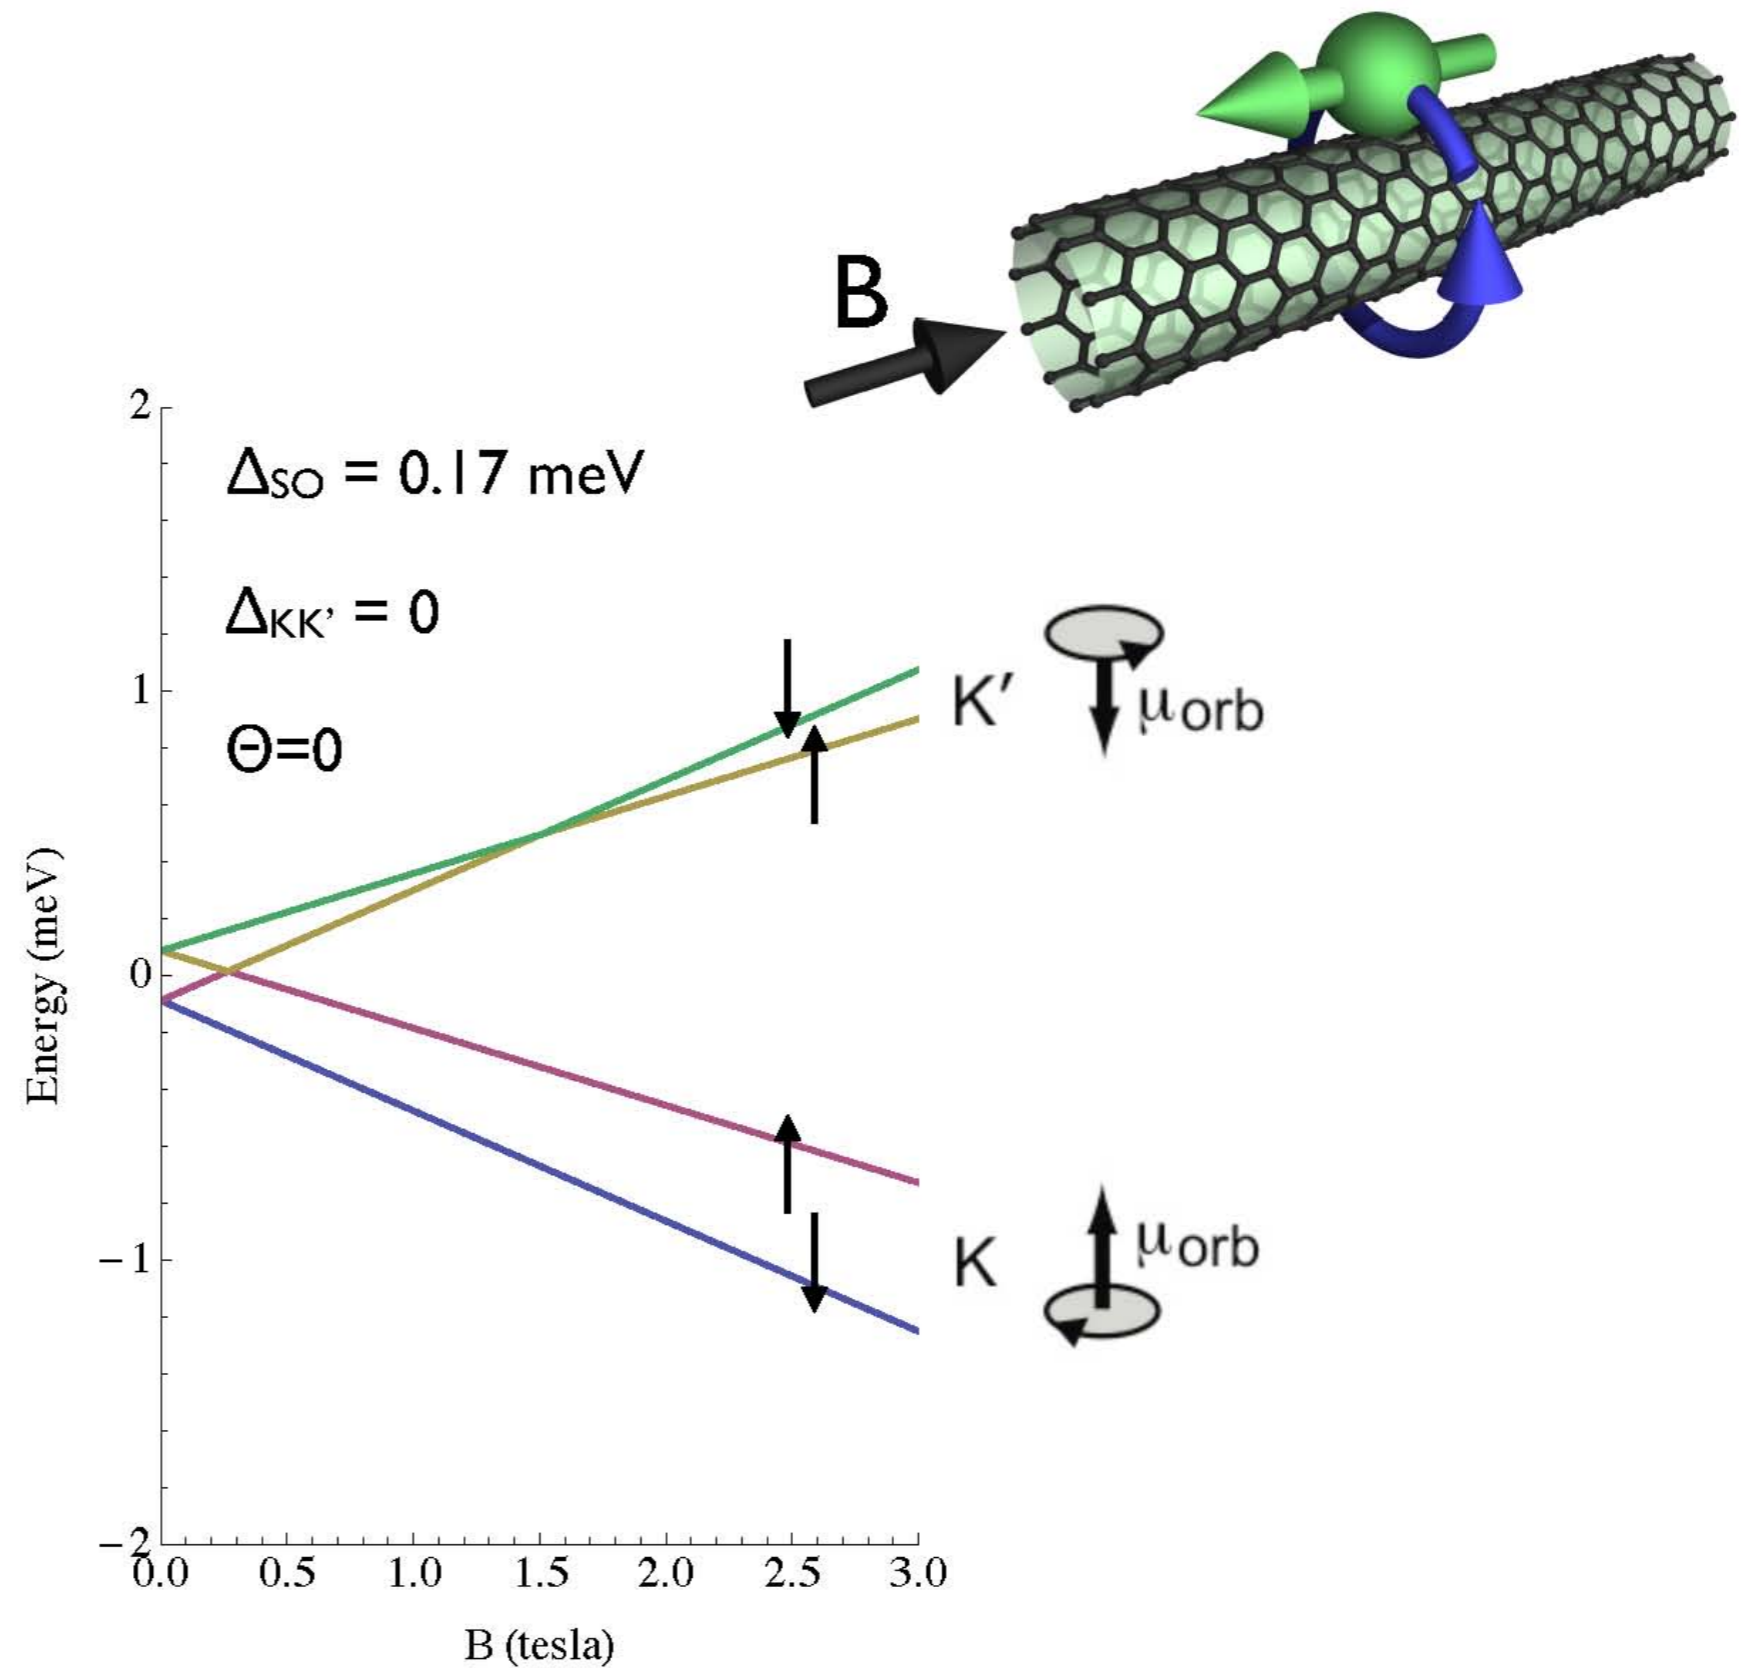


Levels in a single dot, including spin-orbit coupling and valley mixing

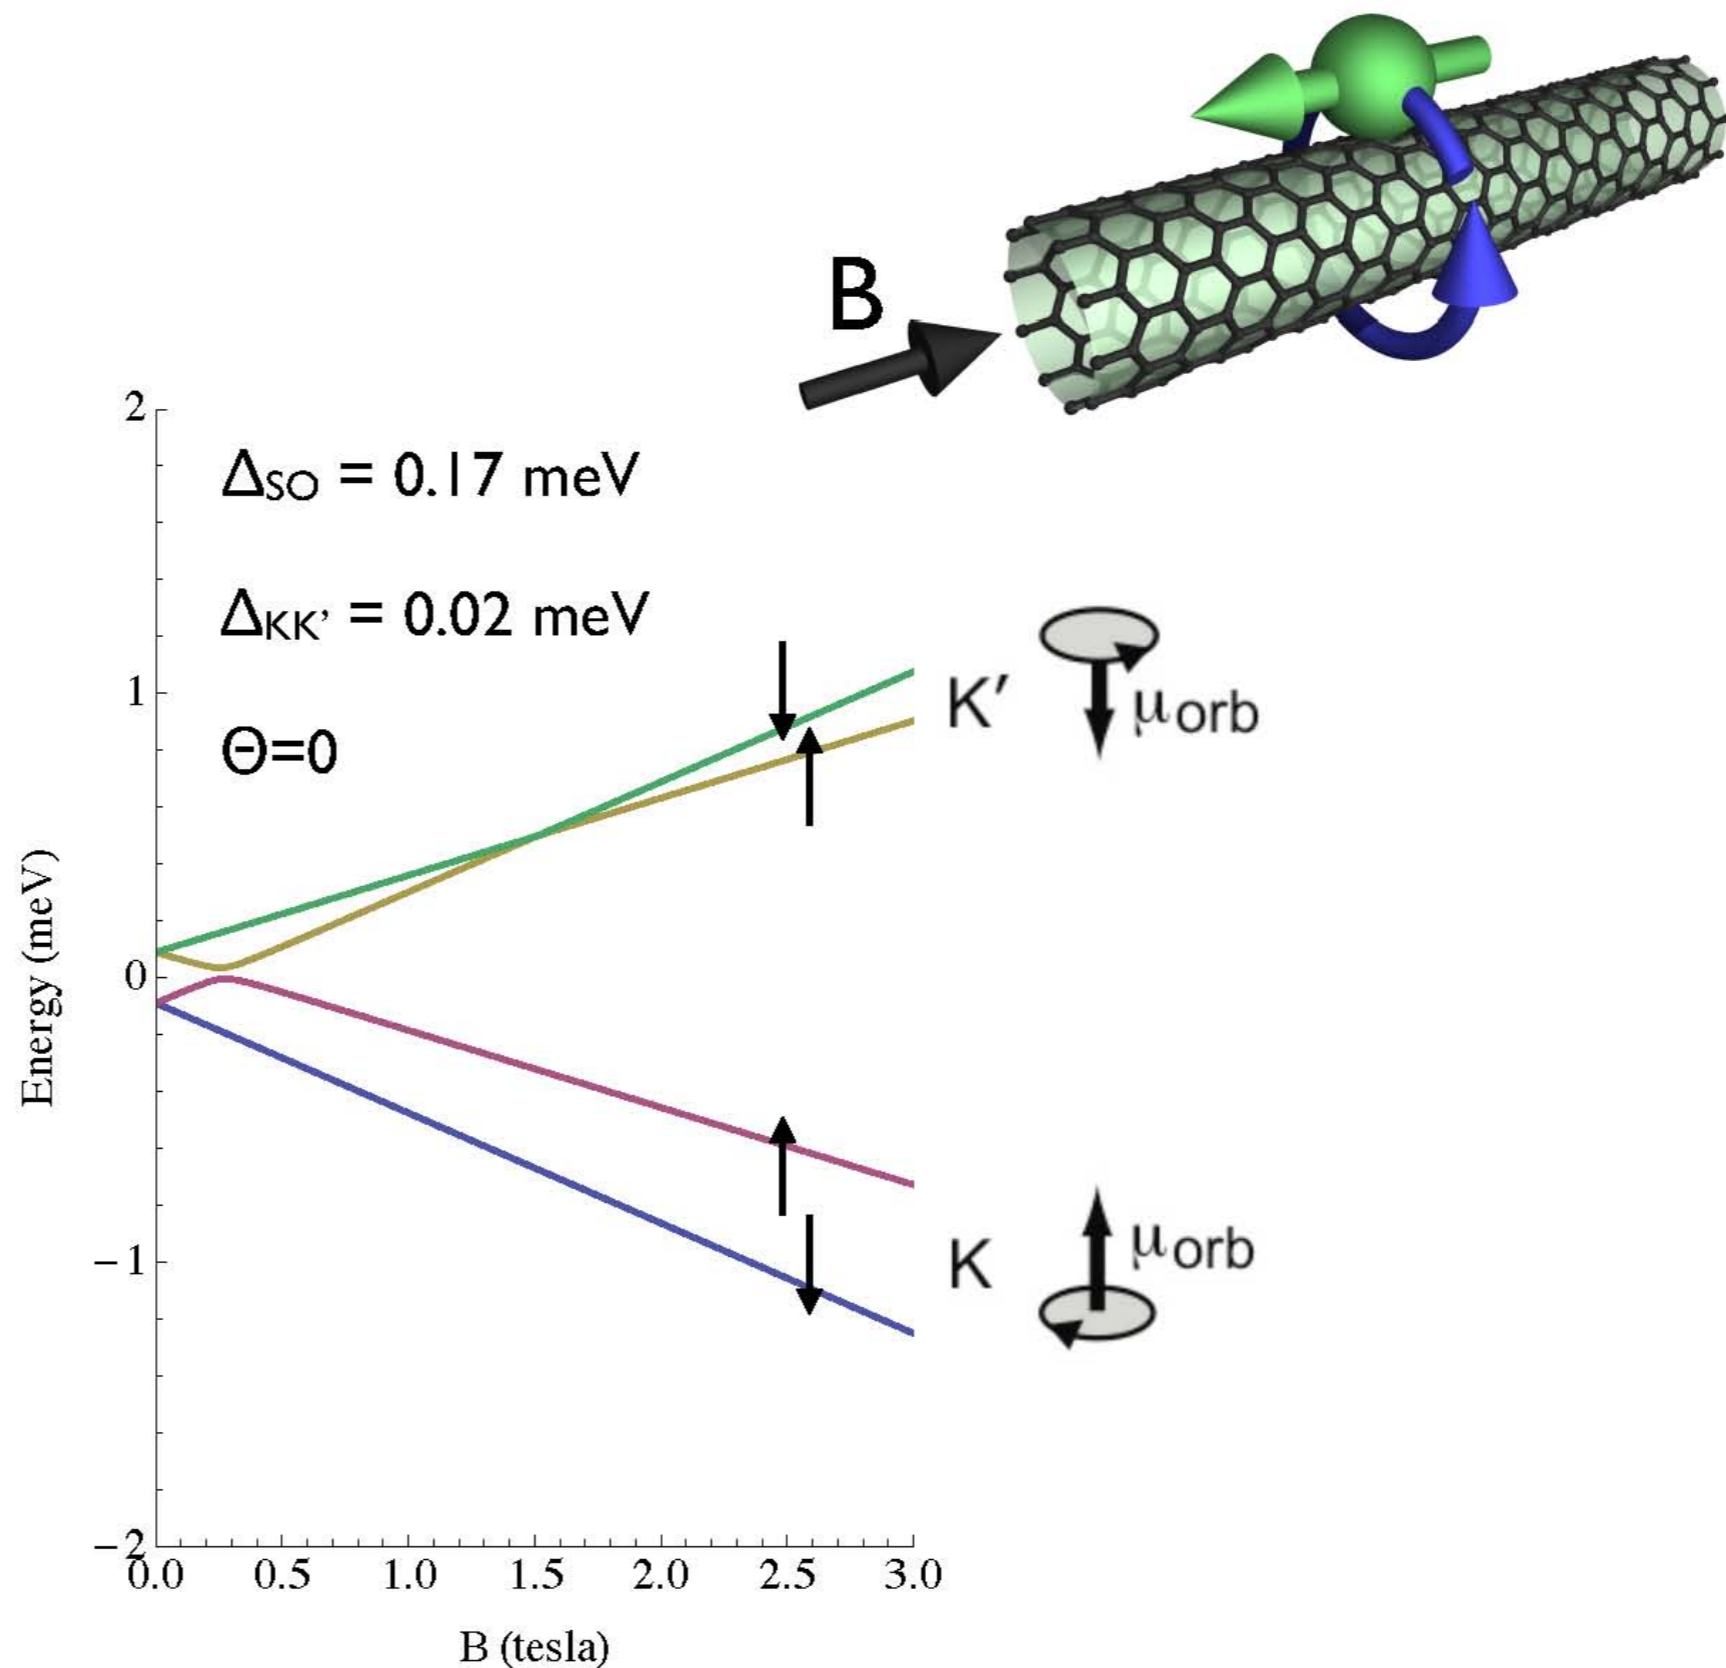



Levels in a single dot, including spin-orbit coupling, valley mixing, and misaligned field

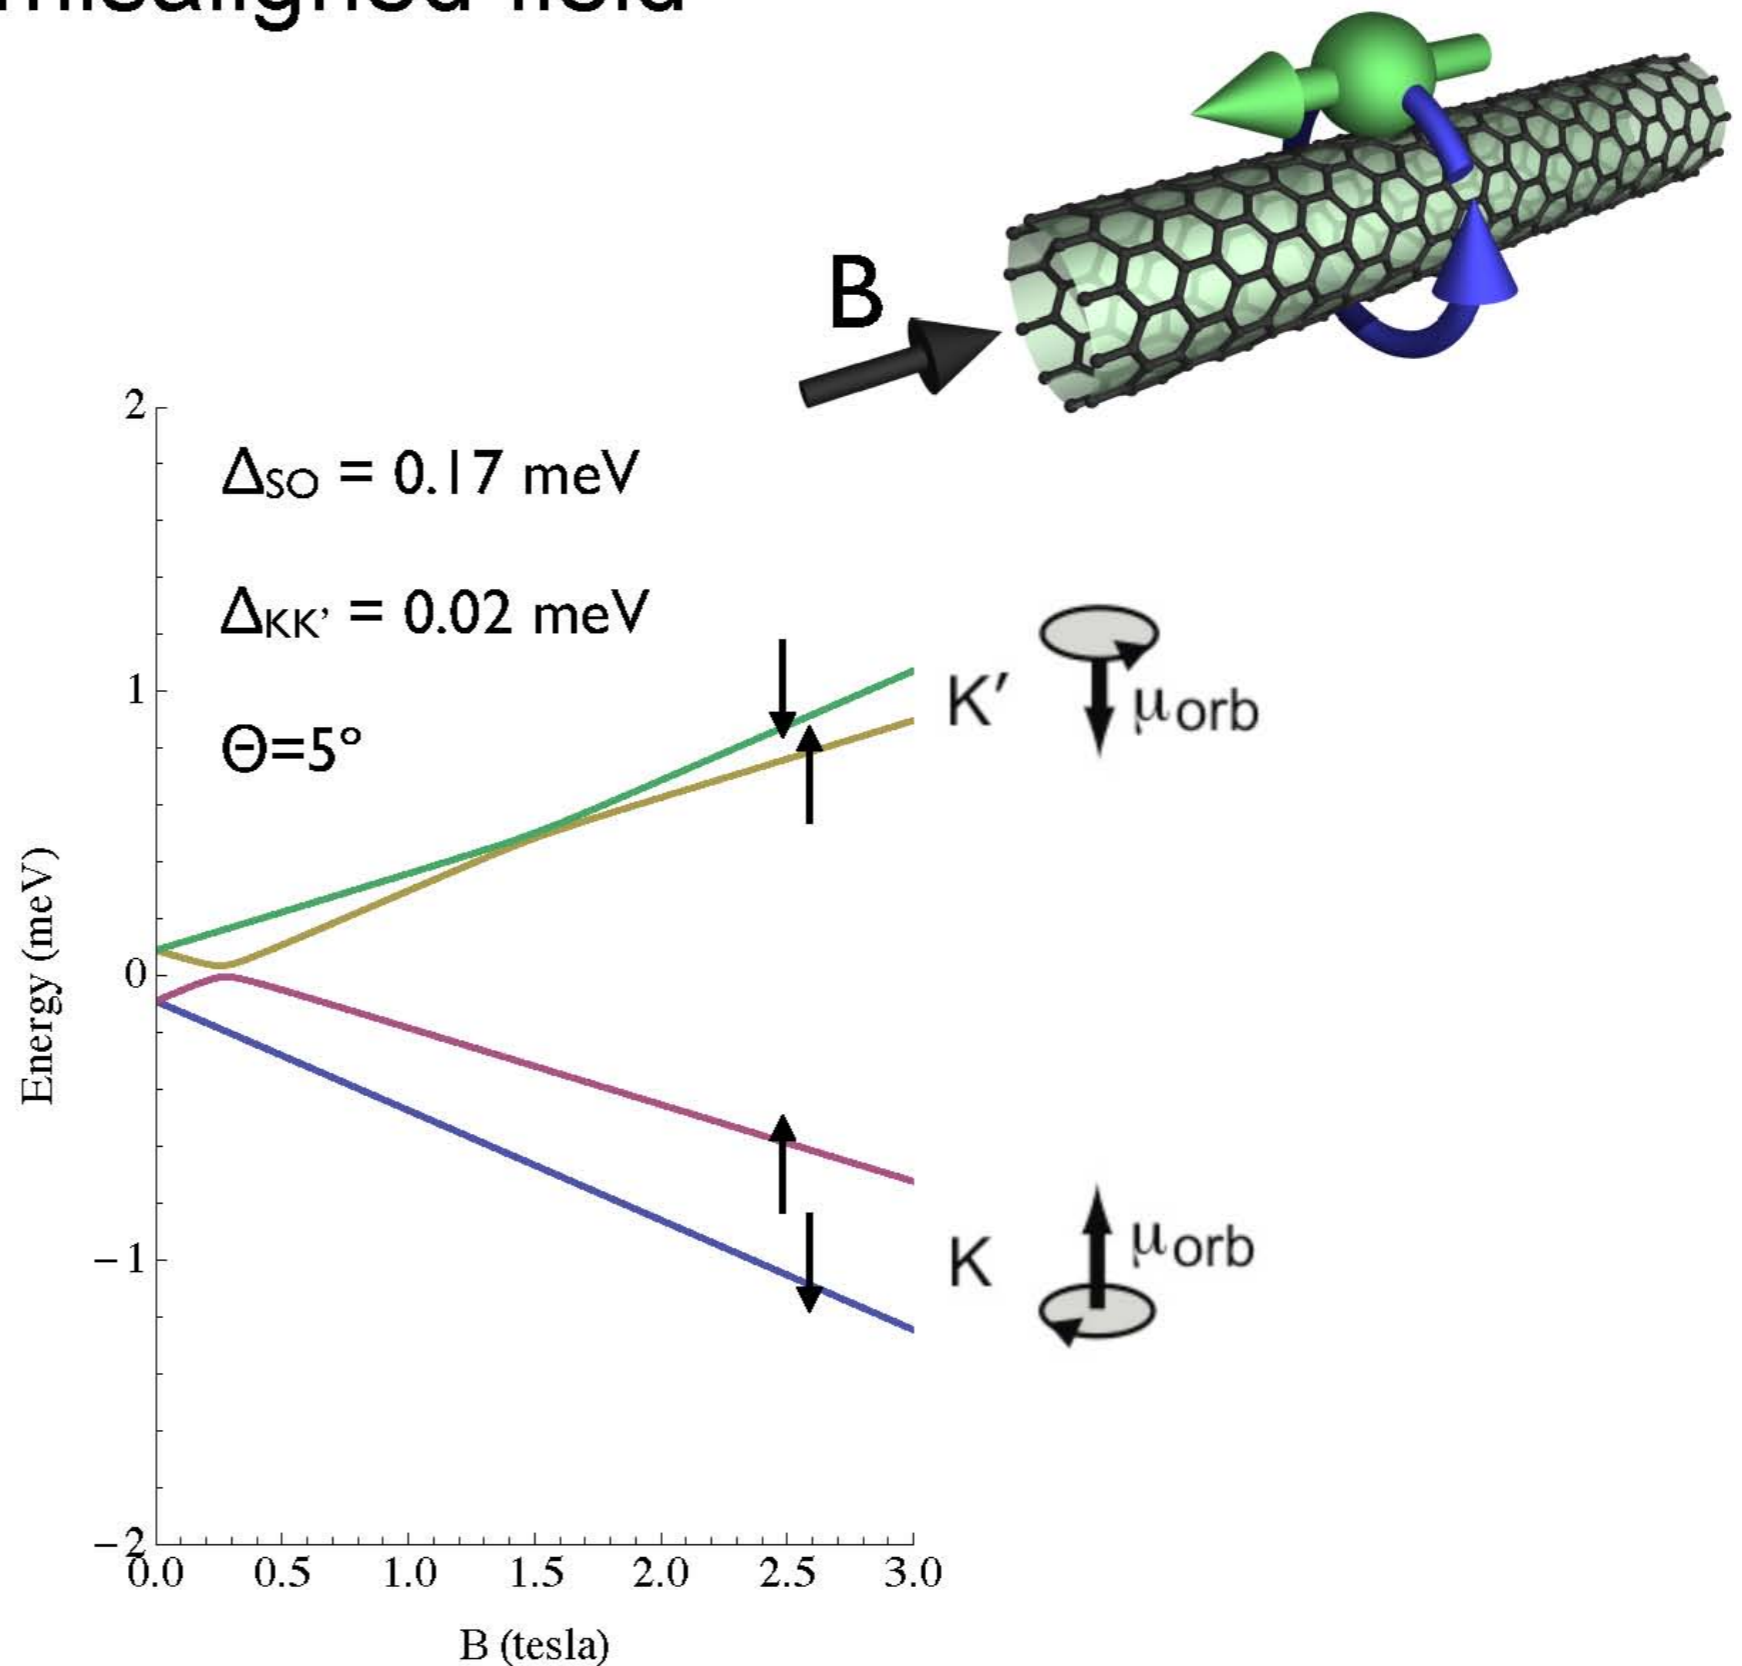

Levels in a single dot, including spin-orbit coupling, valley mixing, and misaligned field

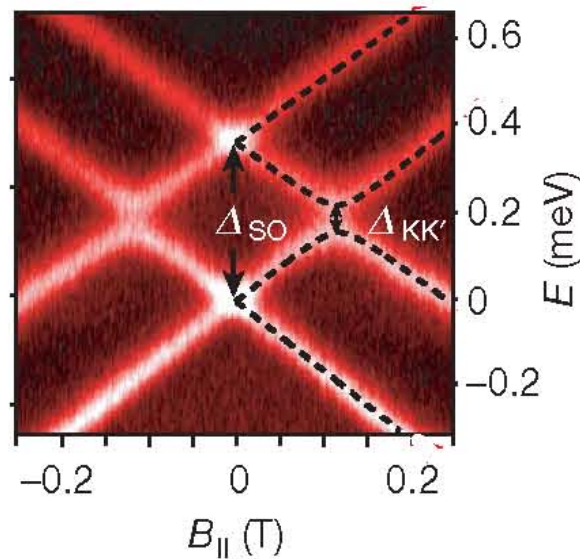


See Also
Kuemmeth, Ilani *et al.*
Nature **452**, 448 (2008)

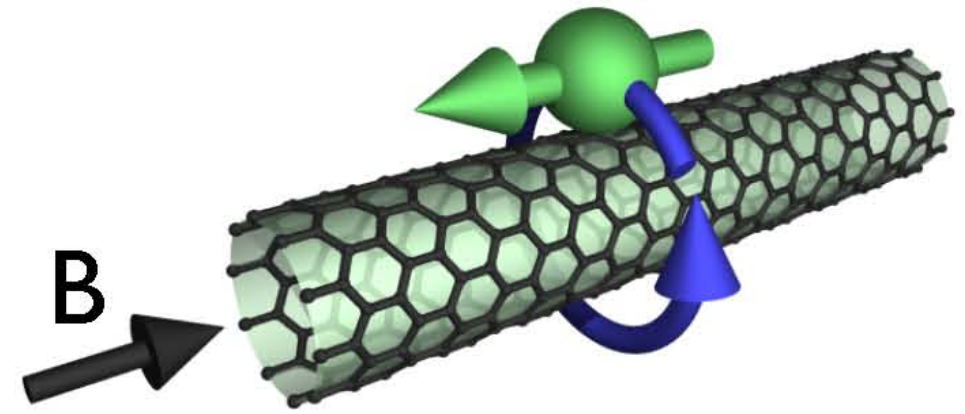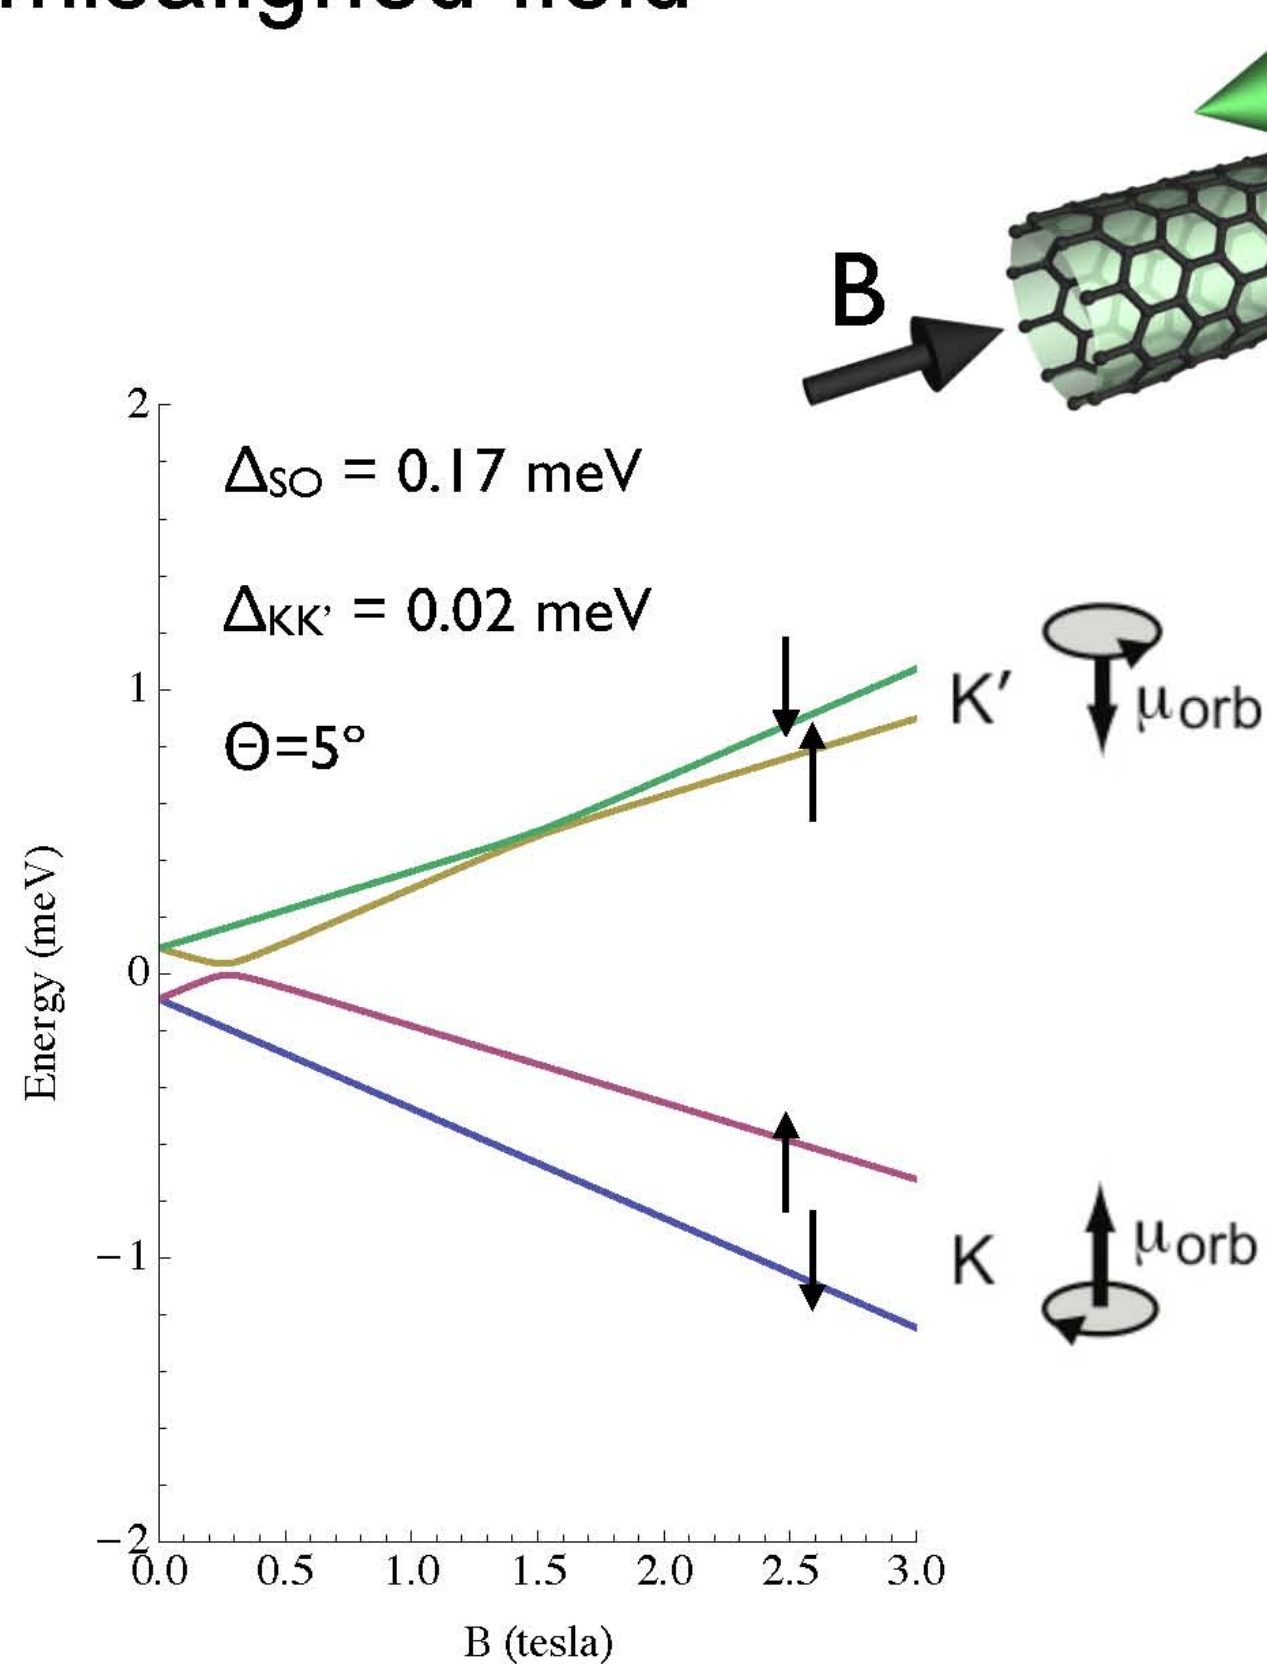


Levels in a single dot


single-particle levels

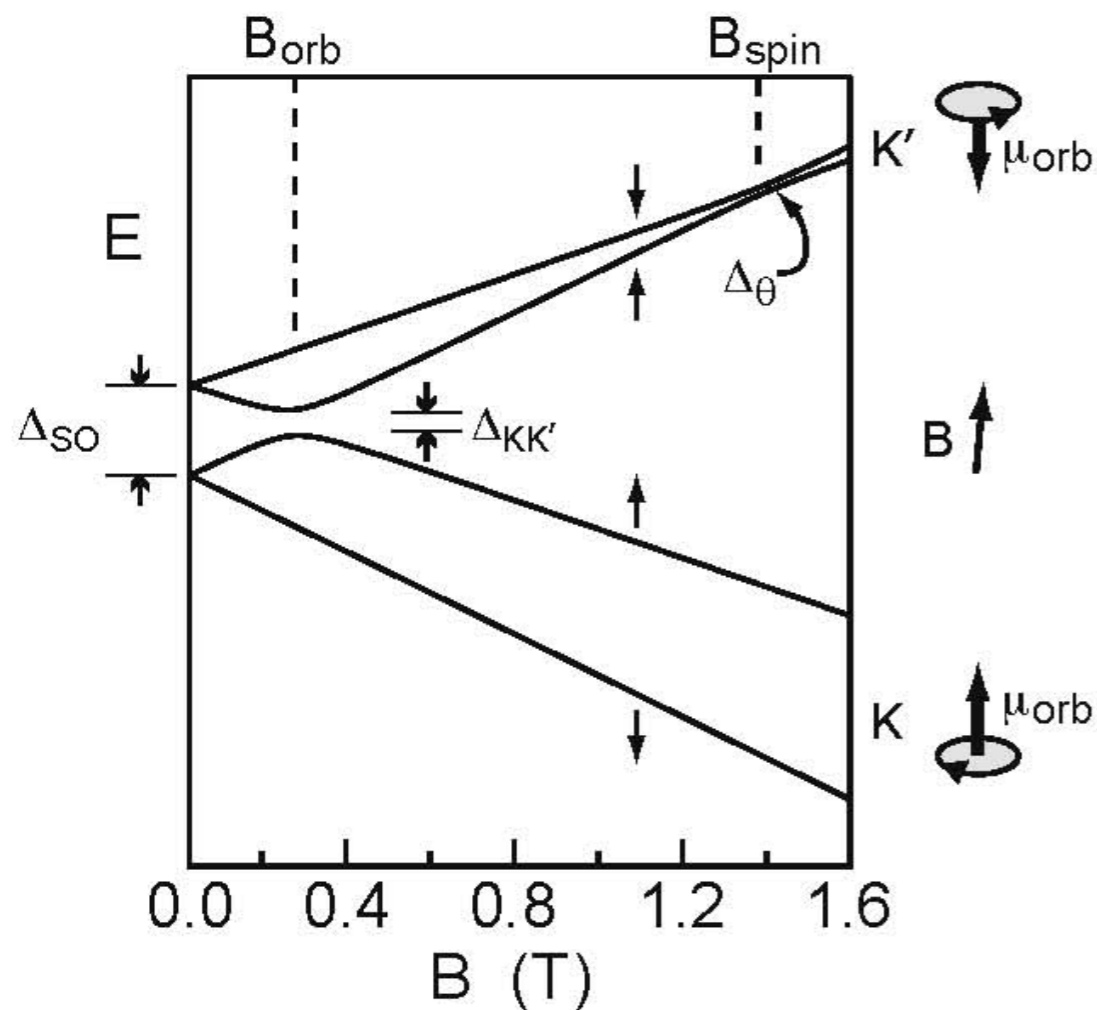

addition spectrum

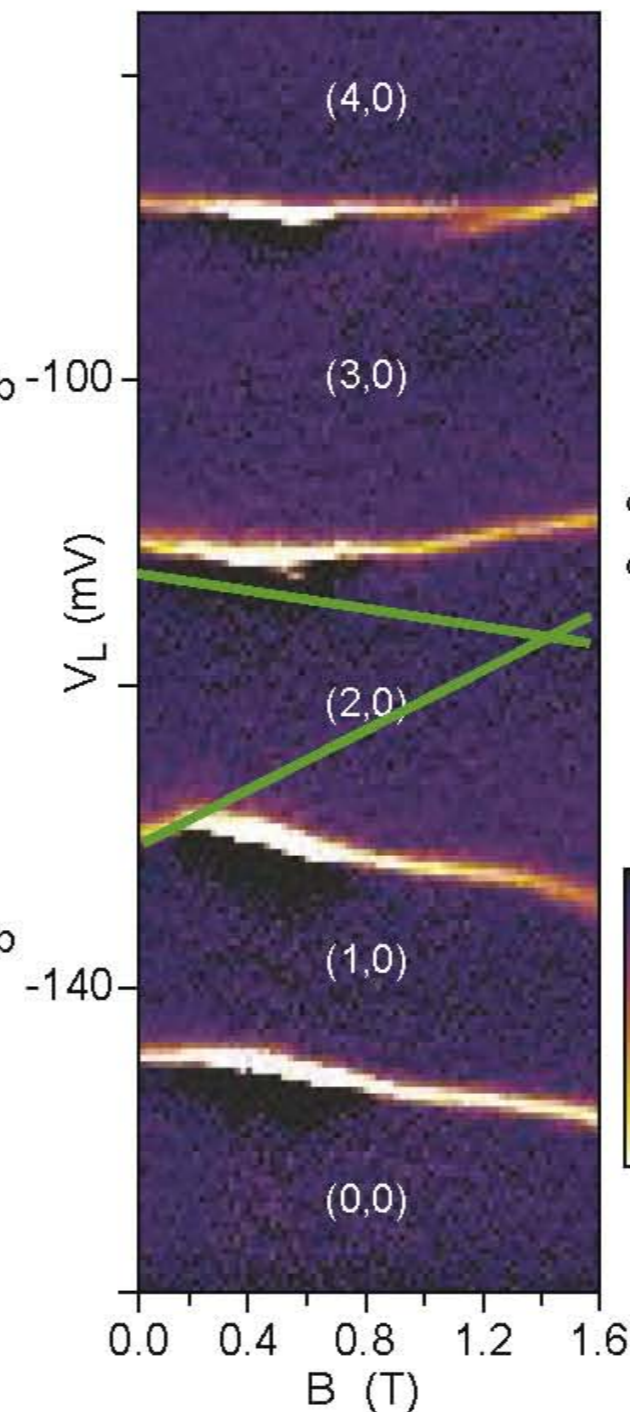


slopes differ
by $2\mu_B$

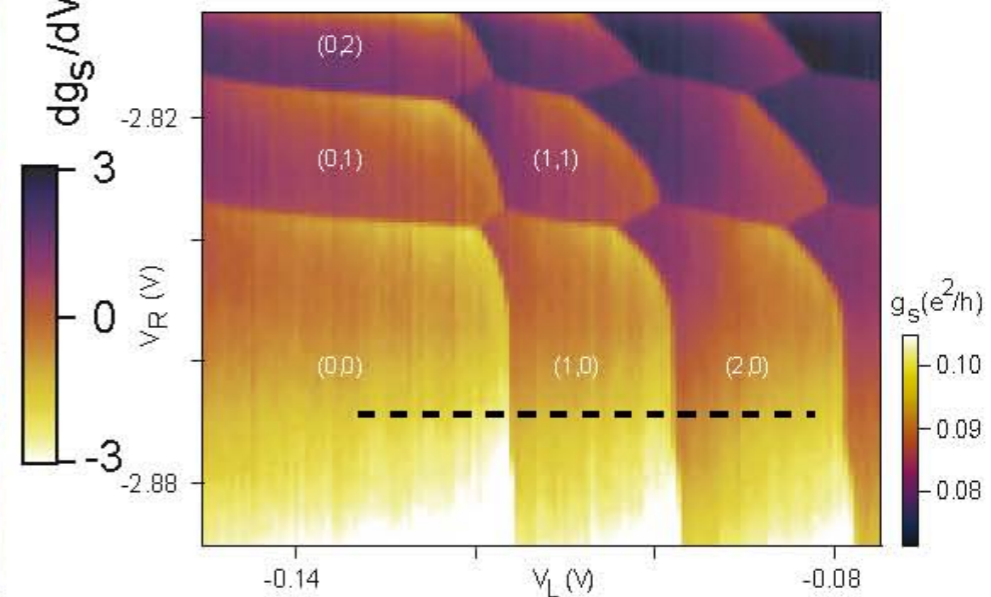

H. O. H. Churchill, et al. Phys. Rev. Lett. **102** 1066802 (2009).

(1,1) and (0,2) nanotube double dot states

one-electron states

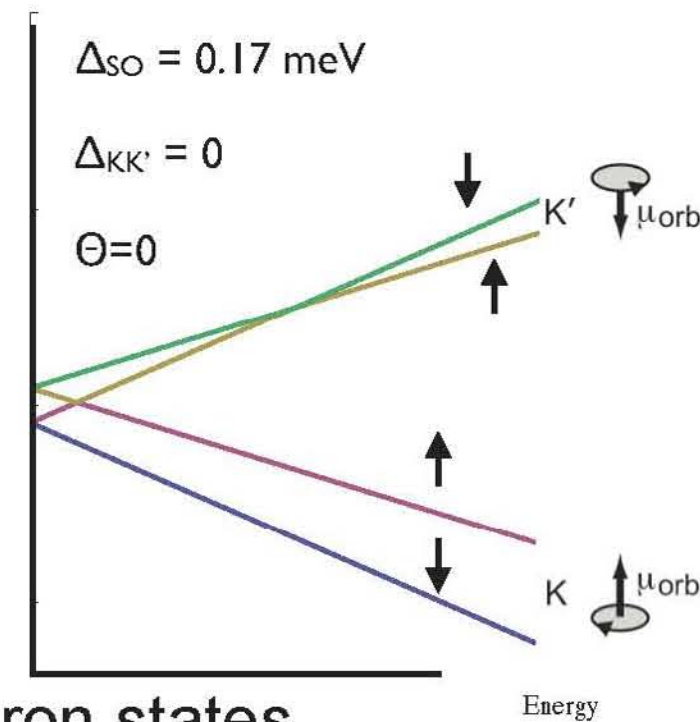


10 blocked and 6 unblocked two-electron states



$$\begin{aligned}
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K\rangle|K\rangle \otimes \mathbf{T}_+ \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K'\rangle|K'\rangle \otimes \mathbf{T}_- \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes (|K'\downarrow\rangle|K\uparrow\rangle + |K\uparrow\rangle|K'\downarrow\rangle) \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes (|K'\downarrow\rangle|K\uparrow\rangle - |K\uparrow\rangle|K'\downarrow\rangle)
 \end{aligned}$$

$$\begin{aligned}
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K\rangle|K\rangle \otimes \mathbf{T}_0 \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K'\rangle|K'\rangle \otimes \mathbf{T}_0 \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes (|K'\rangle|K\rangle + |K\rangle|K'\rangle) \otimes \mathbf{T}_- \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes (|K'\rangle|K\rangle + |K\rangle|K'\rangle) \otimes \mathbf{T}_+ \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes |K'\rangle|K'\rangle \otimes \mathbf{S} \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes |K\rangle|K\rangle \otimes \mathbf{S} \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes (|K'\rangle|K\rangle - |K\rangle|K'\rangle) \otimes \mathbf{T}_+ \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes (|K'\rangle|K\rangle - |K\rangle|K'\rangle) \otimes \mathbf{T}_-
 \end{aligned}$$

$$\begin{aligned}
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K\rangle|K\rangle \otimes \mathbf{T}_- \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K'\rangle|K'\rangle \otimes \mathbf{T}_+ \\
 &(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes (|K'\uparrow\rangle|K\downarrow\rangle + |K\downarrow\rangle|K'\uparrow\rangle) \\
 &(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes (|K'\uparrow\rangle|K\downarrow\rangle - |K\downarrow\rangle|K'\uparrow\rangle)
 \end{aligned}$$

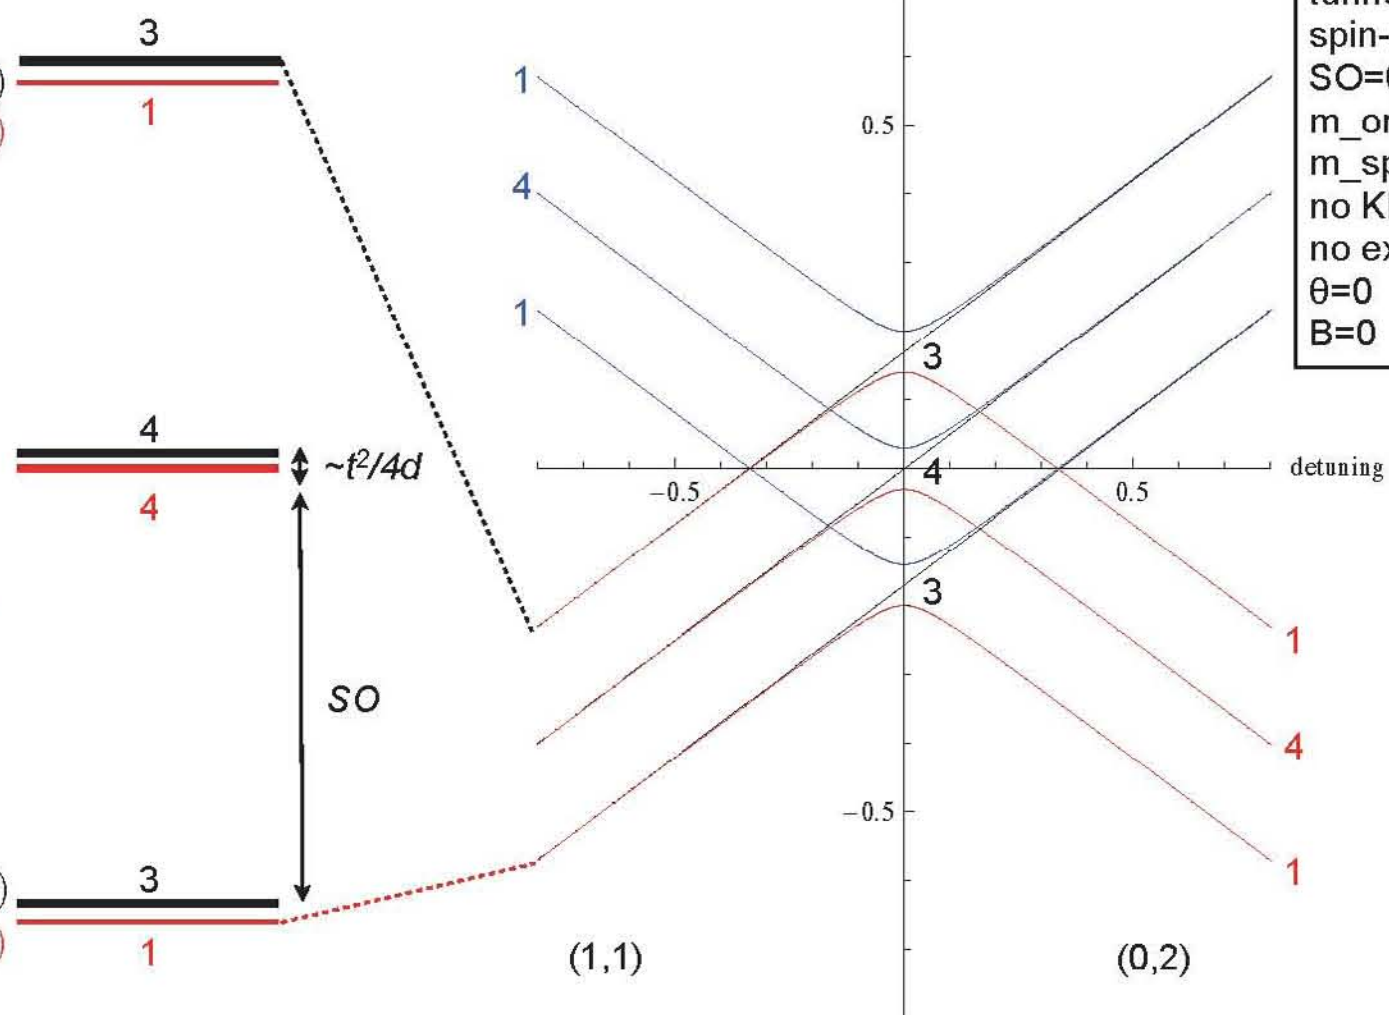


Pauli blockade in carbon nanotube double dot despite spin-orbit coupling

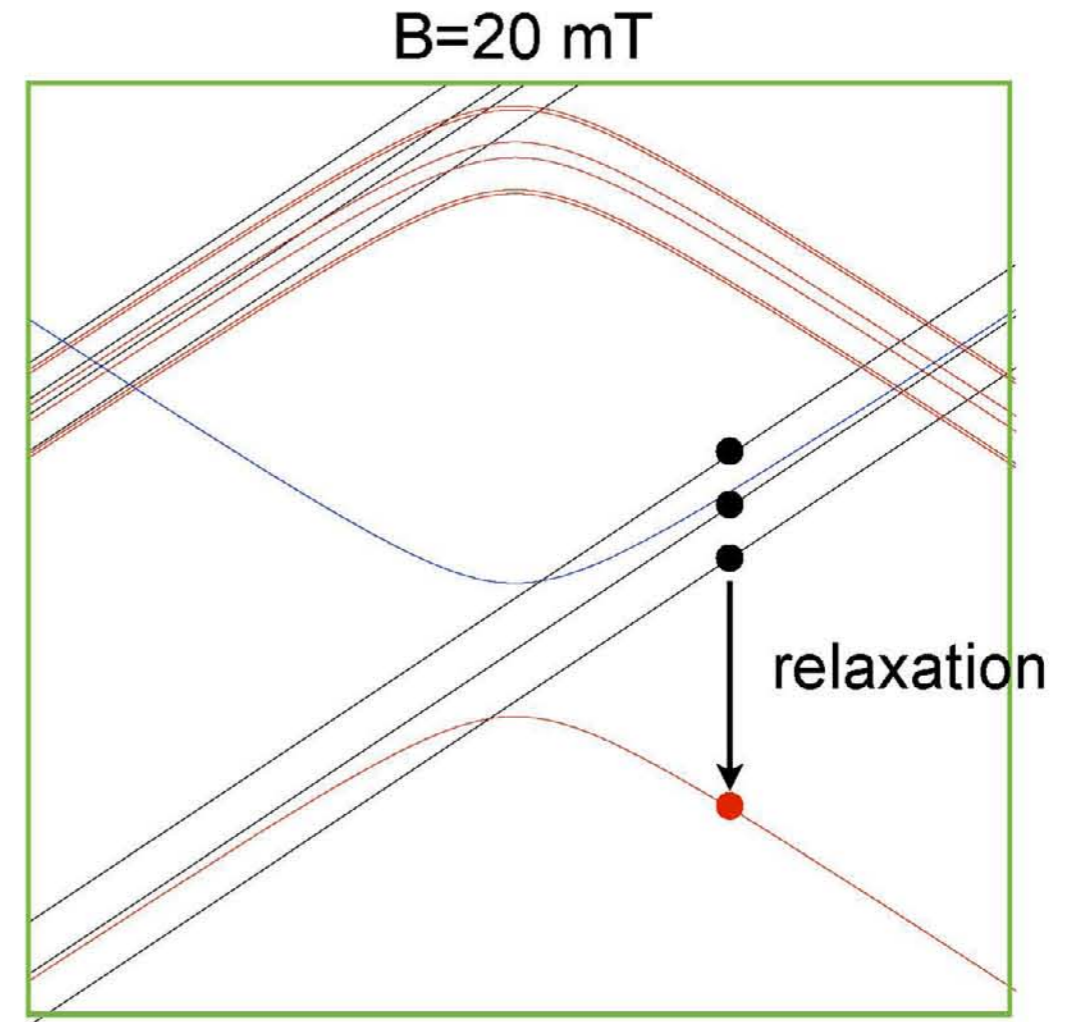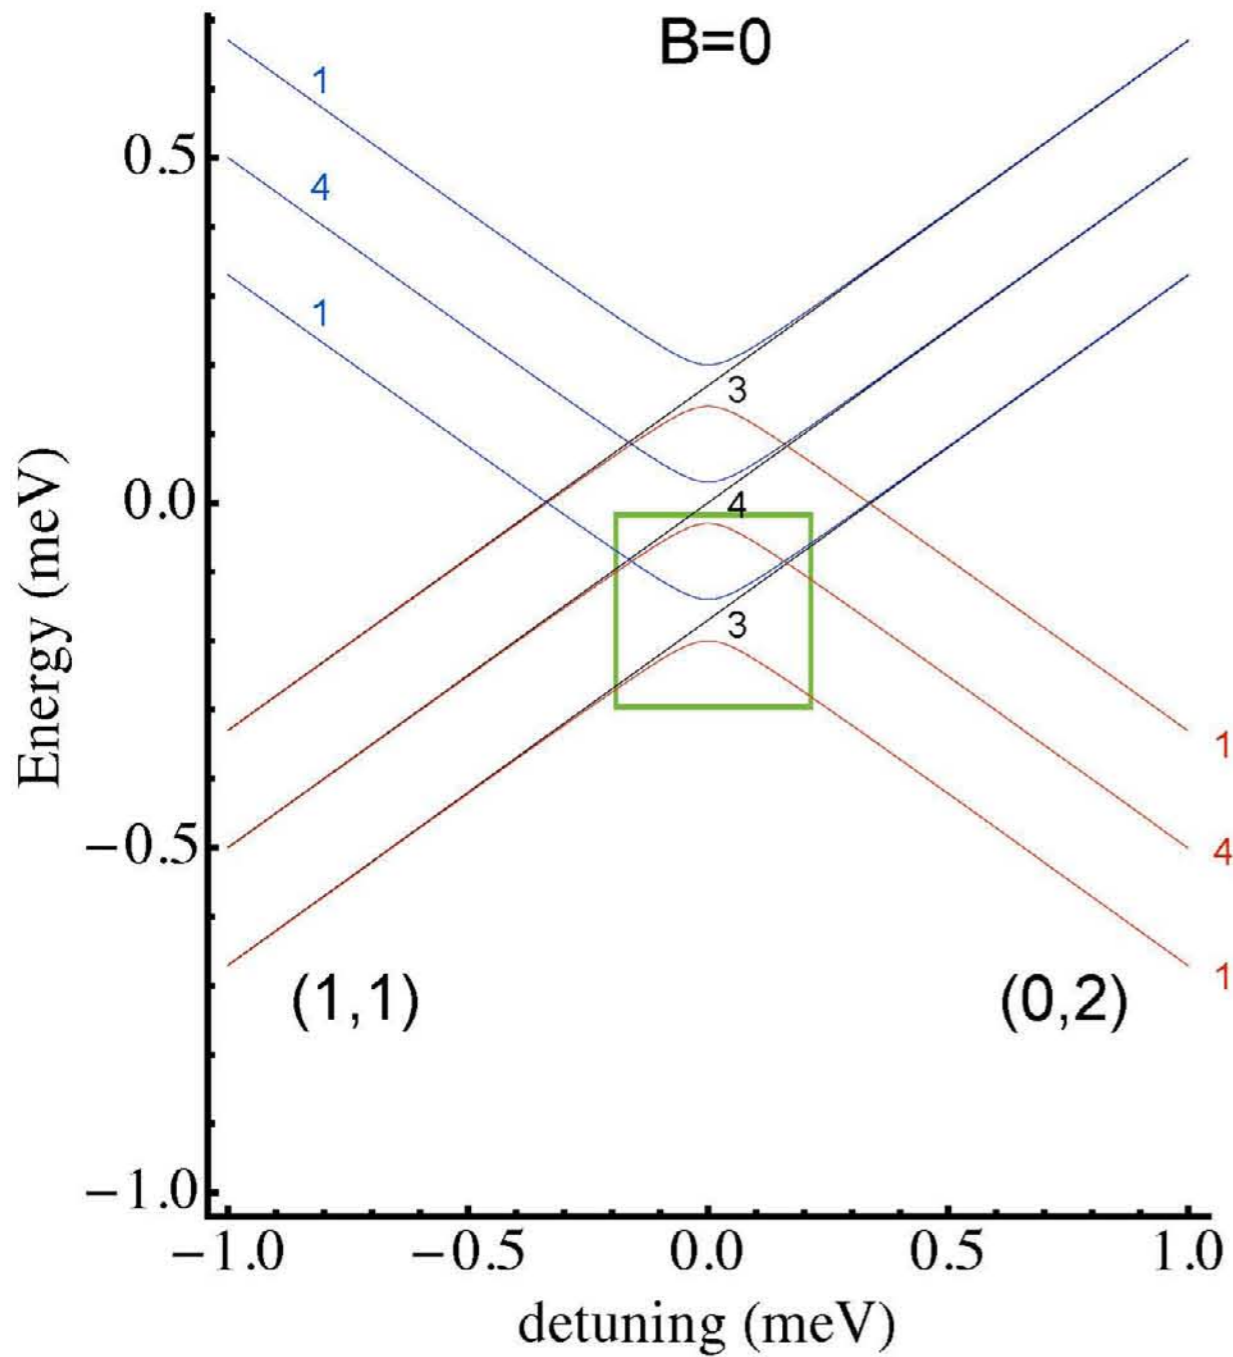

- $(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K'\rangle|K'\rangle \otimes \mathbf{T}_+$
- $(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes (|K' \uparrow\rangle|K \downarrow\rangle + |K \downarrow\rangle|K' \uparrow\rangle)$
- $(|R\rangle|L\rangle - |L\rangle|R\rangle) \otimes |K\rangle|K\rangle \otimes \mathbf{T}_-$
- $(|R\rangle|L\rangle + |L\rangle|R\rangle) \otimes (|K' \uparrow\rangle|K \downarrow\rangle - |K \downarrow\rangle|K' \uparrow\rangle)$



lowest two-particle states have different spin & valley symmetries

T1 sequence


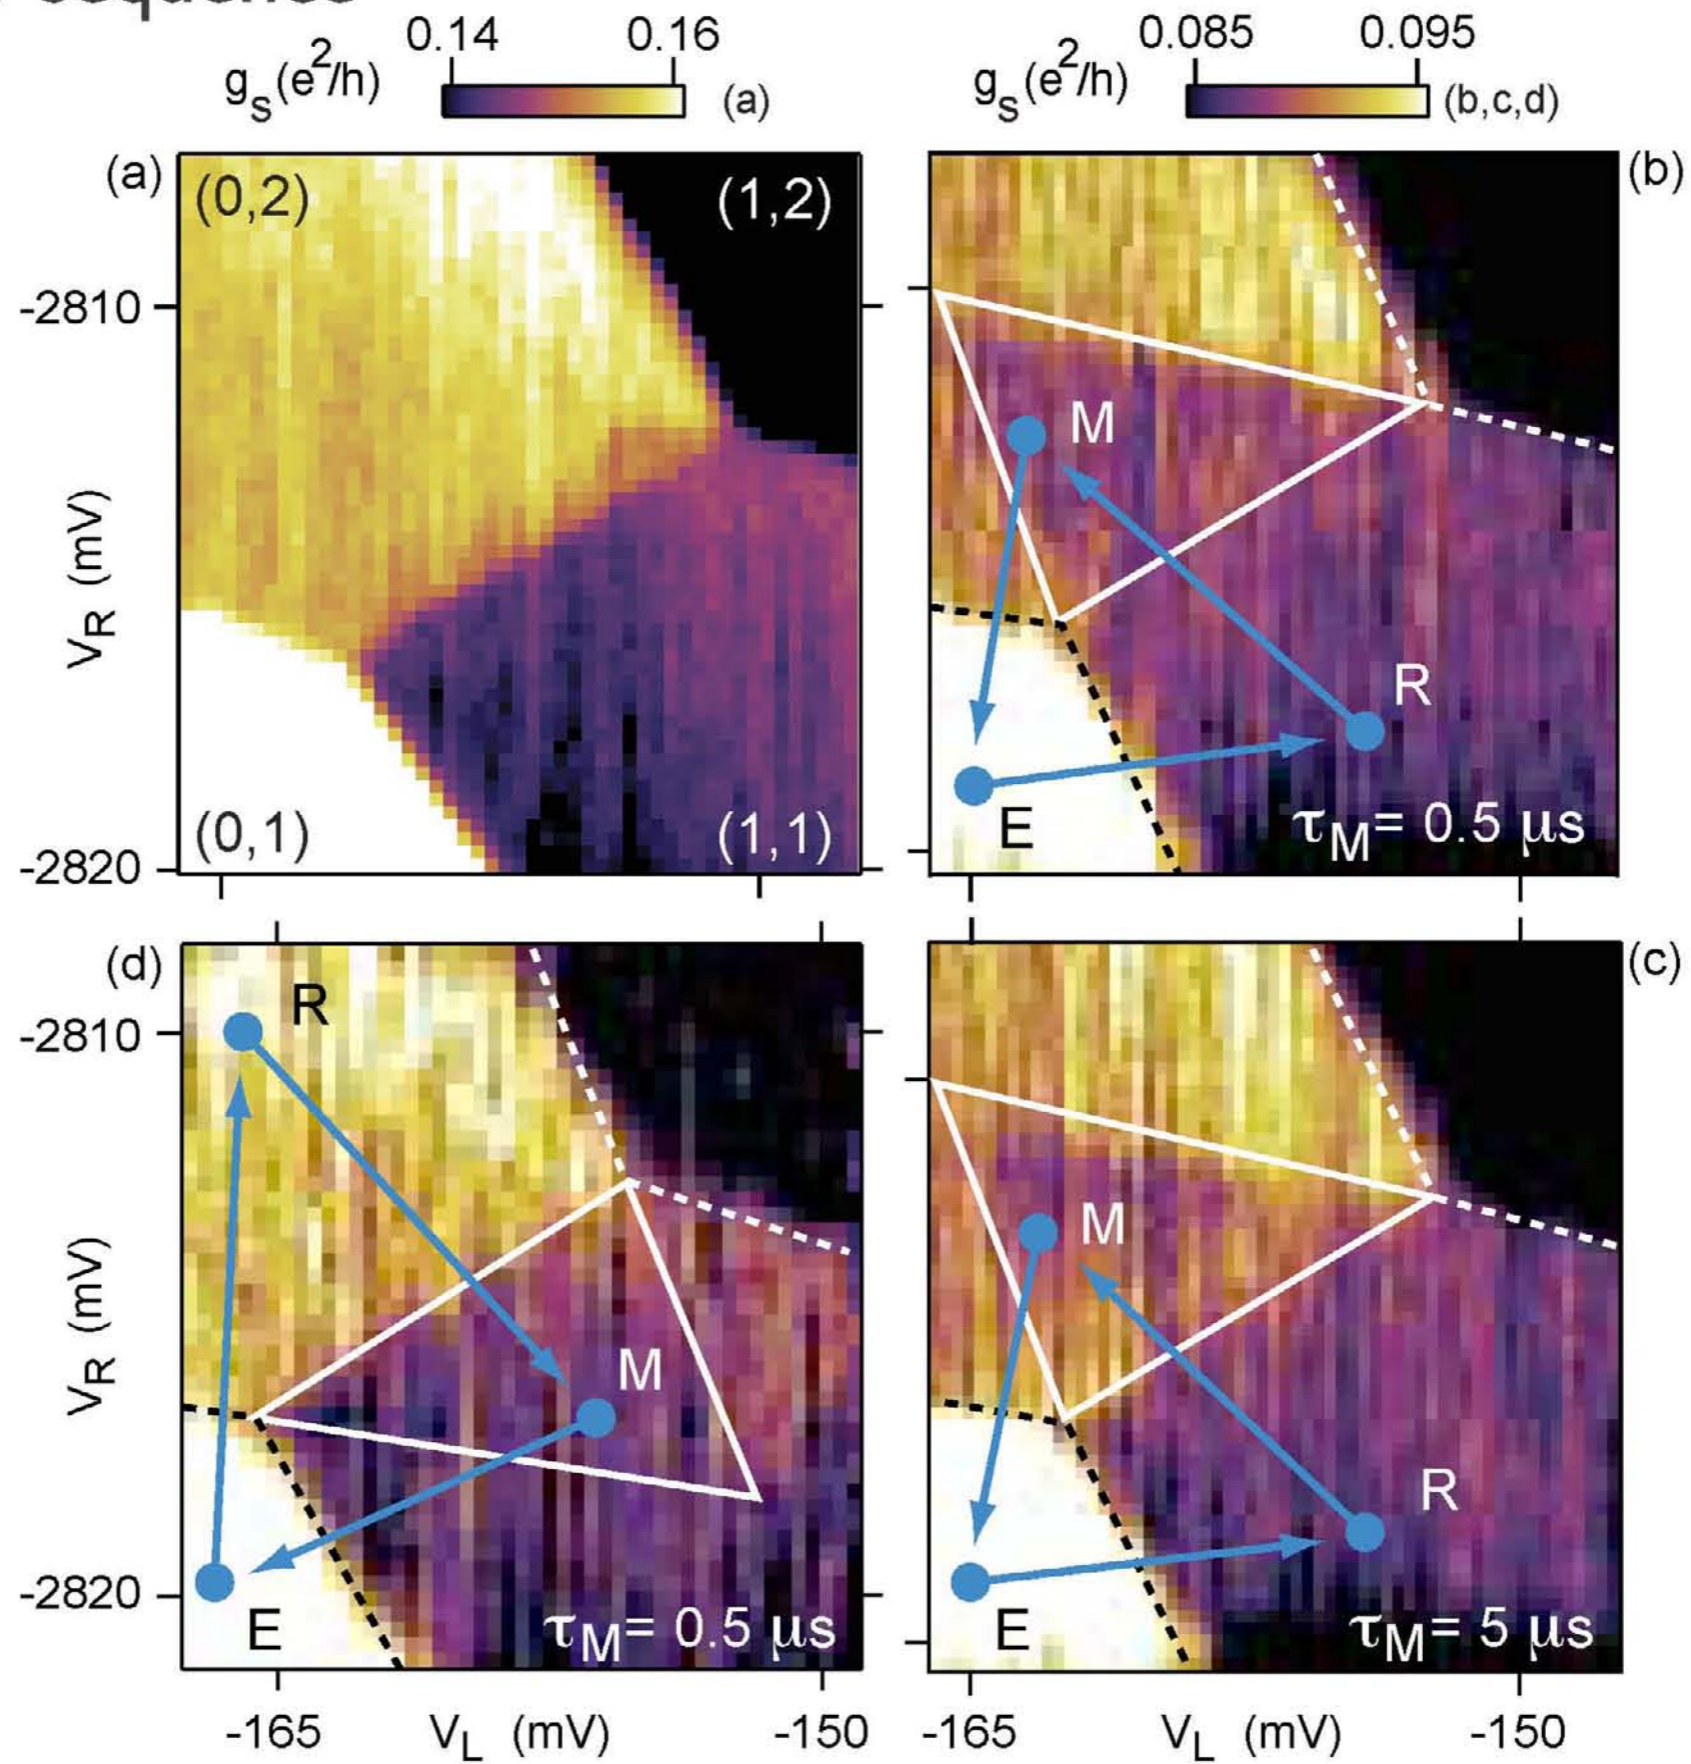


B-dependence of relaxation rate





Charge sensing

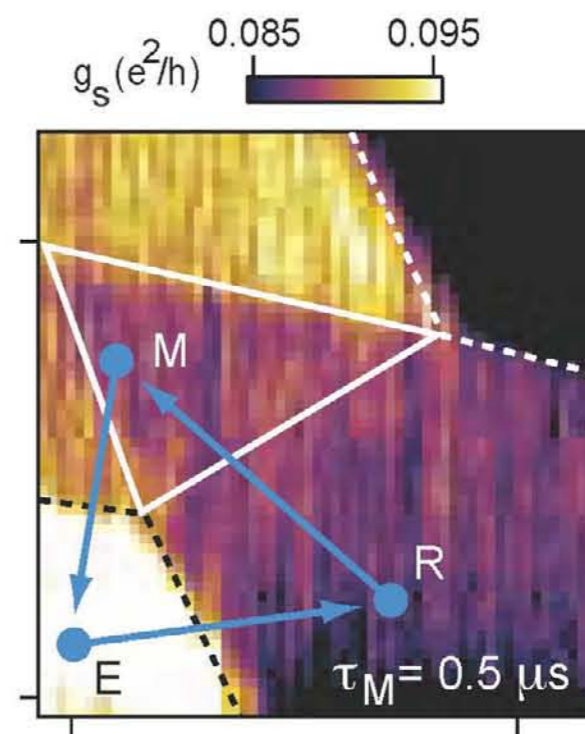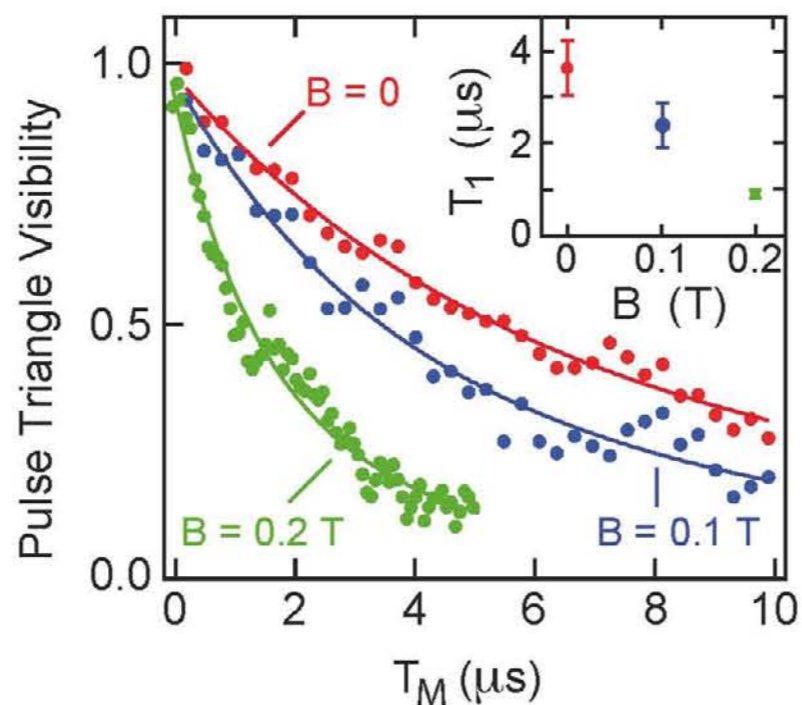

Transport

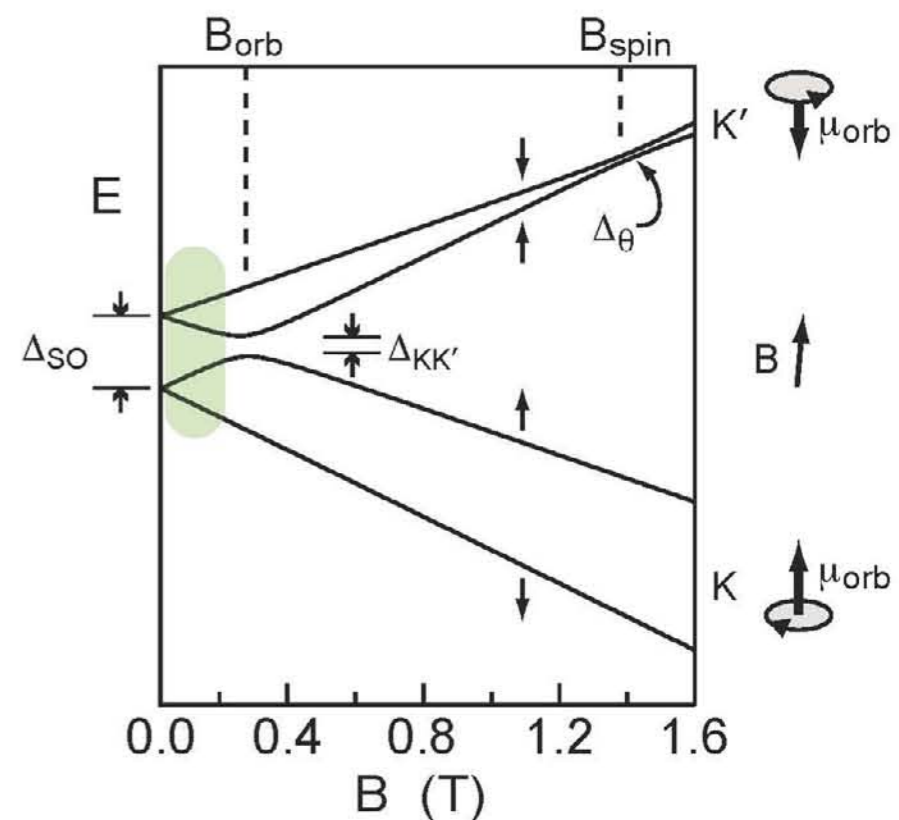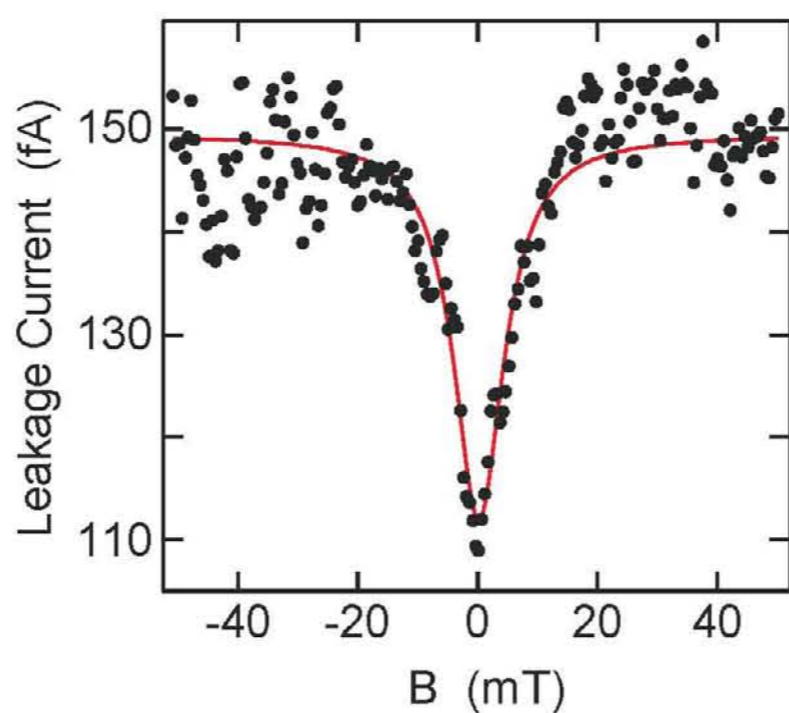



B-dependence of relaxation rate

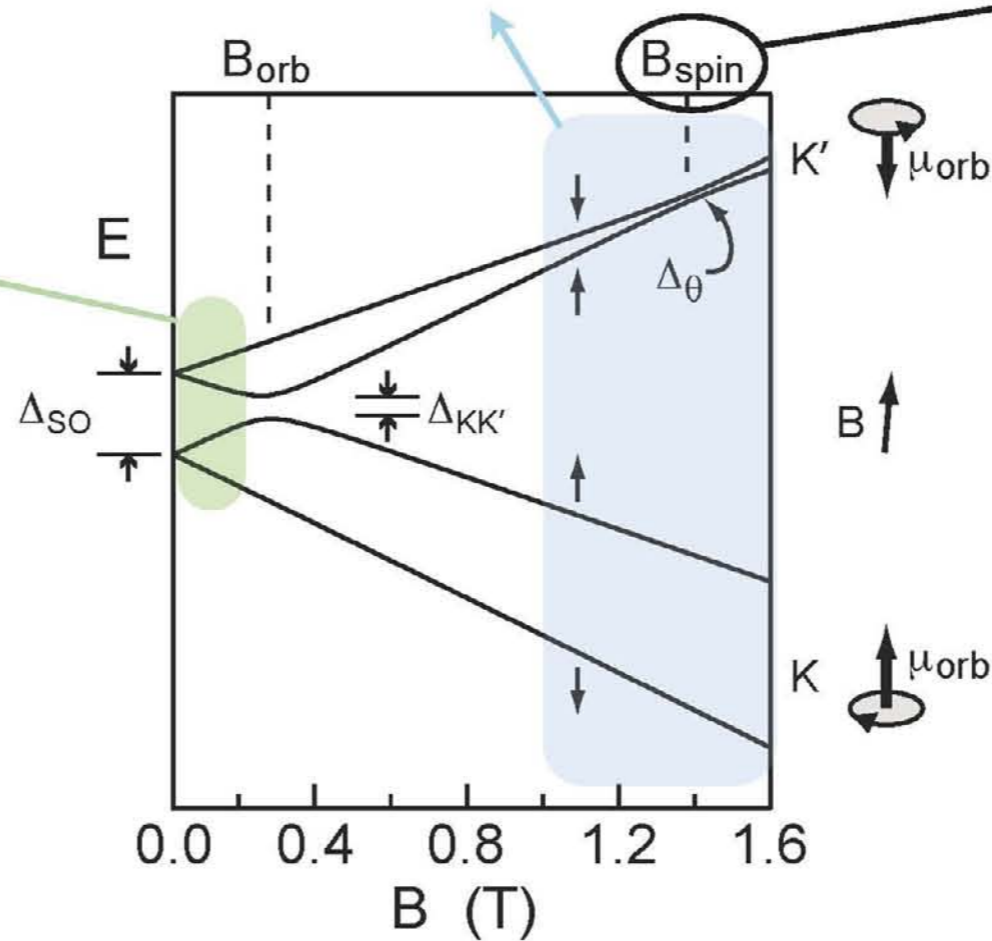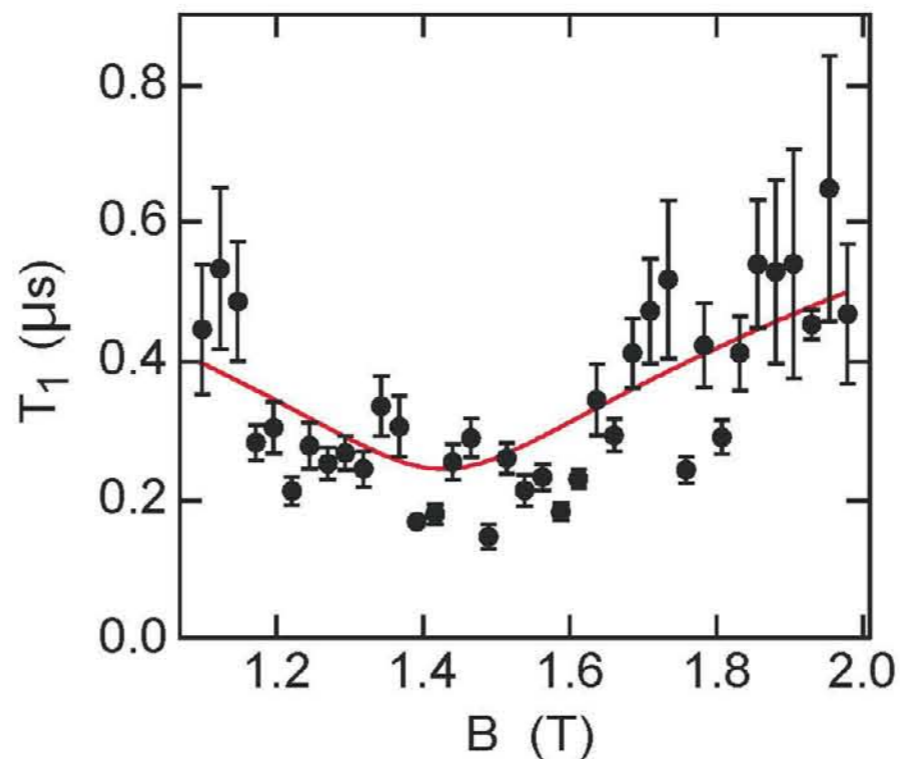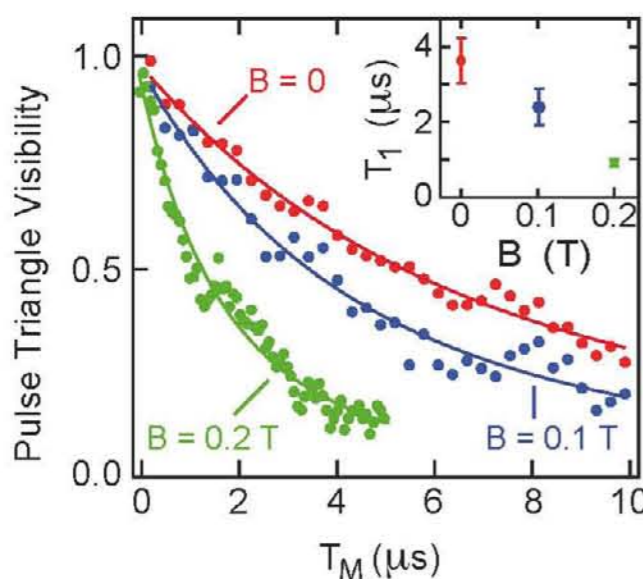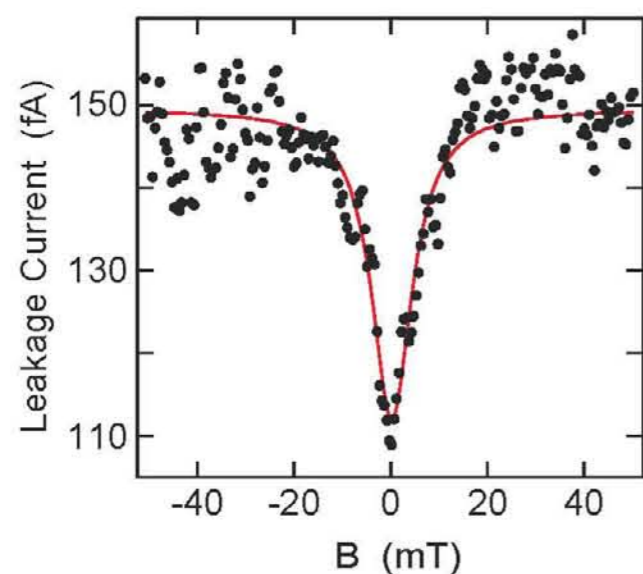

$$T_1 \propto \sqrt{\text{splitting}}$$

Bulaev et al. PRB **77**,
235301 (2008)


Inhomogeneous Dephasing

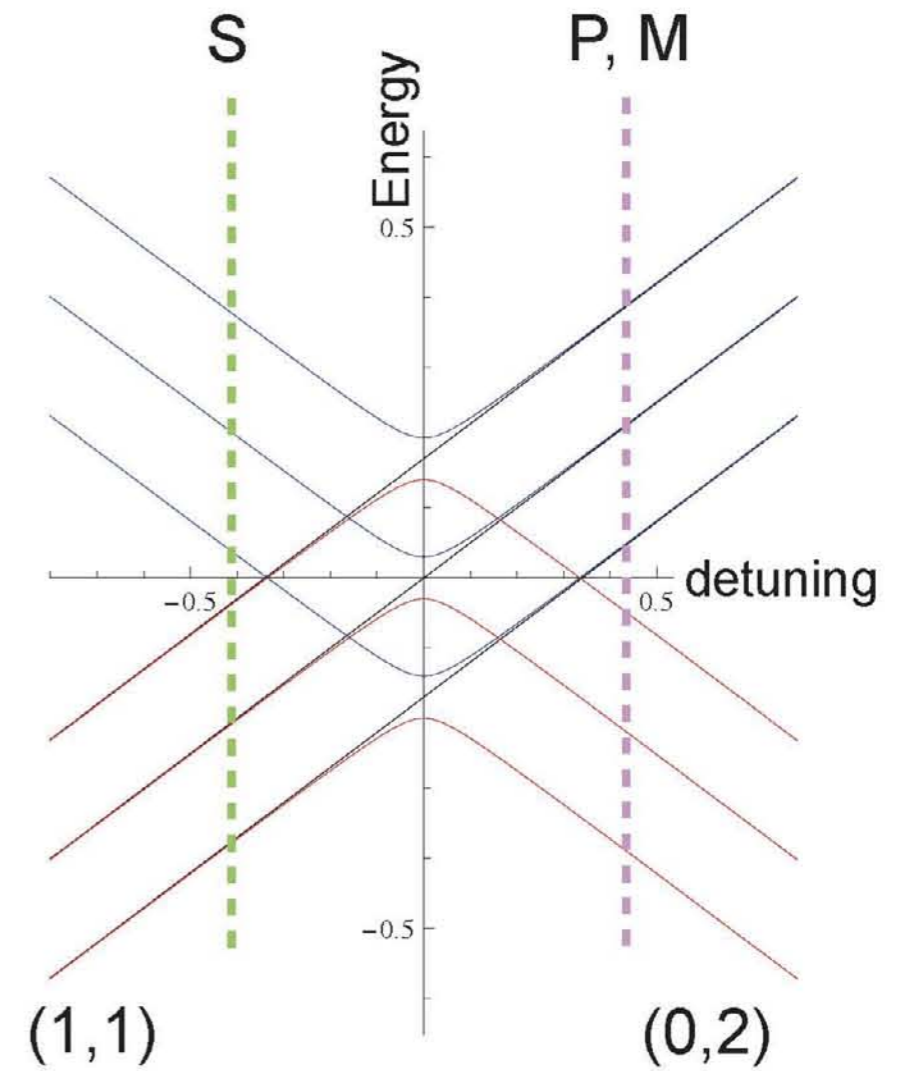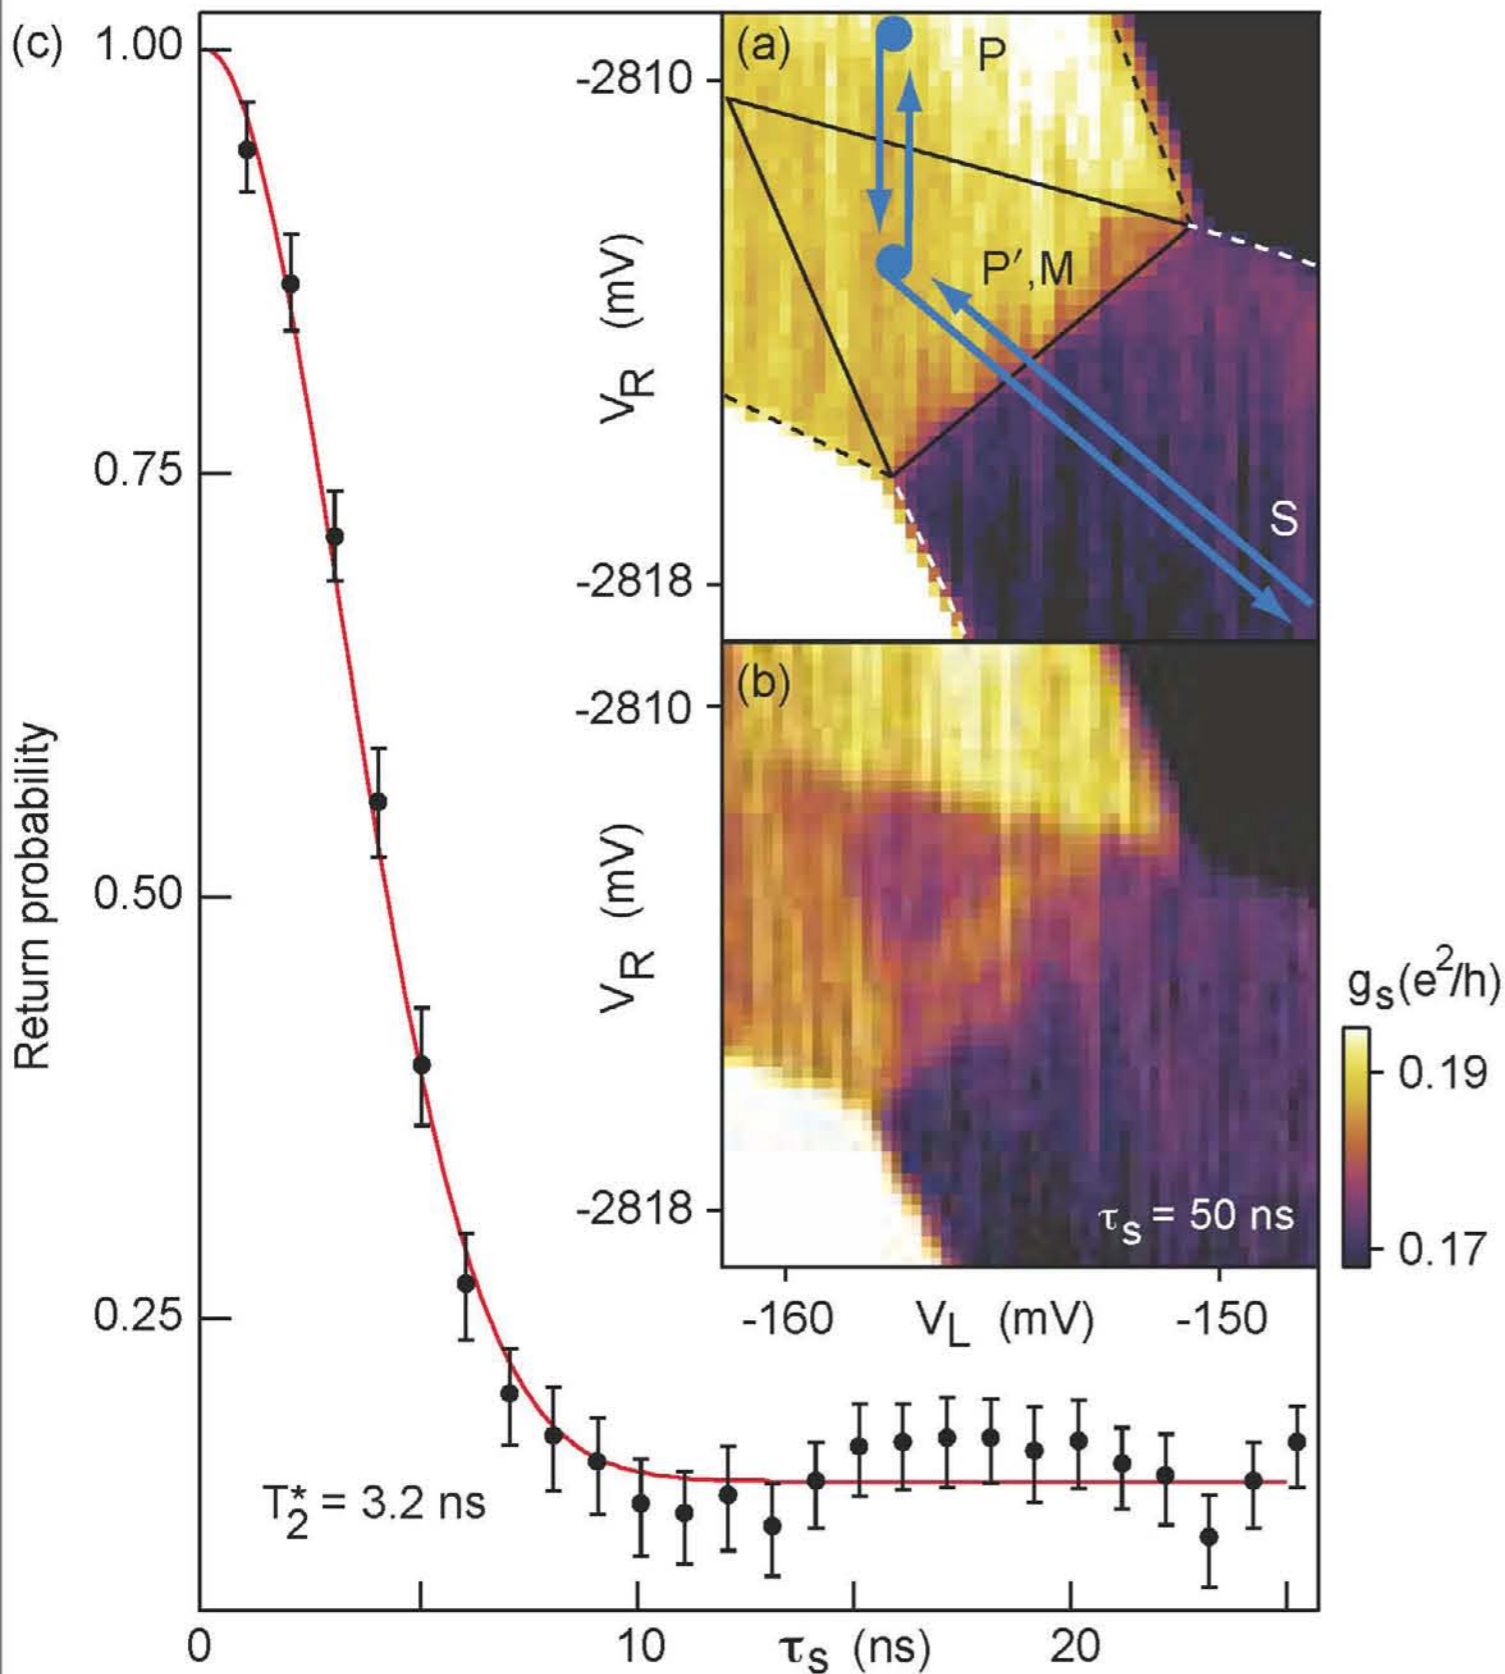


$$T_2^* = \hbar / g \mu_B \delta B_{\text{nuc}}^{\parallel} = 3.2 \text{ ns}$$

$$\longrightarrow \delta B_{\text{nuc}}^{\parallel} = 1.8 \text{ mT} \approx B_{\text{nuc}} / 2$$



Summary

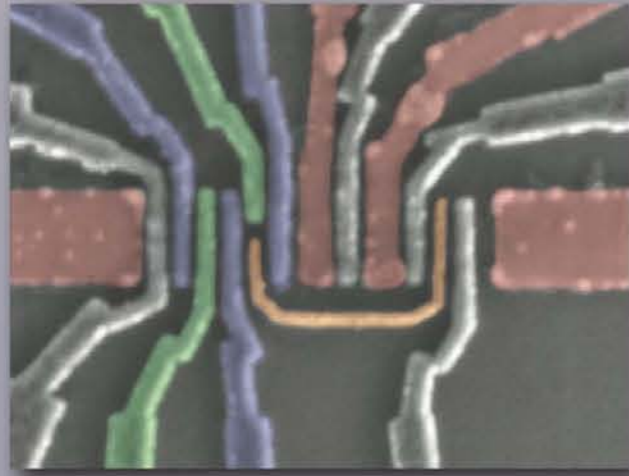

nanotubes can form gate-controlled dots with controlled hyperfine coupling

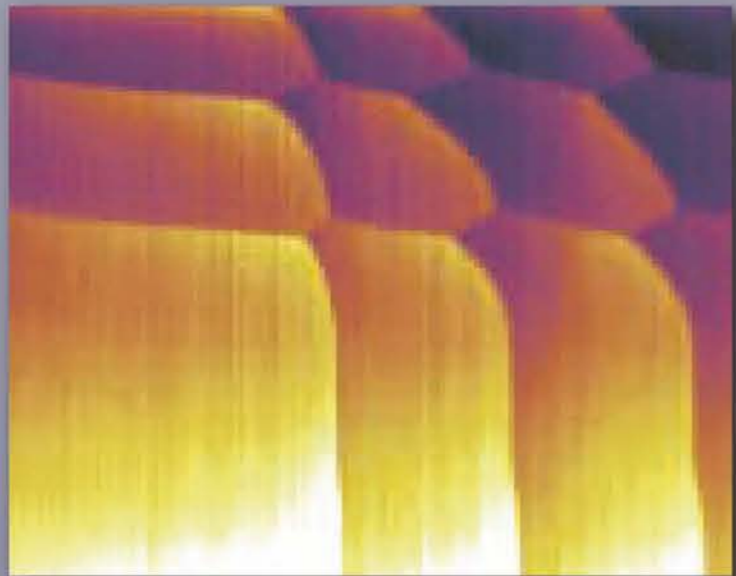

few-electron regime accessible using charge sensing readout

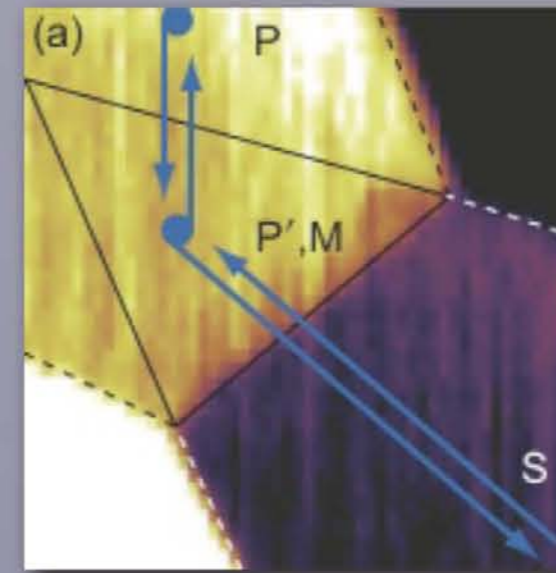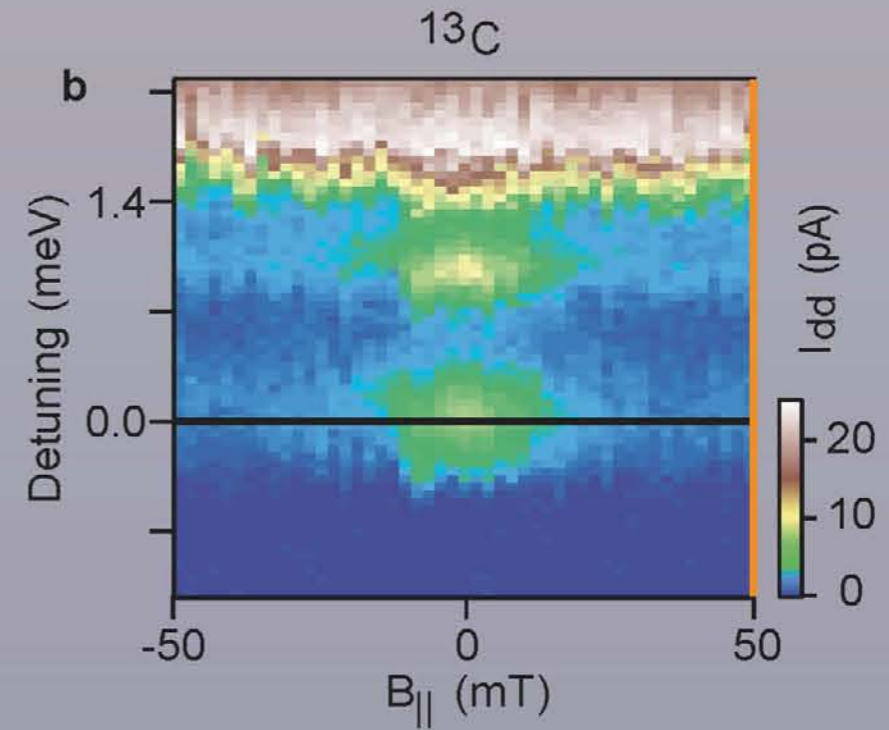

Both many-electron Pauli Blockade and two-electron T_2^* measurements indicate large hyperfine coupling in nanotubes